

Modeling of Critical Blank Holder Force Based on a Gap Limit and Unbending Strain Energy in Deep Drawing Process

Susila Candra^{#1}, I Made Londen Batan^{#2}, Wajan Berata^{#3}, Agus Sigit Pramono^{#4}

[#] Departemant of Mechanical Engineering, Faculty of Industrial Technology
Institute of Technology Sepuluh Nopember (ITS), Sukolilo, Surabaya, 60111, East Java, Indonesia

^{*} Departement of Manufacturing Engineering, Faculty of Engineering,
University of Surabaya, Jl. Raya Kalirungkut, Surabaya, 60293, East Java, Indonesia

¹ susilac@yahoo.com,

² londbatan@me.its.ac.id,

³ wayanb@me.its.ac.id and

⁴ pramono@me.its.ac.id

Abstract— This study is aimed to predict the minimum varying blank holder force (VBHF) during the punch stroke, in order to eliminate wrinkle on cup deep drawing product. The slab method was used to develop mathematical modeling of the minimum VBHF base on a gap limit and unbending energy. The mathematical modeling has been validated to FE simulations for the prevention of wrinkling in the same criterion. Steel sheet of SPCD grade with thickness of 0.2 mm is used to generate the cylindrical cup-shaped product with 40 mm diameter. Analytical Results of minimum VBHF have a similar trend result compared to FE simulation. However, the minimum VBHF can be quite effective for preventing the occurrence of excessive wrinkle.

Keyword— Modeling blank holder force, Deep drawing, Wrinkling, FE simulation.

I. INTRODUCTION

Wrinkling is one type of product defects that are often found in the deep drawing process. In order to avoid these defects, the process parameters, i.e. the blank holder force (BHF) must be determined in the proper value [1-20]. The constant blank holder force during the process, it's frequently not capable to prevent wrinkling, effectively. To achieve the proper process performance, the blank holder force should be set to make process deformation with the balance of material flow, tangential stress and radial stress [10-17]. The lowest of BHF magnitude could give consequences for increasing tangential stress, and gap [15-17]. If the gap between the blank holder and die more than 180% of material thickness, it will potentially occur the wrinkling products [10-14]. To prevent this problem, the BHF over the punch stroke should be set in proper value to anticipate the deformation condition dynamically.

R. Venkat Renddy et al. [1] conducted a study of the influence of process parameters, i.e. the constant BHF, punch-die radius and coefficient of friction against the onset of wrinkling in a deep drawing cylindrical cup. This study was also investigating the mechanism of wrinkling initiation and growth in cylindrical cup deep drawing process.

Anupam Agrawal et al. [2] developed the mathematical modeling of minimum constant BHF to avoid wrinkling of cylindrical cups, base on calculating of restraining energy and considering the aspect of thinning material. The constant BHF applied a spring type blank holder. The wrinkling would occur when the buckling strain as tangential strain is excessive.

Xi Wang et al. [3] and qin si-ji et al. [9] have developed the buckling analysis to predict the onset of wrinkling, and determined the BHF magnitude by using the theory of strain energy. This paper develops an analytical approach to calculate the critical wrinkling by using a constant blank holder force, base on the theory of restraining energy and buckling criterion.

M. Kadkhodaya et al. [4], E. Chu et al. [5] Joao Pedro et al. [6], and Mohammad Amin Shafaat et al. [7][8] have developed a model of wrinkle with the analysis of elastic-plastic by using the method of bifurcation function and Tresca criterion. The results of the analysis were predicting the minimum constant BHF without wrinkling, during the punch stroke.

M Gavass et al. [10] [11], Wang Wu-rong et al. [12], Lin Zhong-qin et al. [13] and T. Yagami et al. [14] have researched related to wrinkling prevention by using criteria limits of the maximum gap. The Application of gap criterion can effectively prevent the occurrence of excessive wrinkling, therefore the flow of material can still move into the die cavity completely. The normal gap, which still permitted between 110% to 180% of the initial thickness of the material. An analytical study, continued by S. Candra et al. [15] [16], which aims to control

tangential and radial stress base on limits the maximum gap and the fracture condition, to estimate the maximum varying blank holder force (VBHF).

The current study will develop a different mathematical models to obtain a minimum variable blank holder force each punch stroke, based on a gap limit and strain energy on Cylindrical Drawn Cup Product, and its also compared to simulation to predict the critical limit of wrinkling. By using the a gap limits and strain energy, can be expected simultaneously prevents wrinkling. The analytical calculation of the minimum VBHF, will be validated by the FE simulation of cup deep drawing process.

II. MATHEMATICAL MODELING OF CRITICAL BLANKHOLDER FORCE

In the cup deep drawing process, the sheet material will deform the flange to follow a rule of force and energy equilibrium. The force equilibrium diagrams in a small element and ignoring friction on flange, as shown in Fig. 1, the mathematical equation of formation of radial stress can be written as [16][17][21]

$$r d\sigma_r da s_0 + \sigma_r dr da s_0 + 2|\sigma_t| s_0 dr \sin\left(\frac{d\alpha}{2}\right) = 0 \quad (1)$$

Where σ_r is the radial stress, r is the inside radius at the moment, $d\alpha$ is a small segment angle of the flange, s_0 is the initial thickness of material, and σ_t is the tangential stress in the flange.

An angle of the segment $d\alpha/2$ is very small, then it can be considered to be $\sin(d\alpha/2) \approx d\alpha/2$, so the equation (1) becomes:

$$d\sigma_r = (\sigma_r - \sigma_t) \left(\frac{dr}{r}\right) \quad (2)$$

Where R_1 is the outer flange radius.

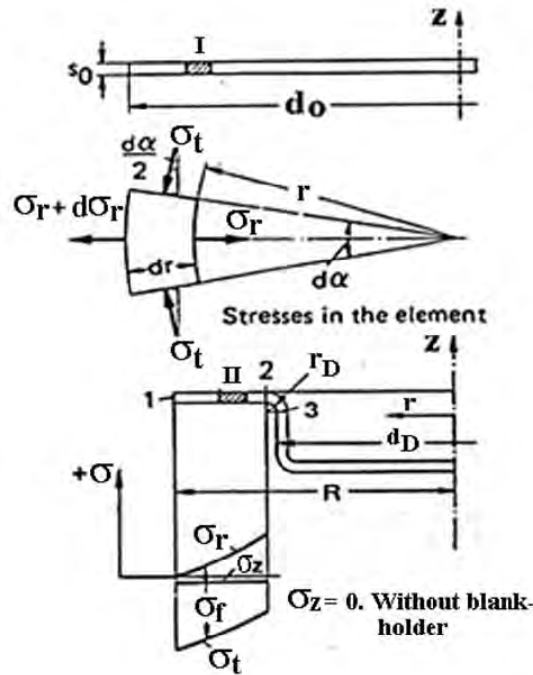


Fig. 1 The Force equilibrium diagrams in a small element on flange, [21]

By using the criteria Tresca and the equivalent stress [14], the relationship between radial and tangential stress under the condition of plain strains can be obtained.

$$(\sigma_r - \sigma_t) = \sqrt{\frac{2(\bar{R}_n + 1)}{1 + 2\bar{R}_n}} \sigma_f \quad (3)$$

Where σ_f is the flow stress on flange from the initial position until another position, and \bar{R}_n is the mean anisotropy coefficient of the material.

Substituting Eq. (3) into Eq. (2) and integrating with the boundary of $r = r_m$ ($d = d_m$) until $r = R_1$, or ($d = d_i$) the equation of ideal stress ($\sigma_{r,i}$) formation on the flange every punch position obtained as follows,

$$\sigma_{r,i} = \sqrt{\frac{2(\bar{R}_n + 1)}{1 + 2\bar{R}_n}} \sigma_{fml,i} \ln(R_{1,i}/R_m) \quad (4)$$

Where $\sigma_{fm,i}$ is the mean flow stress on flange from point 1-2 over punch stroke, $R_{1,i}$ is the outer local radius of flange - function of punch stroke (point 1), R_m is the average radius of cylindrical cup deep drawing ($R_m = R_D - s_0$) and R_D is the die radius.

In order to simplify the calculation of mean flow stress on flange, the equivalent strain will be divided into two sections, as at point 1 and point 2. The strain at point 1 ($\varepsilon_{1,i}$) and 2 ($\varepsilon_{2,i}$) can be calculated respectively by Eq. (5), [9]

$$\varepsilon_{1,i} = \sqrt{\frac{2(\bar{R}_n+1)}{1+2\bar{R}_n}} \ln\left(\frac{R_0}{R_{1,i}}\right) \quad (5)$$

And

$$\varepsilon_{2,i} = \sqrt{\frac{2(\bar{R}_n+1)}{1+2\bar{R}_n}} \ln\left(\frac{R_{int,i}}{R_D+r_d}\right) \quad (6)$$

Where R_0 is the blank size radius (initial blank sheet), r_d is the radius of die edge and $R_{int,i}$ is the unknown inside diameter (point 2), $R_{int,i} = \sqrt{R_0^2 + (R_D + r_d)^2 - R_{1,i}^2}$

The mean flow stress between point 1 and point 2 can be calculated by Eq. (7),

$$\sigma_{fm,p1-2,i} = \left(\frac{1}{2}\right) K(\varepsilon_{1,i}^n + \varepsilon_{2,i}^n) = \left(\frac{1}{2}\right) \left(\sqrt{\frac{2(\bar{R}_n+1)}{1+2\bar{R}_n}}\right)^n K \left[\left(\ln \frac{d_0}{d_{1,i}}\right)^n + \left(\ln \frac{d_{int,i}}{d_D+2r_d}\right)^n \right] \quad (7)$$

Substituting Eq. (7) into Eq. (4) and considering the friction on the flange surface, thus the equation of radial stress will be determined as follows,

$$\sigma_{r,i} = \left\{ \sqrt{\frac{2(\bar{R}_n+1)}{1+2\bar{R}_n}} (\sigma_{fm,i}) \left(\ln \frac{R_{1,i}}{R_m} \right) \right\} + \left\{ \frac{\mu F_{bh,i}}{\pi R_{1,i} s_0} \right\} \quad (8)$$

To determine radial strain and radial stress each step of punch stroke, the changing of diameter should be calculated under the condition a constant volume.

Wrinkling is often approached through buckling phenomena approach, which is caused by too excesses the magnitude of local tangential stress on the flange. Buckling prediction was still an ongoing, conducted by researchers with the wrinkles criteria, e.g. buckling studies based geometric model change [3] [9]. M Gavvas et al [10-11], Lin Zhong et al [13] have conducted research and experiments with the result, that limit gap (safe gap) is under $(180\% + 1) s_0$. The maximum gap limit is useful to set the minimum blank holder force for preventing wrinkling. Moreover, wave number and behavior of the buckling are strongly influenced by the material mechanical properties, thickness and the punch-die dimensions. To eliminate local buckling at each position of the punch stroke, VBHF is applied and determined by using a limit gap criterion and a theory of strain energy. And to predict the condition of the flange area, analysis and simulation study, this approach will use the assumption that follows the reference height buckling previous studies [3][4][9][10][11][13]. The schematic model of the ideal buckling and local stress that it will be used to predict the VBHF on this analysis defined as illustrated Fig. 2.




If the waveform is assumed sinusoidal buckling, and the height of the buckling wave angle ($\phi_0 = \phi$) is assumed constant from beginning until the end of the process (see Fig. 2), as well as the angle of wave height can be estimated:

$$\phi_0 = \phi \approx \arcsin\left(\frac{gap_1}{R_{1,i} - R_D - r_d}\right) \quad (9)$$

Where gap_1 is the gap at the beginning of the punch stroke, the $gap_i = gap_1$ on punch stroke (i) is assumed to arise early wrinkling occurs in early stroke punch that $i = 1$. And assuming a constant angle $\phi_0 = \phi$. Therefore, the gap height prediction punch stroke function approximated by the following equation.

$$gap_i \approx (R_{1,i} - R_D - r_d) \sin(\phi_0) \quad (10)$$

Where $R_{1,i}$ is the outer local flange radius under the function of the punch stroke (the height of cup or h), R_D is die radius and r_d is the edge die radius and ϕ_0 is the angle of wave height.

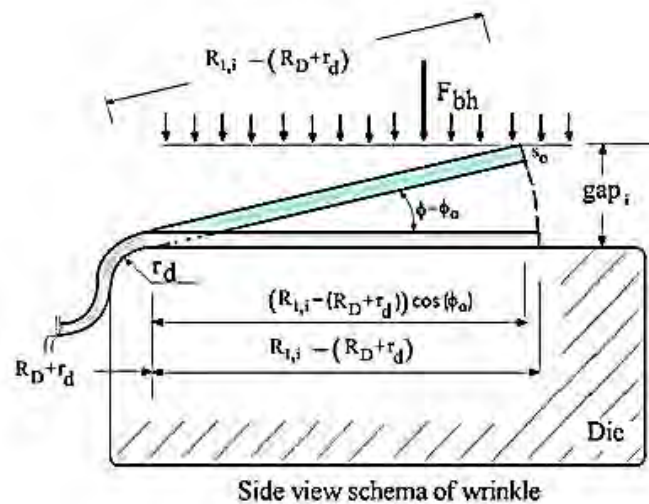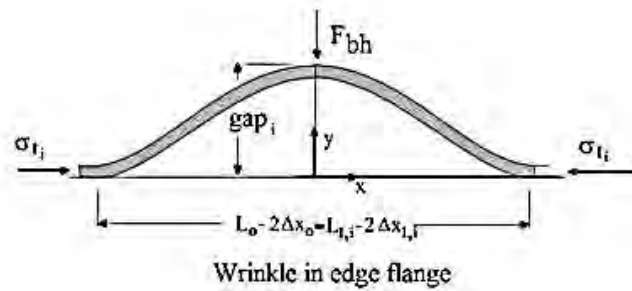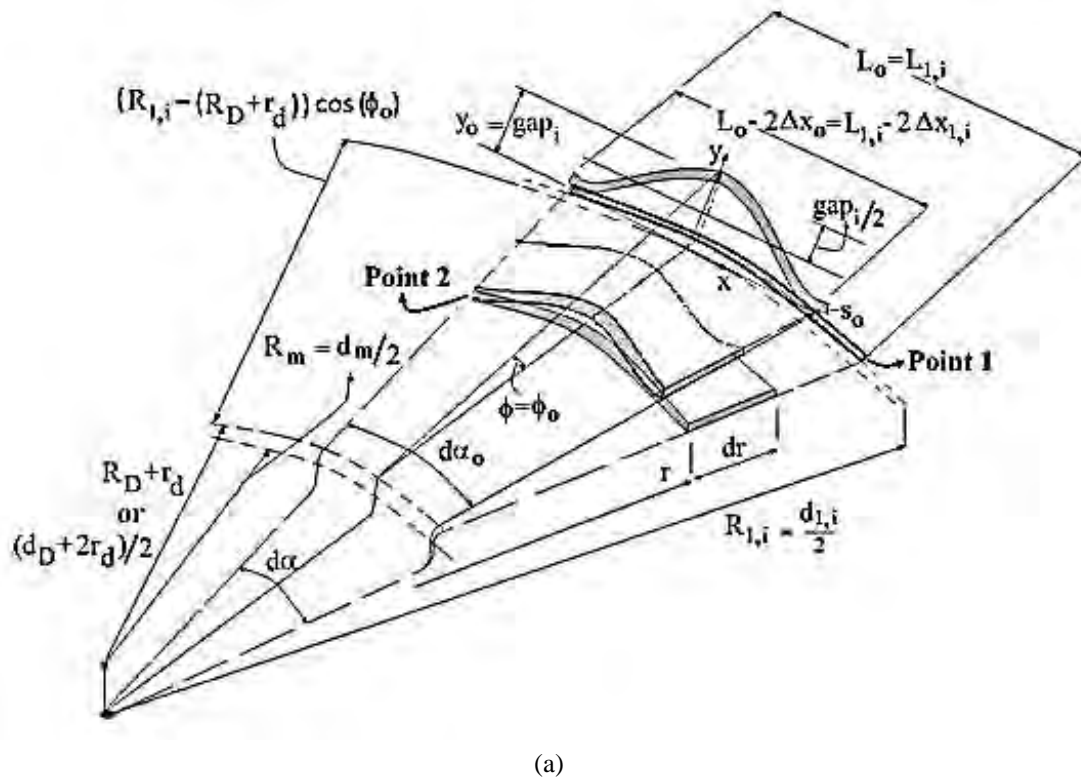

(b)

Fig. 2. a. Three dimension of the ideal buckling scheme of sheet material on flange, b. Front and side view of the ideal buckling scheme

The changing of flange dimension can be calculated from the material displacement of points 1 and 2 during the punch stroke gradually. Therefore, it can be described as follows.

Under the condition of the product without a wrinkle (see Fig. 2), the circumference of the outer flange and

dimension changing of flange (point 1 position) can be estimated as a function of radius and the wrinkling wave number over punch stroke (i) as the following equation:

$$L_{1,i} = (2\pi R_{1,i})/N_i \quad (11)$$

$$(L_{1,i} - 2\Delta x_{1,i}) = \left(2\pi \left((R_{1,i} - R_D - r_d) \cos(\phi_0) \right) + (R_D + r_d) \right) / N_i \quad (12)$$

$$2\Delta x_{1,i} = (L_{1,i}) - (L_{1,i} - 2\Delta x_{1,i}) \quad (13)$$

$$2\Delta x_{1,i} = (2\pi R_{1,i}) - \left(2\pi \left((R_{1,i} - R_D - r_d) \cos(\phi_0) \right) + (R_D + r_d) \right) \quad (14)$$

Where, $L_{1,i}$ is the circumference of the outer flange (position of point 1) for an insignificant wrinkling wave, $R_{1,i}$ is radius of an outer flange (position of point 1), $2\Delta x_{1,i}$ is reduction in the circumference of the outer ring flange for a wrinkle wave (position point 1), when appearing wrinkling, and N_i is the wave number of wrinkle each punch stroke.

Based on research conducted by M. Kadkhodayan et al. [4], the number of wrinkle wave can be estimated by using the equation (15).

$$N_i = 1,65 \frac{R_{\text{mean}}}{W} = 1,65 \left(\frac{(R_{1,i} + (R_D - r_d))/2}{(R_{1,i} - (R_D - r_d))} \right) \quad (15)$$

Where, R_{mean} is the mean radius of flange and W is the flange width.

In the same calculation as above, the length of the circumference and the dimensional change of flange at point 2 for an insignificant wrinkling wave (see Fig. 2) can use the equations as follows:

$$L_{2,i} = \left(2\pi \left((R_{\text{int},i} - R_D - r_d) \cos(\phi_0) \right) + (R_D + r_d) \right) / N_i \quad (16)$$

$$(L_{2,i} - 2\Delta x_{2,i}) = 2\pi(R_D - r_d)/N_i \quad (17)$$

$$2\Delta x_{2,i} = (L_{2,i}) - (L_{2,i} - \Delta x_{2,i}) \quad (18)$$

$$2\Delta x_{2,i} = \left(\left(2\pi \left((R_{\text{int},i} - R_D - r_d) \cos(\phi_0) \right) + (R_D + r_d) \right) - (2\pi(R_D - r_d)) \right) / N_i \quad (19)$$

Where, $L_{2,i}$ is the circumference on the position of point 2 for an insignificant wrinkling wave, $R_{\text{int},i}$ is unknown inside radius-function of the punch stroke (point 2), $2\Delta x_{2,i}$ is reduction in the circumference of the flange inside radius for a wrinkle wave (position point 2).

The average length of the circumference (\bar{L}_i) to the wave wrinkle and the average displacement direction of the x axis (length reduction circular flange) between point 1 and 2, for a wrinkle wave is:

$$\bar{L}_i = (L_{1,i} + L_{2,i})/2 \quad (20)$$

$$\bar{\Delta x}_i = (\Delta x_{1,i} + \Delta x_{2,i})/2 \quad (21)$$

In case of buckling or wrinkling due to tangential stress over punch stroke, furthermore the strain energy balance on the surface of the flange can follow the equation [3][9]:

$$E_{t,i} = E_{\text{bending(wrinkle)},i} + E_{\text{bh},i} \quad (22)$$

Where $E_{t,i}$ is the strain energy to straighten wrinkle wave, $E_{\text{bending(wrinkle)},i}$ is the bending energy of buckling due to tangential stress, $E_{\text{bh},i}$ is the strain energy due to the application of blank holder force or energy unbending, and which serves to maintain the tangential stress is not excessive, with reference to the allowable gap.

Strain energy can also be represented by a magnitude formation based on the value of the circumference reduction, which can be approximated as the following equation (23).

$$E_{t,i} = \int_{R_D+r_d}^{R_{1,i}} \sigma_{t,i} s_0 S' dR \quad (23)$$

Where S' is the additional length of the circumference (the incremental of circumferential length) when wrinkling occurs, i.e. $S' = \int_0^1 (1 + \bar{\Delta x}_i) dx - \int_0^1 dx$, and $S' = \int_0^1 \bar{\Delta x}_i dx$, R is the outer local radius of the flange, $\sigma_{t,i}$ is the tangential stress and s_0 is the initial thickness of material.

By knowing the magnitude of increase in length of the tour, furthermore the equation (23) would be

$$E_{t,i} = \int_{R_D+r_d}^{R_{1,i}} \int_0^1 (\bar{\Delta x}_i) \sigma_{t,i} s_0 dx dR \quad (24)$$

$$E_{t,i} = \int_{R_D+r_d}^{R_{1,i}} \sigma_{t,i} s_0 \bar{\Delta x}_i dR \quad (25)$$

$$E_{t,i} = \sigma_{t,i} s_0 \left(R_{1,i} - (R_D + r_d) \right) \bar{\Delta x}_i \quad (26)$$

Substituting equation (3) and (8) into the equation (26), thus the strain energy ($E_{t,i}$) for one of wrinkle wave would becomes,

$$E_{t,i} = \left(\sqrt{\frac{2(\bar{R}+1)}{1+2\bar{R}}} \sigma_{fml,i} \ln \left(\frac{R_{1,i}}{R_m} \right) + \left\{ \frac{\mu F_{bh}}{\pi R_{1,i} s_0 / N_i} \right\} - \sqrt{\frac{2(\bar{R}+1)}{1+2\bar{R}}} \sigma_{f,i} \right) s_0 (R_{1,i} - (R_D + r_d)) \bar{\Delta} X_i \quad (27)$$

$$E_{t,i} = \left(1,1 \sigma_{fml,i} \ln \left(\frac{R_{1,i}}{R_m} \right) + \left\{ \frac{\mu F_{bh}}{\pi R_{1,i} s_0 / N_i} \right\} - 1,1 \sigma_{f,i} \right) s_0 (R_{1,i} - (R_D + r_d)) \bar{\Delta} X_i \quad (28)$$

Where:

$$\bar{\Delta} X_i = f(R_{1,i} \phi_0)$$

$$\bar{\Delta} X_i = 2\pi \left((R_{1,i}) - \left(((R_{1,i} - R_D - r_d) \cos(\phi_0)) + (R_D + r_d) \right) + \left(((R_{int,i} - R_D - r_d) \cos(\phi_0)) + (R_D + r_d) \right) - ((R_D - r_d)) \right)$$

$$R_{1,i} = R_{1(i=h)} = f(h_i) = \sqrt{(R_0)^2 + 8R_D (h_i - (0,43r_p - 0,43r_d))}$$

$$R_{int,i} = f(R_{1,i}) = \sqrt{(R_0)^2 + (R_D + r_d)^2 - (R_{1,i})^2}$$

$$\phi_0 = f(N, gap_{0,1})$$

$\sigma_{fml,i}$ is the mean flow stress by considering the alignment wrinkle.

The mean flow stress between point 1 to point 2 ($\sigma_{fmp1-2,i}$ – function position of punch stroke) can be calculated by:

$$\sigma_{fml,i} = \left(\frac{1}{2} \right) K \left((\varepsilon_{t_{crt-point 1}})^n + (\varepsilon_{t_{crt-point 2}})^n \right) \quad (29)$$

Where K is the strength coefficient of material, n is the strain hardening exponential of material, $\varepsilon_{t_{crt-point 1}}$ is the critical tangential strain at point 1, and $\varepsilon_{t_{crt-point 2}}$ is the critical tangential strain at point 2.

To estimate the critical tangential strain can be used the follows equation, respectively [21]:

$$(\varepsilon_{t_{crt-point 1}}) = \sqrt{\frac{2(\bar{R}+1)}{1+2\bar{R}}} \left\{ \ln \left(\frac{L_{1,i} \text{ point 1}}{L_{1,i} \text{ point 1} - \Delta X_{1,i} \text{ point 1}} \right) + \ln \left(\frac{R_0}{R_{1,i}} \right) \right\} \quad (30)$$

$$(\varepsilon_{t_{crt-point 2}}) = \sqrt{\frac{2(\bar{R}+1)}{1+2\bar{R}}} \left\{ \ln \left(\frac{L_{2,i} \text{ point 2}}{L_{2,i} \text{ point 2} - \Delta X_{2,i} \text{ point 2}} \right) + \ln \left(\frac{R_{int,i}}{R_D + r_d} \right) \right\} \quad (31)$$

Substituting the equations (30) and (31) into the equation (29), therefore the equation of mean flow stress between point 1 to point 2 becomes,

$$\sigma_{fml,i} = \left(\frac{1}{2} \right) K \left[\left\{ \sqrt{\frac{2(\bar{R}+1)}{1+2\bar{R}}} \left\{ \ln \left(\frac{L_{1,i} \text{ point 1}}{L_{1,i} \text{ point 1} - \Delta X_{1,i} \text{ point 1}} \right) + \ln \left(\frac{R_0}{R_{1,i}} \right) \right\} \right\}^n - \left\{ \sqrt{\frac{2(\bar{R}+1)}{1+2\bar{R}}} \left\{ \ln \left(\frac{L_{1,i} \text{ point 1}}{L_{1,i} \text{ point 1} - \Delta X_{1,i} \text{ point 1}} \right) + \ln \left(\frac{R_0}{R_{1,i}} \right) \right\} \right\}^n \right] \quad (32)$$

By using the phenomena of bending moment, thus the bending energy magnitude ($E_{bending(wrinkle),i}$) can be approximated by the equation:

$$E_{bending(wrinkle),i} = \int_{R_D+r_d}^{R_{1,i}} \left(\frac{\bar{\sigma}_{bending,i} dR s_0 gap_i}{dI_i} \right) s_0 \bar{\Delta} X_i dR \quad (33)$$

Where $\bar{\sigma}_{bending,i}$ is the average bending stress between points 1 and 2, dI_i is the moment of inertia of the cross section area of the flange. If the radius of a moment in the flange segment is constant R and the thickness of the material that is s_0 , then change the moment of inertia in every place (dI_i) can be shown equation.

$$dI_i = \frac{dR}{12} (s_0)^3 / \left(\frac{s_0}{2} \right) \quad (34)$$

By integrating the equation (33), and combine it into the equation (34), furthermore the equation will be obtained:

$$E_{bending(wrinkle),i} = 6(\bar{\sigma}_{bending,i} gap_i) \bar{\Delta} X_i (R_{1,i} - (R_D + r_d)) \quad (35)$$

The average of bending stress is a function and a reduction of the circumference length average between points 1 and 2. If the value of $\varepsilon_{t_{crt-point 1}}$ and $\varepsilon_{t_{crt-point 2}}$ is obtained, the average of bending stress ($\bar{\sigma}_{bending,i}$) between points 1 and 2 can be approximated by the equation:

$$\bar{\sigma}_{bending,i} = K \left(\left(\sqrt{\frac{2(\bar{R}+1)}{1+2\bar{R}}} \left(\ln \left(\frac{\bar{L}_{i-0}}{\bar{L}_{i-0} - \bar{\Delta} X_{i-0}} \right) + \ln \left(\frac{\bar{L}_i}{\bar{L}_i - \bar{\Delta} X_i} \right) \right) \right)^n \right) \quad (36)$$

While the unbending energy is the energy required to align the sheet material that has been buckling. Unbending energy on flange surfaces approximated by the following equation.

$$E_{bh,i} = F_{bh} \text{ gap}_i \quad (37)$$

Where F_{bh} is blank holder force (BHF).

The physical meaning of this formula is the energy to straighten a wrinkle, where the magnitude is a multiplication between the blank holder force with a high amount of wrinkle (gap). Then, based on the principle of energy conversion which has considered the normal formation energy and energy buckling, the equation blank holder force to perform unbending one wrinkle wave can be determined as follows.

$$F_{bh} \text{ gap}_i = (E_{t,i} - E_{\text{bending(wrinkle),i}}) \quad ; \text{ for } N_i = 1 \quad (38)$$

Then the equations (28) and (37) respectively substituted into the equation (38), taking into account the friction factor, it will obtain the equation of blank holder force of each punch stroke ($F_{bh} \text{ gap}_i$) as follows:

$$F_{bh} \cdot \text{gap}_i = \left\{ \left(\sqrt{\frac{2(\bar{R}+1)}{1+2\bar{R}}} \sigma_{fm,i} \ln \left(\frac{R_{1,i}}{R_m} \right) + \left\{ \frac{\mu F_{bh}}{\pi R_{1,i} s_0 / N_i} \right\} - \sqrt{\frac{2(\bar{R}+1)}{1+2\bar{R}}} \sigma_{f,i} \right) s_0 (R_{1,i} - (R_D + r_d)) \bar{\Delta}x_i \right\} - \{6(\bar{\sigma}_{\text{bending,i}} \text{ gap}_i) \bar{\Delta}x_i [R_{1,i} - (R_D + r_d)]\} \quad (39)$$

And

$$F_{bh} \left(\text{gap}_i - \frac{\mu (R_{1,i} - (R_D + r_d)) \bar{\Delta}x_i}{\pi R_{1,i} s_0 / N_i} \right) = \left\{ \left[\left(\sqrt{\frac{2(\bar{R}+1)}{1+2\bar{R}}} \sigma_{fm,i} \ln \left(\frac{R_{1,i}}{R_m} \right) - \sqrt{\frac{2(\bar{R}+1)}{1+2\bar{R}}} \sigma_{f,i} \right) s_0 (R_{1,i} - (R_D + r_d)) \bar{\Delta}x_i \right] - [6(\bar{\sigma}_{\text{bending,i}} \text{ gap}_i) \bar{\Delta}x_i \{R_{1,i} - (R_D + r_d)\}] \right\} \quad (40)$$

Furthermore, the equation (40) can be transformed into the equation (41), which can be used to predict the magnitude of the minimum varying blank holder force (VBHF) without wrinkling during the punch stroke, as follows.

$$F_{bh,i \text{ min.}} = \left(\frac{\left\{ \left(\sqrt{\frac{2(\bar{R}+1)}{1+2\bar{R}}} \sigma_{fm,i} \ln \left(\frac{R_{1,i}}{R_m} \right) - \sqrt{\frac{2(\bar{R}+1)}{1+2\bar{R}}} \sigma_{f,i} \right) s_0 (R_{1,i} - (R_D + r_d)) \bar{\Delta}x_i \right\} - \{6(\bar{\sigma}_{\text{bending,i}} \text{ gap}_i) \bar{\Delta}x_i (R_{1,i} - (R_D + r_d))\}}{\left(\text{gap}_i - \frac{\mu (R_{1,i} - (R_D + r_d)) \bar{\Delta}x_i}{\pi R_{1,i} s_0 / N_i} \right)} \right) \quad (41)$$

The total of minimum VBHF without wrinkles on the entire surface of the flange, can determined by the following equation.

$$F_{bh,i \text{ min.TOTAL}} = \left(\frac{\left\{ \left(\sqrt{\frac{2(\bar{R}+1)}{1+2\bar{R}}} \sigma_{fm,i} \ln \left(\frac{R_{1,i}}{R_m} \right) - \sqrt{\frac{2(\bar{R}+1)}{1+2\bar{R}}} \sigma_{f,i} \right) s_0 (R_{1,i} - (R_D + r_d)) \bar{\Delta}x_i \right\} - \{6(\bar{\sigma}_{\text{bending,i}} \text{ gap}_i) \bar{\Delta}x_i (R_{1,i} - (R_D + r_d))\}}{\left(\text{gap}_i - \frac{\mu (R_{1,i} - (R_D + r_d)) \bar{\Delta}x_i}{\pi R_{1,i} s_0 / N_i} \right)} \right) N_i \quad (42)$$

Where : $\sigma_{fm,i}$ is the average flow stress in the flange function metrial punch stroke, and $\sigma_{f,i}$ is the bending stress at the die radius, $\bar{\sigma}_{\text{bending,i}}$ is the unbending stress of wrinkling.

The equation (42) is useful for predicting the minimum VBHF, which can be applied as the lower limit of the distribution profile of blank holder force based on the theory of buckling and unbending energy, where the product is not expected to experience wrinkling.

III.FE MODELING

In this study, FE modeling provided the essential data, that will be compared to analytical solution. Element formation is carried out using FE of elastic-plastic deformation and ignore the effects of spring back. The curve of flow stress is following the Swift formulation by considering the yield stress and plastic flow stress. Simulation of wrinkling, and tearing (cracking) was done using the implicit AUTOFORM ver3.1. FE simulations had been done for cylindrical cups deep drawing as shown in Fig. 3. Dimensions of product, tools and used mechanical properties can be shown in Table I and table II below.

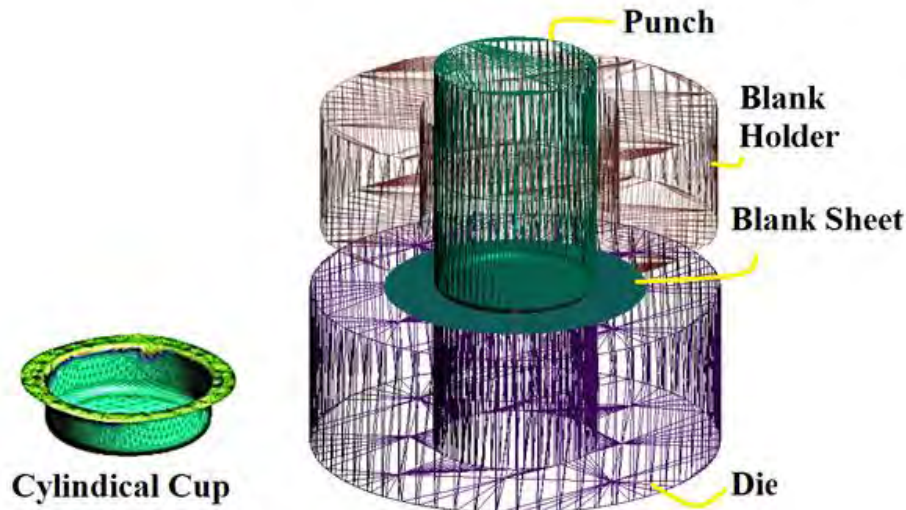


Fig. 3. Finite element model of cylindrical cup, by using AUTOFORM

TABLE I
Dimension of Tools

| Dimension of tools | Remarks |
|---|----------|
| d_0 (Blank sheets diameter) | 64 mm |
| d_D (Die diameter) | 40 mm |
| d_p (Punch diameter) | 39.58 mm |
| 2 x Clearance | 0.43 mm |
| s_0 (Initial thickness of sheet material) | 0.2 mm |
| r_d (Die edge radius) | 1 mm |
| r_p (Edge punch radius) | 2 mm |
| h (height of cylindrical cup) | 15-34 mm |

TABLE II
Mechanical Properties and Processes Variable

| Steel Sheet grade SPCD equivalent to DIN D03 | | Processes Variable | |
|--|--------------------------|----------------------------|--|
| K | 559 N/mm ² | Coefficient of friction | 0.4-0.45 (dry) 0.18-0.2 (Palm oil) |
| n | 0.176 | Punch velocity | 1 mm/Sec. |
| \bar{R}_n | 2 | BHF | Variable or Varying |
| UTS | 355 N/mm ² | | |
| Yield Stress | 232 N/mm ² | | |

The analysis result of the minimum VBHF is incorporated into the process generator functions of FE software for generating an animation and describing the quality of a cylindrical cup drawing during the forming process.

IV. RESULT AND DISCUSSION

Based on mathematical approaches and FE modeling, then it obtained the results as shown in Tables III and IV. The FE and analysis results are covering the calculation of the gap, the material displacement, strain energy and minimum VBHF. The magnitude of bending strain and wrinkle straightening energy increase drastically at the beginning of the punch stroke. This caused by the magnitude of tangential stress is very high. Furthermore, the strain energy magnitude will decrease at a middle - stroke, and increase at the end of the punch stroke. The application of minimum VBHF would be used to produce a product without wrinkling, where it was using the wrinkling gap limit around 180 % of the initial material thickness. The Height of gap is always changing in accordance with the strain energy conditions, and its identify the magnitude of tangential stress and wrinkling wave. To anticipate the occurrence of an excessive gap, BHF must be raised properly. The strain energy is highest at the beginning of the punch stroke, furthermore declined in the middle of the punch stroke, and finally increased at the end of the punch stroke, as shown in Table III.

The analytical approach has been validated and confirmed by the FE simulation. Table III has also shown the results of FE simulation related to the minimum VBHF. The FE simulation results of minimum VBHF are in the range of mathematical analysis results based on gap limits around 180% of the initial thickness material.

The minimum VBHF increases from the beginning until the end of the stroke punch. Overall, the minimum VBHF result of mathematical modeling has shown an average increasing value in similar percentage around of 9.3 % (from 360 N up to 890 N) compared to the FE simulation results (from 587 N up to 1432), as shown in table III.

TABLE III
Strain Energy and Minimum VBHF without Wrinkling – Analytical Result and FE Simulation with Gap 180% of the Initial Thickness


| i=h (mm) | Gap _i | θ (rad) | $\Delta\bar{X}$ Wrinkle At Point 1 | $\Delta\bar{X}$ Wrinkle At Point 2 | \bar{L}_i | N _i | E _i Bending | E _{bb,i} Unbending | F _{bb,i_Min} Analiti- cal (N) | F _{bb,i_Min} FE Simulation (N) |
|-------------|------------------|------------|--|--|-------------|----------------|---------------------------|--------------------------------|--|--|
| 1 | 0.34 | 0.0310 | 0.058796 | 0.208718 | 200.65 | 3.55 | 43.87 | 60.04 | 587 | 360 |
| 2 | 0.33 | 0.0310 | 0.058150 | 0.211790 | 198.17 | 3.64 | 40.49 | 63.68 | 677 | 252 |
| 3 | 0.31 | 0.0310 | 0.057084 | 0.217206 | 194.17 | 3.81 | 35.38 | 61.39 | 707 | 400 |
| 4 | 0.29 | 0.0310 | 0.055961 | 0.223396 | 190.08 | 3.99 | 30.55 | 57.51 | 740 | 580 |
| 5 | 0.27 | 0.0310 | 0.054770 | 0.230527 | 185.91 | 4.21 | 26.01 | 53.06 | 770 | 605 |
| 6 | 0.25 | 0.0310 | 0.053497 | 0.238814 | 181.64 | 4.46 | 21.77 | 48.35 | 802 | 602 |
| 7 | 0.22 | 0.0310 | 0.052122 | 0.248537 | 177.26 | 4.77 | 17.85 | 43.50 | 837 | 625 |
| 8 | 0.20 | 0.0310 | 0.050616 | 0.260076 | 172.78 | 5.14 | 14.25 | 38.59 | 877 | 646 |
| 9 | 0.18 | 0.0310 | 0.048936 | 0.273938 | 168.18 | 5.60 | 11.00 | 33.65 | 925 | 664 |
| 10 | 0.16 | 0.0310 | 0.047018 | 0.290815 | 163.44 | 6.19 | 8.12 | 2.72 | 983 | 703 |
| 11 | 0.13 | 0.0310 | 0.044756 | 0.311628 | 158.57 | 6.96 | 5.62 | 2.80 | 1055 | 702 |
| 12 | 0.11 | 0.0310 | 0.041959 | 0.337492 | 153.54 | 8.04 | 3.54 | 1.91 | 1146 | 730 |
| 13 | 0.08 | 0.0310 | 0.038253 | 0.369129 | 148.34 | 9.65 | 1.91 | 1.06 | 1260 | 787 |
| 14 | 0.05 | 0.0310 | 0.032781 | 0.403037 | 142.95 | 12.29 | 0.76 | 9.25 | 1392 | 876 |
| 15 | 0.03 | 0.0310 | 0.023035 | 0.402736 | 137.35 | 17.48 | 0.13 | 4.49 | 1432 | 890 |
| 16 | 0.03 | 0.0310 | 0.023035 | 0.402736 | 131.51 | 32.35 | 0.13 | 4.49 | 1432 | 683 |
| Etc. | | | | | | | | | | |

Table III shows the gap limits around 180% of initial thickness, is still permitted to use as a reference. This analytical approach could be validated and confirmed by the FE simulation. Therefore, the gap limits and unbending energy will be used to determine the minimum VBHF with no excessive wrinkle.


In addition, the application of minimum VBHF has maintained the maximum gap without excessive wrinkle product of 0.395 mm or in around 180% of the initial material thickness, as shown in Table IV and Fig. 4. The results of simulation agree with Gavas's [23] [24] and Lin's gap criteria [28], so their method can be considered feasible to prevent excessive wrinkling.

TABLE IV
Height of Wrinkle and Average Gap in The Several Cross Section Direction (90°, 45° and 0° Rolling Sheet Direction); FE Simulation Result.


| i=h Punch Stroke (mm) | Average Height of Wrinkle and Gap (mm) | | | | | | | | Maxi- mum Height of Wrinkle (mm) | Maxi- mum of Gap _i (mm) |
|--------------------------------|--|------------------|-------------------------|------------------|-------------------------|------------------|---|---|---|---|
| | Cross section Direction | | | | | | Total Average of Wrinkle Height | Total Average of Gap _i | | |
| | 45 ^o | | 0 ^o | | 90 ^o | | | | | |
| | Height of Wrinkle | Gap _i | Height of Wrinkle | Gap _i | Height of Wrinkle | Gap _i | | | | |
| 0 | 0 | 0 | 0 | 0 | 0 | 0 | 0.000 | 0.000 | 0.192 | 0.392 (around 180% of initial thick- ness) |
| 4 | 0.164 | 0.364 | 0.730 | 0.273 | 0.100 | 0.300 | 0.113 | 0.313 | | |
| 6 | 0.086 | 0.286 | 0.132 | 0.332 | 0.137 | 0.373 | 0.130 | 0.330 | | |
| 10 | 0.152 | 0.352 | 0.160 | 0.360 | 0.266 | 0.466 | 0.192 | 0.392 | | |
| 14 | 0.192 | 0.392 | 0.037 | 0.237 | 0.122 | 0.322 | 0.117 | 0.317 | | |
| Etc. | | | | | | | | | | |

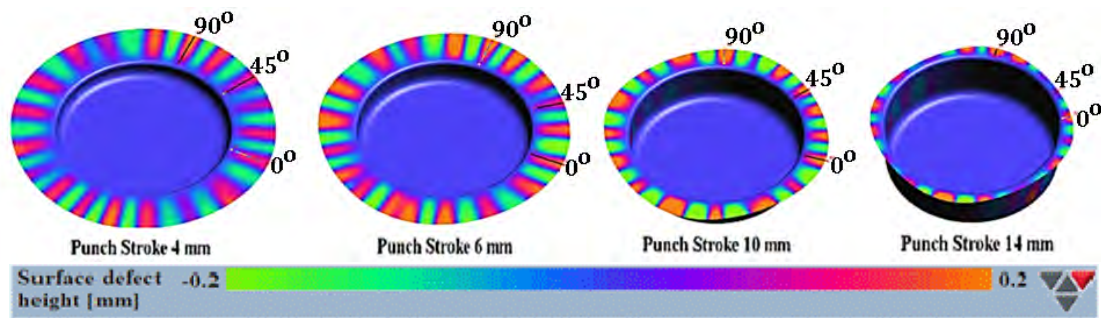

(a)

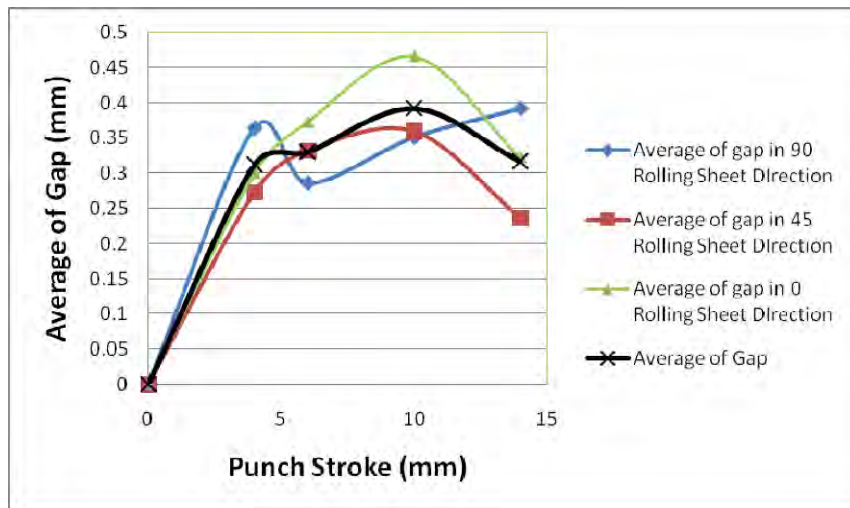

(b)

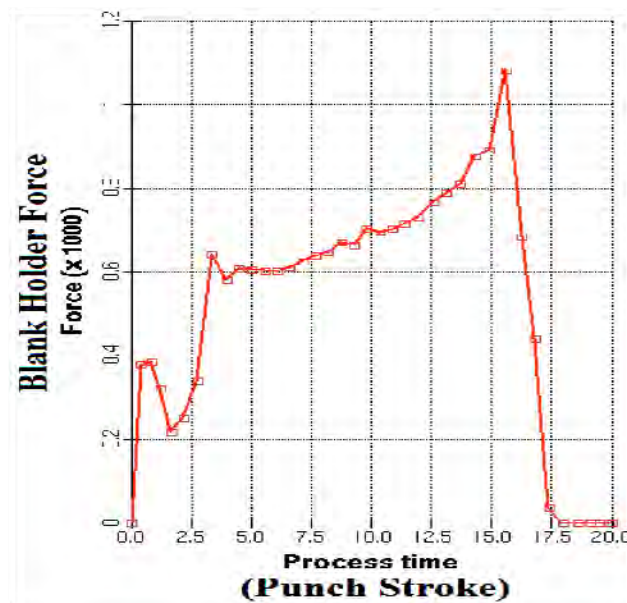

(c)

Fig. 4. FE Simulation results of cylindrical cup product with gap around 180 % of s_0 ; a. Virtual image of height wrinkle wave every punch stroke in cross section direction of 90°, 45° and 0°, b. Average of Gap during punch stroke, c. The minimum VBHF during punch stroke.

The wrinkle wave height image in the other cross section is shown in Fig 5 and 6. Those figures provide the information, which the application of mathematical modeling of minimum VBHF into AUTOFORM software would maintain the height of gap not more than 0.392 mm. Where, the maximum height of the gap is obtained by summing of the maximum wave height of 0.192 mm with the material initial thickness of 0.2 mm. Those figures also show, that the highest wave height wrinkles are on the outer flange diameter (“a” and “c” position in graphic). Furthermore, the sheet material closer to the die radius (“b” position), wave height of wrinkles

decreased. These results while ensuring mathematical modeling results shown in table III, have a relatively similar trend results.

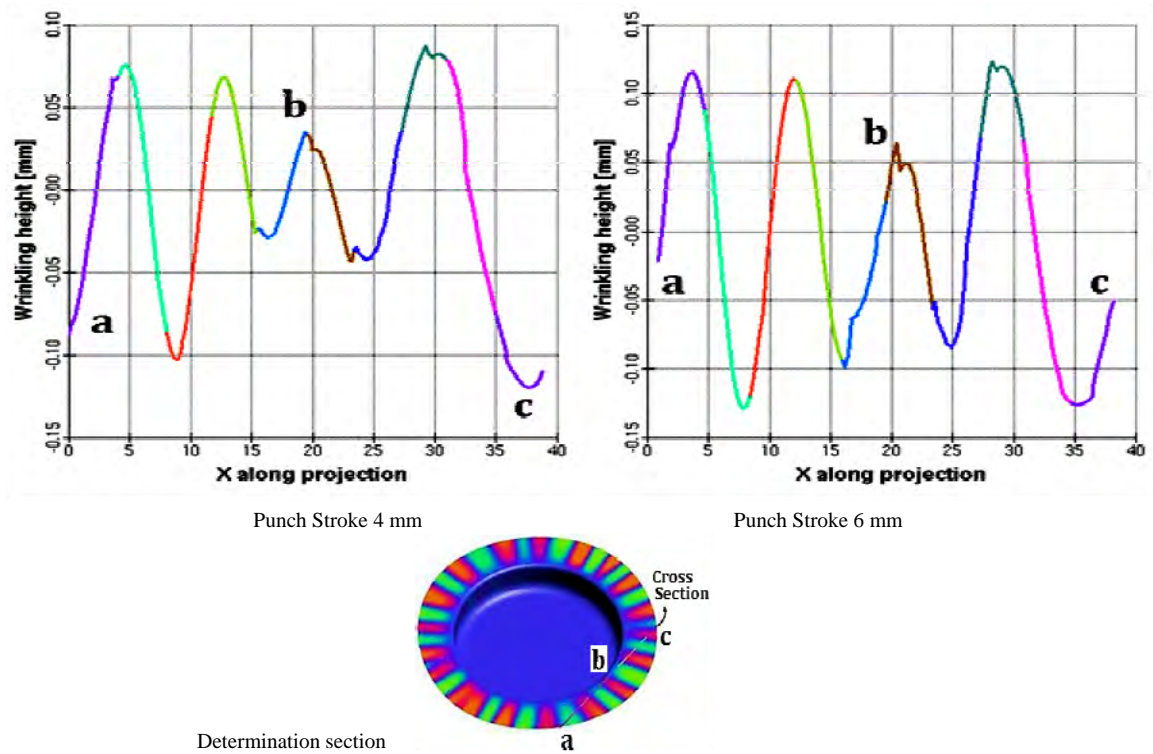


Fig. 5. FE simulation; Wrinkling wave height of cross section of flange at punch stroke of 4 mm and 6 mm.

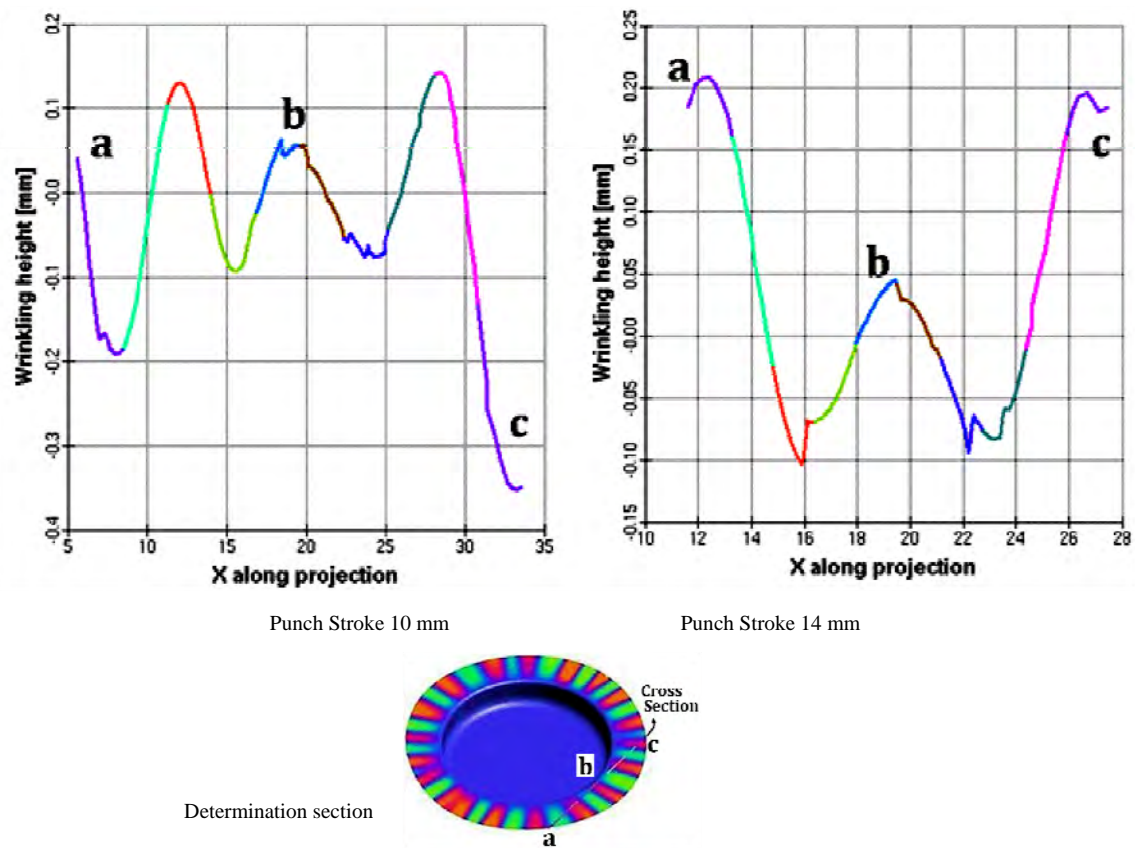


Fig. 6. FE simulation results; Wrinkling wave height of cross section of flange at punch stroke of 10 mm and 14 mm

The minimum VBHF, as a condition of safe limit in order to produce a product without cracking and wrinkling, can be shown in Fig. 7. This figure also shows the similarity value between the results of analytical calculations compared to the FE simulation results, related to the distribution of the minimum VBHF. In practice, the magnitude of VBHF minimum was recommended slightly above that value. With this minimum VBHF will maintain a safe area of the gap and the tangential stress on flange surface.

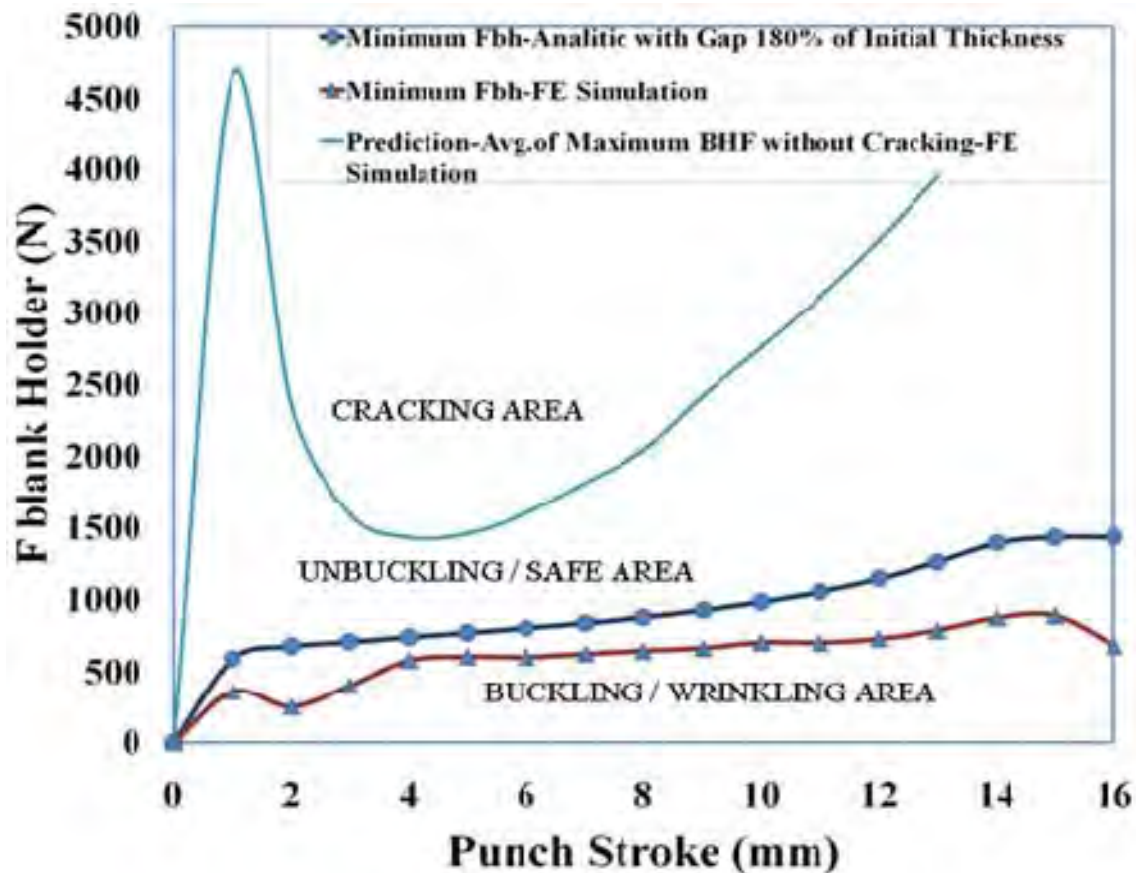


Fig. 7. The minimum VBHF to avoid wrinkling, by using the slab method (analytic calculation) and FE method; $d_0=64$ mm; $\mu=0.45$

V. CONCLUSION

Base on the gap limit and strain energy, the mathematical model of minimum VBHF has been described. It could be used as reference in deep drawing process, to prevent wrinkling. A good correlation between the analytical predicted results and FE simulation in order to determine the magnitude of minimum VBHF without excessive wrinkling was obtained. The application results of the minimum VBHF models have shown similar trends compared to the FE simulation results. The gap around 180% of the initial thickness is still permitted to use as a gap limit with realistic strain energy (not too high). The maximum gap without excessive wrinkle product is 0.395 mm of initial material thickness or around 180% of the thickness. Therefore, this gap limit can be used as a basic criteria to determine minimum VBHF to prevent excessive wrinkling with maintaining the maximum gap around that range. The critical VBHF is recommended slightly higher than the results of this study.

ACKNOWLEDGMENT

The authors would like to acknowledge to department of mechanical engineering, University of Indonesia, for allowing to use FE simulations of AUTOFORM V3.1. Also, we gratefully acknowledge helpful discussion and consultation with Prof. Dr. Dedi Priadi.

REFERENCES

- [1] Reddy, R.V., Reddy, T.A.J, Reddy, G.C.M., "Effect of various parameters on the wrinkling deep drawing cylindrical cups", International Journal of Engineering Trends and Technology, (2) 910 (2012) 53-58.
- [2] Agrawal, A., Reddy, N.V., Dixit, P.M., "Determination of optimum process parameters for wrinkle free products in deep drawing process", Journal of Materials Processing Technology 191 (2007) 51-54.
- [3] Wang, X., Cao, J., "An Analytical prediction of flange wrinkling in sheet metal forming", Journal of Manufacturing Process 2 (2000) 100-106.

- [4] Kadkhodaya, M., Moayyedean, F., "Analytical elastic-plastic study on flange wrinkling in deep drawing process", Journal of Scientia Iranica Transaction B: Mechanical Engineering 18 (2) (2011) 250-260.
- [5] E. Chu, Yu Xu, "An elastoplastic analysis of flange wrinkling in deep drawing process", Int. Journal of Mechanical Science, 43 (2001) 1421-1440.
- [6] Pedro, J.et. al., "Wrinkling prediction in the deep-drawing process of anisotropic metal sheets", Journal of Materials Proc.Tech., 128 (2002) 178-190.
- [7] Shafaat, M.A., Abbasi, M., Ketabchi, M., "Investigation into wall wrinkling in deep drawing process of conical cups", Journal of Materials Processing Technology, 211 (2011) 1783-1795.
- [8] Shafaat M. A., Abbasi, M., Ketabchi, M., "Effect of different yield criteria on prediction of wrinkling initiation of interstitial-free galvanized steel sheet", Material and Design, 32 (2011) 3370-3376.
- [9] Si-ji, Q., Bai-qing, X, Hong, L., Ting-ting, Z., "Critical blank-holder force in axisymmetric deep drawing", Transaction of nonferrous metals society of china, 22 (2012) s239-s246.
- [10] Gavas, M., "Increasing height of conical square cups using anti-lock braking system (ABS)". Journal of Mech. Science and Tech., 23 (2009) 3079-3087.
- [11] Gavas, M. and Izciler, M., "Effect of blank holder gap on deep drawing of square cups". Journal of Materials and Design, 28 (2007) 1641-1646.
- [12] Wu-rong, W., Guan-long, S., Zhong-qin, "Application of new VBHF optimization strategy to improve formability of automobile panels with Al alloy sheet", Transac. of nonferrous metals society of china, 20 (2010) 471-477.
- [13] Zhong-qin, L., Wu-rong, W., Guan-long, C., "A new strategy to optimized variable blank holder force towards improving the forming limits of Al sheet metal forming", Journal of Materials Proc.Tech., 183 (2007) 339-346.
- [14] Yagami, T., Manabe, K., and Yamauchi, Y., "Effect of alternating blank holder motion of drawing and wrinkle elimination on deep-drawability", Journal of Materials Processing Technology, 187-188 (2007) 187-191.
- [15] Candra, S., Batan, I M.L., "Experimental Study and Analysis of the Influence of Drawbead against Restriction and Deep Drawing Force of Rectangular Cup-Cans with Tin Plate Material", Journal of Applied Mechanic and Material (Trans. Tech Publications LTD), doi:10.4028, 315 (2013) 246-251.
- [16] Candra, S., Batan, I M.L., Pramono, A.S., Pramujati, B., "Simulation of The Metal Flow in Deep Drawing Process of Cup By Using Antilock Brake Mechanic System", Advance Materials Research, 789 (2013) 367-372.
- [17] Candra, S., Batan, I M.L., Berata, W., Pramono, A.S., "Simulation of Semi-Active the Blank Holder Force Control to Prevent Wrinkling and Cracking in Deep Drawing Process", Applied Mechanic and Material (Trans. Tech Publications LTD), 493 (2014) 473-479.
- [18] Sheng, Z.Q., Jirathearnat, S., Altan, T., "Adaptive FEM simulation for prediction of variable blank holder force in conical cup drawing", International Journal of Machine Tools and Manufacturing, Elsevier Ltd., 44 (2004) 487-494.
- [19] Yoshihara, S., Ken-ichi Manabe, Nishimura, H., "Effect of blank holder force control of magnesium alloy sheet", Journal of Materials Technology Elsevier Ltd, 170 (2005) 579-585.
- [20] Candra, S., Batan, I M.L., Berata, W., Pramono, A.S., "Analytical study and FEM simulation of the maximum VBHF to prevent cracking on cylindrical cup deep drawing", 12th Global Conf. on Sustainable Manufacturing 2014. TU-Berlin and UTM Malaysia, The Paper has been accepted for publication in Procedia CIRP by Elsevier B.V., (2014).
- [21] Lange, K., "Hand book of metal forming", Mc Graw Hill Co., Chapter 20 (1985) 20.1-20.65

AUTHOR PROFILE



Ir. Susila Candra, M.Tech was born in Surabaya, East Java, Indonesia. He received the Insinyur degree in mechanical engineering from Institute of Technology Sepuluh Nopember (ITS) Surabaya Indonesia in 1992, and M.Tech in manufacturing engineering from University of Indonesia in 2000. Now he is as Dr (candidate) in mechanical engineering, Institute of Technology Sepuluh Nopember (ITS) Surabaya. More than 5 years, he had experience to solve a lot of problems in the manufacture industries as employee. Since 1997, he has been become a lecturer and researcher in University of Surabaya with major of manufacturing engineering. His research interests include metal forming, tools design, metal cutting and CNC/CAM/CAE.



Prof. Dr. Ir. Made Londen Batan, M.Eng. received an engineering degree (Insinyur) in mechanical engineering from Institute of Technology Sepuluh Nopember (ITS) Surabaya, Indonesia, a graduate degree Sophia University, Tokyo, Japan and a Doctorate from Univ. of Paderborn, Germany. More than 27 years, He was as a senior lecturer, and since 2008 he was as Profesor in mechanical engineering, Institute of Technology Sepuluh Nopember (ITS) Surabaya. His research interests include engineering design of medical product, tools design, mould design and CAE for several engineering application. He has conducted a lot of research in the field of engineering design and manufacturing. He has received Five PATENTS related to the field.




Prof. Dr. Ir Wajan Berata, DEA received an Insinyur degree (B.E. degree) in mechanical engineering from Institute of Technology Sepuluh Nopember (ITS) Surabaya, Indonesia, in 1984. He received DEA and Dr in mechanical engineering from ENSMA-Poitiers, France. More than 29 years, He was as a senior lecturer, and since 2007 he was as Profesor in mechanical engineering, Institute of Technology Sepuluh Nopember (ITS) Surabaya. His focus research interests include stress analysis, strength of material, fracture mechanic and metal forming. He has many award for his dedication during a lecturer i.e Satyalancana Dwidya Sistha of Indonesian president, Exemplary Lecturer of ITS rector etc.



Dr. Ir Agus Sigit Pramono, DEA received an Insinyur degree (B.E. degree) in mechanical engineering from Institute of Technology Sepuluh Nopember (ITS) Surabaya, Indonesia, in 1989. He received DEA and Dr in mechanical engineering from Ecole Nationale Supérieure Des Mécanique, France. More than 20 years, He has been became as senior lecturer in ITS Surabaya His research interests include stress analysis, modeling system dynamic and FEM/CAE for several engineering application ie. manufacturing sector, automotive and transportation sector. He has a lot of getting grants from several research institutions and organizations, i.e IMHERE project, Research and Tech. Ministry of Indonesia, graduate grants from ITS, and research institutes and technology directorate of Indonesia. He has received a PATENTS related to the field.

International Journal of Engineering & Technology

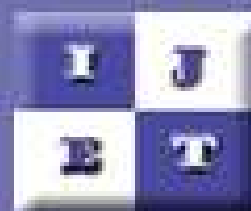

ISSN: 0975-4024

www.enggjournals.com/ijet



[Home](#)

[IJET Topics](#)

[Call for Papers 2021](#)

[Author Guidelines](#)

[Special Issue](#)

[Current Issue](#)

[Articles in Press](#)

[Archives](#)

[Editorial Board](#)

[Reviewer List](#)

[Publication Ethics and
Malpractice statement](#)

[Authors Publication Ethics](#)

[Policy of screening for
plagiarism](#)

[Open Access Statement](#)

[Terms and Conditions](#)

[Contact Us](#)

IJET Editorial Board

EDITOR IN CHIEF

K.SivaKumar,
KEJA Technologies,
Singapore

Dr. S.S.RIAZ AHAMED AMIE.,MCA.,M.Phil.,M.Tech.,MIEEE.,MACM.,Ph.D.,FIETE.,C.Engg.
Principal, Sathak Institute Of Information Technology, Ramanathapuram, Tamilnadu, INDIA

ASSOCIATE EDITOR

A.Selvi,
SIPS Technologies,
India

Dr. Shuming Chen Ph.D.

Associate Professor of Vehicle Engineering
College of Automotive Engineering
Jilin University
No. 5988 Renmin Street, Changchun, Jilin, 130022, China

EDITORIAL OFFICE

M.Azath
Calicut university/Mets School of Engineering, Kerala, India.

Bilal Bahaa Zaidan

Al- Nahrain University, Baghdad, Iraq

Dr. S. Abdul Khader Jilani

College of Computers & Information Technology, University of Tabuk, Tabuk,
Ministry of Higher Education, The Kingdom of Saudi Arabia.

Dr. Vipin Kakkar

Associate Professor, Q. No. 6, Chanakya Marg, Shri Mata Vaishno Devi Unvers Katra. J&K. 182 320. India.

Dr. DEBOJYOTI MITRA

Associate Professor & Head, Mechanical Engineering Department, Sir Padampat Singhania University,
Hill Villa Annexe, Opp. Hotel Hilltop Palace, Ambavgarh, Udaipur 313001, Rajasthan, India.

Dr.S.Sasikumar

Professor and head, Department of ECE.,Hindustan college of Engg. and Tech.,Coimbatore.

Dr. GOVINDARAJ THANGAVEL

Professor, Muthayammal Engineering College , Rasipuram, India

Dr. Vijay Srivatsan

Digital Technology Lab. Corp. (Subsidiary of Mori Seiki), Davis, CA

Dr. Wang Yong-gang

School of Highway Chang'an University 901 Transportation Sci. & Tech. Building, Middle Section of Nanerhuan, Xi'an 710064, P. R. China

Dr. NAOUFAL RAISSOUNI

Professor of Remote Sensing and Physics at the National Engineering School for Applied Sciences,
Abdelmalek Essaadi University, Tangier-Tetouan-Morocco

Dr. G. V. NAGESH KUMAR

Department of EEE Vignan's Institute of Information Technology Duvvada, Visakhapatnam, India

Dr. VELAYUTHAM .P

Adhiparasakthi Engineering College, Melmaruvathur, India

Dr DANWE RAIDANDI

Head of Mechanical Department, The College of Technology, University of DOUALA, Cameroon.

Dr. Bharat Raj Singh

Professor and Associate Director, School of Management Sciences, Technical Campus, India.

DR. SIVARAO SUBRAMONIAN

ASSOC. PROFESSOR, UNIVERSITI TEKNIKAL MALAYSIA MELAKA(UTeM), MELAKA, MALAYSIA.

Vijendra Singh

Assistant Professor, MITS, Lakshmangarh(sikar),Rajasthan-332311

Dr B.RUSHI KUMAR

Assistant Professor, VIT University, Vellore-632014, INDIA

Dr. Mueen Uddin

Senior Lecturer, Asia Pacific University of Technology and Innovation Kuala Lumpur Malaysia

Jian ian Liu

R&D Engineer in Alcon Laboratories

R.NAVANEETHAKRISHNAN

"Associate Professor, Bharathiyar College of Engineering & Technology, Karaikal"

Varun.G.Menon

Assistant Professor, SCMS School of Engineering and Technology, Karukutty, Kerala

T.R. Neelakantan

Associate Dean (Research), SASTRA Deemed University, Thanjavur, TN, India

Mr.Harikishore

Assistant Professor, KL University, Vijayawada, Andhra Pradesh, India.

Dr. Mohammad Israr

Principal, Balaji Engineering College, Junagadh [Gujrat]

B.T.P.MADHAV

Associate Professor, KLU

Bensafi Abd-El-Hamid

Associate Professor, Abou Bekr Belkaid University of Tlemcen

Dr. M.Chithirai Pon Selvan

Associate Professor,
Amity University, Dubai.

Dr. SREENIVASA RAO BASAVALA

Sr. Application Security Specialist, Yodlee InfoTech Pvt. Ltd, Bangalore.

DR. BRIJENDER KAHANWAL

Associate Professor, Galaxy Global Imperial Technical Campus, Dinarpur, Ambala

D . Asir Antony Gnana Singh

Assistant Professor, M.I.E.T Engineering College, Trichy-7, India.

Ahmed Nabih Zaki Rashed

lecturer in Menoufia University

SEYEZHAI RAMALINGAM

Associate Professor, SSN College of Engineering, Kalavakkam, Tamilnadu.

Shahryar Sorooshian

Senior lecturer, University Malaysia Pahang (UMP), Malaysia

GOVINDARAJ THANGAVEL

Professor, Muthayammal Engineering College , Rasipuram

Wang Yong-gang

Chang'an University, Transportation Sci. & Tech. Building, Middle Section of Nanerhuan, Xi'an 710064, P. R. China

Dr. S. Abdul Khader Jilani

Lecturer in College of Computers and Information Technology, University of Tabuk, Tabuk, The Kingdom of Saudi Arabia.

Lai Khin Wee

Research Officer, Universiti Teknologi Malaysia

Vijay Srivatsan

Vision Team Leader, Digital Technology Lab. Corp., Davis, CA

Mr. Kodge Bheemashankar G.

lecturer/Head, Swami Vivekanand College, Udgir Dist. Latur (MH) INDIA.

Dr.S.Sasikumar

Professor and Head, Hindustan College of Engineering and Technology, Coimbatore

Dr. DEBOJYOTI MITRA

Associate Professor & Head, Sir Padampat Singhania University, Hill Villa Annexe, Opp. Hotel Hilltop Palace, Ambavgarh, Udaipur 313001, Rajasthan, India.

Prof. T.Venkat Narayana Rao

Professor and Head, Hyderabad Institute of Technology and Management , Kompally, R.R Dist.

Dr. NAOUFAL RAISSOUNI

Professor, Abdelmalek Essaadi University, Tangier-Tetouan-Morocco

Rajesh Kumar Vishwakarma

Senior Lecturer, Jaypee University of Engineering & Technology A. B. Road Raghogarh, Dist.Guna 473226 (M.P) INDIA

Dr. G. V. NAGESH KUMAR

Associate Professor, Vignan's Institute of Information Technology, Duvvada, Visakhapatnam - 530046

Adis Medić

System and Network Engineer, Infosys Ltd-Bosanska Krupa, Una-Sana Canton, Bosnia and Herzegovina

Raj Gaurang Tiwari

Assistant Professor, Azad Institute of Engineering and Technology, Lucknow-226002, UP INDIA

VELAYUTHAM .P

Associate Professor, Adhiparasakthi Engineering College, Melmaruvathur

M. DANWE Raïdandi

Head, The College of Technology, University of DOUALA, Cameroon.

VIVEK S. DESHPANDE

Assistant Professor, MIT College of Engineering, Pune, India

Umbarkar Anantkumar Janardan

Assistant Professor, Walchand College of Engineering, SANGLI.

Jifeng Wang

University of Illinois at Urbana-Champaign

ANUJ K. GUPTA

Associate Prof., RIMT - Institute of Engineering & Technology, Mandi Gobindgarh

SUKUMAR SENTHILKUMAR

Post Doctoral Fellow, Universiti Sains Malaysia, Pulau Pinang-11800 [Penang], Malaysia.

Maniya Kalpesh Dudabhai

Lecturer/ Asst. Professor, C.K.Pithawalla college of Engg.& Tech.,Surat

Harish Kumar

Scientist in Force & Hardness Standard Group of National Physical Laboratory, New Delhi

P.VELAYUTHAM

Assistant Professor, Adhiparasakthi Engineering College, Melmaruvathur

Mariya Petrova Aleksandrova

Assistant Professor and Department Researcher, Technical University of Sofia, Faculty of Electronic Engineering and Technologies, Sofia, Kliment Ohridski blv.

Süleyman KORKUT

Associate Professor, Duzce University, Duzce-Turkey.

Sina Kazemian

Senior Geotechnical Engineer, SCG Consultant Company, Selangor, Malaysia

U C srivastava

Asst.Professor, Amity University, Noida, U.P-201301-India

Ch.V.Subbarao

Assistant Professor, University of Petroleum and Energy studies-Rajahmundry.

Antonella Petrillo

Contract Researcher in Industrial Plant with specific skills in Multicriteria Decision Analysis and Decision Support System, University of Cassino

Dr. Debasish Basak

Senior Principal Scientist, Central Institute of Mining and Fuel Research, Barwa Road, Dhanbad – 826015.

FAHIMUDDIN.SHAIK

Assistant Professor, Annamacharya Institute of Technology & Sciences, Rajampet, A.P.

DR. DEWAN MUHAMMAD NURUZZAMAN

Professor, Dhaka University of Engineering and Technology (DUET), Gazipur, Gazipur-1700, Bangladesh.

Dr V S GIRIDHAR AKULA

Professor and Principal At Vemu Inst of Tech, P Kotha Kota Chittoor dist

Prasenjit Chatterjee

Assistant Professor, MCKV Institute of Engineering, a Co-ed P.G. Degree Engineering College, Liluah, Howrah, West Bengal

Amin Paykani

Lecturer in Goldis English Institute, Tabriz.

Dr. Sameer Mahadeorao Wagh

Assistant Professor, Laxminarayan Institute of Technology, Rashtrasant Tukadoji Maharaj Nagpur University, Nagpur

Dhahri Amel

Research professor, Gafsa University-Faculty of Sciences

Dr.Waleed Khalil Ahmed

Instructor, United Arab Emirates University

DR. RAJNEESH KUMAR GUJRAL

Assoc. Professor, M.M. Engineering College, M.M university Mullana, Ambala-133 203, Haryana, India"

Ing. Norbert Herencsar

Contact person of the LLP Erasmus Bilateral Agreement, Czech Republic and Karadeniz Technical University, Trabzon, Turkey.

Dr.R.SATHISHKUMAR

Professor and Head, , Kodaikanal Institute of Technology, Dindigul Dist, India

Dr.V.Vaithiyathan

Associate Dean – Research, School of Computing, SASTRA University, Thanjavur 613 401

SEDDIK BRI

Professor – Researcher, Materials and Instrumentations (MIN), Electrical Engineering Department, High School of Technology, Meknes - Morocco

Dr. Saurabh Pal

Sr. Lecturer, VBS Purvanchal Univ. Jaunpur

R.MANIKANDAN

Senior Assistant Professor, SASTRA University, Thanjavur, India

Professor.K.S.Zakiuddin

Dean Academics (PG), Professor & Head, Dept of Mech Engg,Nagpur.

K.V.L.N.ACHARYULU

Associate Professor, Bapatla Engineering College,Bapatla.

Dr. R. S. SHAJI

Professor at Noorul Islam University, Kumaracoil.

Dr. Roli Pradhan

Assistant Professor, Maulana Azad National Institute of Technology

Sunny Narayan

Assistant professor & Departmental coordinator, Indus University, India.

Dr. A. SENTHIL KUMAR

Professor, Velammal Engineering College, Chennai

Dr. C. LAKSHMI DEVASENA

Assistant Professor, IBS, Hyderabad

All Rights Reserved © 2009 - 2024 Engg Journals Publications



This work is licensed under a [Creative Commons Attribution 2.5 India License](https://creativecommons.org/licenses/by/2.5/in/).

[Home](#)
[IJET Topics](#)
[Call for Papers 2021](#)
[Author Guidelines](#)
[Special Issue](#)
[Current Issue](#)
[Articles in Press](#)
[Archives](#)
[Editorial Board](#)
[Reviewer List](#)
[Publication Ethics and
Malpractice statement](#)
[Authors Publication
Ethics](#)
[Policy of screening for
plagiarism](#)
[Open Access Statement](#)
[Terms and Conditions](#)
[Contact Us](#)

VOLUME 7 Issue 2

ISSN: 0975-4024

Vol. 7, No.2

Search the Article

 ENHANCED BY 

| Article # | Article Title & Authors (Volume 7 Issue 2 Apr-May 2015) | Page |
|-----------|--|---------|
| 1. | Assessment of Homogenization Degree of Powder Mixing in a Cylinder Rotating Under Cascading Regime Alvaro Realpe, Karen Barrios, Martha Roza Abstract PDF | 394-404 |
| 2. | Developing Decision on Suitable Wastewater Treatment Technology Using Fuzzy Simple Additive Weighting Lazim Abdullah Abstract PDF | 405-413 |
| 3. | Improving Discretization by Post- Processing Procedure Taijun Han, Sangbum Lee, Sejong Oh Abstract PDF | 414-421 |
| 4. | Design and simulation of flow through subsonic axial compressor Mutahir Ahmed, Saeed Badshah, Rafi Ullah Khan, Muhammad sajjad, Sakhi Jan Abstract PDF | 422-435 |
| 5. | A 4 × 4 Butler Matrix for 28 GHz Switched Multi-Beam Antenna Stella Ifeoma Orakwue, Razali Ngah, T. A. Rahman, Hamza M. R. Al-Khafaji Abstract PDF | 436-442 |
| 6. | Genetic Algorithm Optimization and Performance Comparative Analysis of Rectangular, Triangular and Circular Patch Antennas for X Band Applications Hayat Errifi, Abdennaceur Baghdad, Abdelmajid Badri, Aicha Sahel Abstract PDF | 443-452 |
| 7. | Polymeric composite laminate to increase the performance of natural stones W. Polini, L. Sorrentino, S. Turchetta, M. Fiorini Abstract PDF | 453-460 |
| 8. | Modeling of Critical Blank Holder Force Based on a Gap Limit and Unbending Strain Energy in Deep Drawing Process Susila Candra, I Made Londen Batan, Wajan Berata, Agus Sigit Pramono Abstract PDF | 461-474 |
| 9. | Performance evaluation of fuzzy and BPN based congestion controller in WSN Rekha Chakravarthi Abstract PDF | 475-481 |
| 10. | Numerical Analysis of Piles in Layered Soils: A Parametric Study Ravi Kumar Reddy C, Padmakar K C, Manjari M, Ekasaikumar CH, Saikumar K P R K Abstract PDF | 482-489 |
| 11. | Evaluation of the Performance of New Laminated Composite Shells for Motorcycle Helmets Nermin M. Aly, Ali Marwa A. Abstract PDF | 490-501 |
| 12. | Implementation of Modified EPSO Technique in 69kV Distribution Network Reconfiguration for Losses Reduction M. F. Sulaima, M.N. M. Nasir, N. H. Shamsudin, M. Sulaiman, W. M. Dahalan Abstract PDF | 502-509 |
| 13. | Feasibility of Back Propagation Network in The Design of Viterbi Decoder Balamurugan.V, Dr.N.M.Nandhitha Abstract PDF | 510-513 |
| 14. | A Symbol Based Graphical Schema Based on Position Value T.Srinivasa Ravi Kiran, R.Satya Prasad Abstract PDF | 514-529 |
| 15. | COMPARATIVE STUDY OF DIFFERENT TYPES OF ROOF AND INDOOR TEMPERATURES IN TROPICAL CLIMATE Mrs. M. Ponni, Dr. R. Baskar Abstract PDF | 530-536 |

| | | |
|-----|--|---------|
| 16. | A Developers Perspective: An Analysis of Processes Involved in Software Development of Health Care Industries Prabu.M, Narasimhan.D, Michaelraj.T.F Abstract PDF | 537-542 |
| 17. | Collaborative Smart Environments for energy-efficiency and quality of life Carmelo Felicetti, Raffaele De Rose, Cinzia Raso, Alberto Michele Felicetti, Salvatore Ammirato Abstract PDF | 543-552 |
| 18. | Monovariant H _∞ Robust Controller for a Permanent Magnet Synchronous Machine (PMSM) J. Khedri Abstract PDF | 553-561 |
| 19. | A Hybrid Coding with Adaptive Filters Using Non-uniform Technique in Speech Signals Seong-Geon Bae, Myung-Jin Bae Abstract PDF | 562-567 |
| 20. | Grouping of Tasks for Cooperative Product Development Takeshi Murayama, Toru Eguchi, Akira Ogawa Abstract PDF | 568-576 |
| 21. | Design and Development of Labview Based Steering Wheel Angle Sensor System Tony George, Susan Zacharia, Elizabeth Rufus, Zachariah C Alex Abstract PDF | 577-582 |
| 22. | An Early Bearing Fault Diagnosis using Effective Feature Selection Methods and Data Mining Techniques S.Devendiran, K.Manivannan, Soham Chetan Kamani, Razim Refai Abstract PDF | 583-598 |
| 23. | Deterministic Seismic Hazard Assessment at Bed Rock Level: Case Study for the City of Bhubaneswar, India Sukanti Rout, R. P. Nanda Abstract PDF | 599-610 |
| 24. | Improved Detection Technique for the Uncoded MIMO Systems Using an Efficient K-best Algorithm. Hellassa Wassim, Boukari Karima Abstract PDF | 611-619 |
| 25. | Incremental Generation and Prioritization of t-way Strategy for Web Based Application Mrs. B. Vani, Dr. R. Deepalakshmi Abstract PDF | 620-630 |
| 26. | PSO Based Multiuser Detection over GK Fading Channels with MRC Receive Diversity in Impulsive Noise Srinivasa Rao Vempati, Habibulla Khan, Anil Kumar Tipparti Abstract PDF | 631-639 |
| 27. | A MODIFIED COMPRESSION TECHNIQUE FOR TRACE DATA USING DICTIONARY METHOD R.AGALYA, S.SARAVANAN Abstract PDF | 640-645 |
| 28. | Experiment Results of the Microstrip Fractal Antenna in Stacked Patch Structure for Wireless Communication Applications Salai Thillai Thilagam.J, Jawahar P.K Abstract PDF | 646-658 |
| 29. | Performance Study on Multicast Routing Protocols for Scalable Wireless Sensor Networks Manikandan, H, Narasimhan, D Abstract PDF | 659-665 |
| 30. | Strength Characteristics of Fiber Reinforced Quarry Dust Stabilized Fly Ash Akshaya Kumar Sabat, Bidula Bose Abstract PDF | 666-672 |
| 31. | Proactive Exploratory Testing Methodology During Enterprise Application Modernization Ravikumar Ramadoss, N.M.Elango Abstract PDF | 673-681 |
| 32. | Simulation of Multi output Fly back Converter with Integrated Auxiliary Buck Converter with reduced components J.KOMATHI Abstract PDF | 682-691 |
| 33. | Modeling the Impact of Border Crossing Bottlenecks on Supply Chain Disruption Risk Shaheen Sardar, Young Hae Lee Abstract PDF | 692-707 |
| 34. | Utilization of Detection and Identification of Detonation (Knock) Using a Wavelet to Create a Chart for a Petrol Engine's Characteristics Agus Sujono, R. Soekrisno, Eka Firmansyah, Oyas Wahyunggoro Abstract PDF | 708-718 |

| | | |
|-----|---|---------|
| 35. | Application of Fuzzy Time Series Forecasting Model for Indian Underground Coal Mining Fatal Accident Data Anupam Anant Kher, Dr. Rajendra R. Yerpude Abstract PDF | 719-726 |
| 36. | DA based Efficient Parallel Digital FIR Filter Implementation for DDC and ERT Applications E. Chitra, T. Vigneswaran Abstract PDF | 727-733 |
| 37. | Double Ridge Cross-Waveguide Bidirectional Coupler Using Algorithms Genetic Method And HFSS Fayza BOUSALAH, Noureddine BOUKLI HACENE Abstract PDF | 734-742 |
| 38. | A Real-time Portable Bioacoustics Species Identification Design Concepts Naufal Alee, Phaklen Ehkan, L.M. Kamarudin, R. Badlishah Ahmad Abstract PDF | 743-748 |
| 39. | Method Enlarge Intensity Illumination Without Adding Power Electricity I Ketut Wijaya Abstract PDF | 749-752 |
| 40. | Preparation and Characterization of Titanium Dioxide Photoelectrodes for Generation of Hydrogen by Photoelectrochemical Water Splitting Alvaro Realpe, Diana Núñez, Isabel Carbal, María T. Acevedo, Gezira De Avila Abstract PDF | 753-759 |
| 41. | On the Resonance Conditions of Rigid Rocking Blocks Claudia Casapulla Abstract PDF | 760-771 |
| 42. | Implement an Advanced Soft Measurement Method of Mine Dust Concentration Based on K-RBF Neural Network Hong Yu, Xuezhen Cheng, Maoyong Cao, Xiaohang Gao Abstract PDF | 772-780 |
| 43. | Hierarchical Watermarking Structure for Combined LSB and Wavelet Methods Jaejoon Kim Abstract PDF | 781-785 |
| 44. | Innovative Knowledge Based System - Decision Support System for Diagnosis of Carcinogenesis Dr. N.P. Gopalan, A .Malathi Abstract PDF | 786-791 |
| 45. | A Comparative Study of Representation Methods for States of Information Poongothai. P, Devi. T Abstract PDF | 792-798 |
| 46. | Structural Behavior by Reinforcement Type in the Joint of RC Beams and Columns Mixed with Waste Tire Material Sun Tae Kwon, Jae Nam Choi, Ki Sang Son Abstract PDF | 799-807 |
| 47. | Evaluation of Seismic Performance of Weir Structures in Korea Bu Seog Ju, Woo Young Jung Abstract PDF | 808-816 |

All Rights Reserved © 2009 - 2024 Engg Journals Publications



This work is licensed under a [Creative Commons Attribution 2.5 India License](#).



Source details

International Journal of Engineering and Technology

Scopus coverage years: from 2009 to 2017

(coverage discontinued in Scopus)

Publisher: Engg Journals Publications

ISSN: 2319-8613 E-ISSN: 0975-4024

Subject area: Engineering: General Engineering

Source type: Journal

CiteScore 2015
0.8 ⓘ

SJR 2019
0.103 ⓘ

SNIP 2020
0.000 ⓘ

[View all documents >](#)

[Set document alert](#)

[Save to source list](#)

[CiteScore](#) [CiteScore rank & trend](#) [Scopus content coverage](#)

Improved CiteScore methodology

CiteScore 2015 counts the citations received in 2012-2015 to articles, reviews, conference papers, book chapters and data papers published in 2012-2015, and divides this by the number of publications published in 2012-2015. [Learn more >](#)

CiteScore 2015

0.8 = $\frac{978 \text{ Citations 2012 - 2015}}{1.201 \text{ Documents 2012 - 2015}}$

Calculated on 01 May, 2016

CiteScore rank 2015 ⓘ

| Category | Rank | Percentile |
|---------------------|----------|------------|
| Engineering | | |
| General Engineering | #145/273 | 47th |

[View CiteScore methodology >](#) [CiteScore FAQ >](#) [Add CiteScore to your site](#)

About Scopus

- What is Scopus
- Content coverage
- Scopus blog
- Scopus API
- Privacy matters

Language

- 日本語版を表示する
- 查看简体中文版本
- 查看繁體中文版本
- Просмотр версии на русском языке

Customer Service

- Help
- Tutorials
- Contact us

ELSEVIER

[Terms and conditions ↗](#) [Privacy policy ↗](#)

All content on this site: Copyright © 2024 Elsevier B.V. ↗, its licensors, and contributors. All rights are reserved, including those for text and data mining, AI training, and similar technologies. For all open access content, the Creative Commons licensing terms apply. We use cookies to help provide and enhance our service and tailor content.By continuing, you agree to the use of cookies ↗.



SJR

Scimago Journal & Country Rank

Enter Journal Title, ISSN or Publisher Name

[Home](#)[Journal Rankings](#)[Country Rankings](#)[Viz Tools](#)[Help](#)[About Us](#)

Ad served by Google

[Ad options](#)[Send feedback](#)[Why this ad?](#)


International Journal of Engineering and Technology

Discontinued in Scopus as of 2017

| | | | |
|--|--|--|----------------------------------|
| <div>COUNTRY</div> <div>India</div> <div>Universities and research institutions in India</div> <div>Media Ranking in India</div> | <div>SUBJECT AREA AND CATEGORY</div> <div>Chemical Engineering</div> <div>Fluid Flow and Transfer Processes</div> <div>Engineering</div> <div>Aerospace Engineering</div> <div>Engineering (miscellaneous)</div> <div>Mechanical Engineering</div> <div>IJFMR - Academic Journal</div> <div>IJFMR Research Journal</div> <div>Open</div> | <div>PUBLISHER</div> <div>Engg Journals Publications</div> | <div>H-INDEX</div> <div>29</div> |
| <div>PUBLICATION TYPE</div> <div>Journals</div> | <div>ISSN</div> <div>23198613, 09754024</div> | <div>COVERAGE</div> <div>2009-2017</div> | |
| <div>SCOPE</div> <div>Information not localized</div> | | | |

Join the conversation about this journal

Quartiles

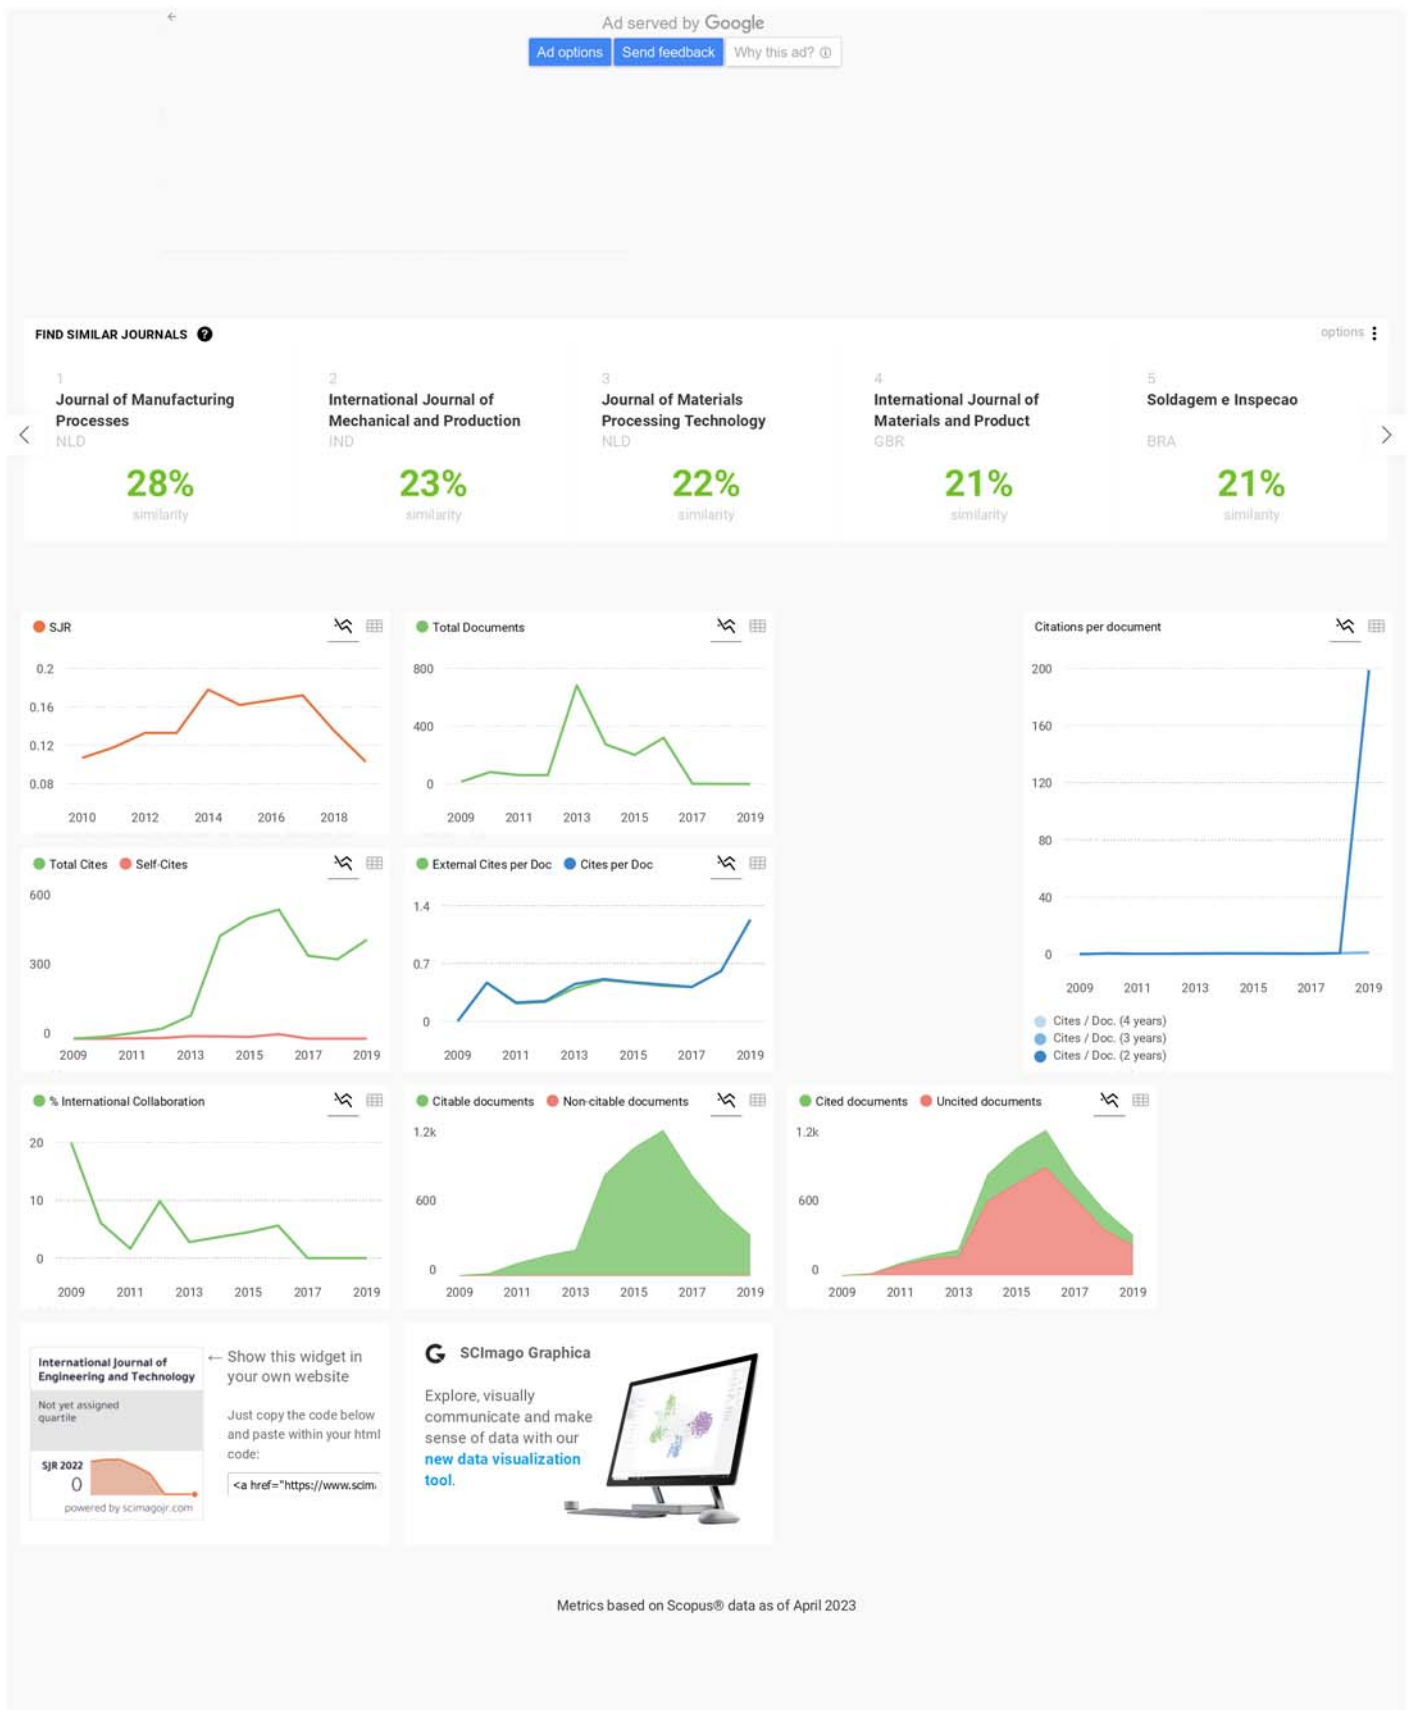

Loading comments...

Developed by:



Powered by:



Follow us on @ScimagoJR

Scimago Lab. Copyright 2007-2022. Data Source: Scopus®

EST MODUS IN REBUS
Horzeka (Scopus: 1.1.100)

[Cookie settings](#)

[Cookie policy](#)