

A SIMPLE SYNTHESIS OF NICKEL OXIDE NANOTUBE USING HIGH VOLTAGE ELECTROLYSIS

Yanatra Budi Pramana¹, Bramianto Setiawan², Prihono¹, Yitno Utomo¹, Marianus Subandowo³, Krisyanti Budipramana^{4*}

¹Department of Industrial Engineering, Faculty of Engineering, University of PGRI Adi Buana Surabaya, Indonesia

²Department of Primary Education, Faculty of Pedagogy and Psychology, Universitas PGRI Adi Buana Surabaya, Indonesia

³Department of Postgraduate physical education and sports, Universitas PGRI Adi Buana Surabaya, Indonesia

⁴Department of Pharmaceutical Biology, Faculty of Pharmacy, University of Surabaya, Surabaya 60293, Indonesia

Received: 1st September 2020; Revised: 29th September 2020; Accepted: 18th October 2020

ABSTRACT

Recently, the development of nanoparticle nickel oxide has increased due to their potential application such as biosensors, catalysts, solar cells, supercapacitors, and batteries. In this work, the addition of CTAB for nickel oxide nanoparticle synthesis using electrolysis was investigated. The nickel plates were used as anode and cathode in the electrolysis process. The process was operated at a constant voltage of 60 V for 30 minutes. The XRD result showed conformity with the Nickel oxide diffraction pattern. Meanwhile, the impurity from nickel hydroxide peaks still appeared. From FTIR characterization also indicates the band of Ni-O stretching vibration. The morphology characterization of nickel oxide using Scanning Electron Microscopy (SEM) showed the nanotube structure, while Transmission Electron Microscopy showed the nanoparticle size from 250.44 to 325.60 nm in length. On the other hand, the transformation of Ni(OH)₂ to NiO has been shown using TGA characterization.

Keywords: nanoparticles; nickel oxide; electrolysis

Introduction

Recently, the high demand for small electronic devices has made research on nanotechnology growing rapidly. Moreover, nanotechnology became more interesting due to its large surface area and different properties than the bulk materials.¹ Nickel oxide one of the metal nanoparticles has been attracted many industries due to its potential applications in modern industries such as batteries,^{2,3} solar cells,^{4,5} catalysts,^{6,7} and sensors.^{8,9} On the other hand, Indonesia has a huge nickel mine in the world, so the use of nickel-based materials is necessary.

Research on the nickel oxide nanoparticles has been conducted since 1994,¹⁰ and continues until now due to its properties such as inexpensive material as an ion storage

material, good durability and electrochemical stability, and various manufacturing possibility.¹¹ The development of research has been conducted to obtain nickel oxide nanoparticles using various methods. The use of precursors such as NiCl₂·6H₂O,¹² nickel metal¹³, and Ni(NO₃)₂·6H₂O,¹⁴ has been conducted. On the other hand, a combination method with thermal decomposition at low-temperature to synthesize nickel oxide nanoparticles also have been applied.¹⁵ The size of the nanoparticle's product is influenced by some parameters such as pH, surfactant, and co-surfactant during the process. Surfactants are commonly used as additives in the synthesis of nanoparticles because of their advantages in reducing surface tension and stabilizing the formation

*Corresponding author

E-Mail: krisyantibudipramana@staff.ubaya.ac.id

of nanoparticles. Cetyl Trimethyl Ammonium Bromide (CTAB) is a popular cationic surfactant due to its ability to produce materials with unique characteristics than different kinds of salts, such as NaCl and Na₂SO₄. Moreover, the advantages of the CTAB surfactant can stabilize the process of nucleation, coagulation, and aggregation.¹⁶

Synthesis of Nickel Oxide nanoparticles was still being carried out at this time, but the method still takes a long time to make Nickel oxide. For this reason, we investigated the synthesis of nickel oxide nanoparticles using the CTAB surfactant and electrolysis method.

Methods

Synthesize Materials

The high purity of the nickel plate (99%) was cut into a smaller size with a dimension of 10 mm x 75 mm as the cathode and anode. The 400 ml of DI water and 10 ml sodium citrate (0.3M) were mixed as electrolyte solution in 500 ml of beaker glass. Then, 1 mm of CTAB was diluted into the electrolyte solution. The process was conducted by arranged the nickel plate and electrolyte solution as shown in figure 1.

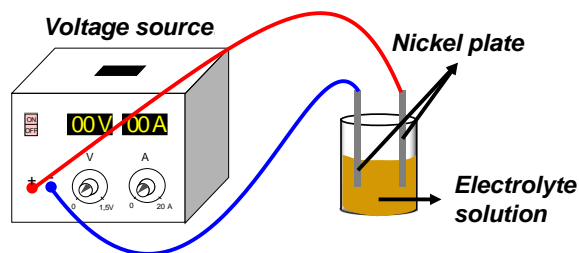


Figure 1. Schematic diagram of the electrolysis nickel plate.

The electrolysis process was carried out at a constant voltage of 60 V for 30 minutes. The solution from the electrolysis process was centrifuged and then was dried 80°C for 10 hours in the oven. After that, the sample was calcinated using a muffle furnace at 600°C to obtain the nickel oxide nanoparticles.

Sample Characterizations


The crystal structure of the sample was analyzed by Philips Xpertpor X-ray

diffraction (XRD). A Scanning Electron Microscopy (FEI Nova SEM 230) and Transmission Electron Microscopy (JEOL-JM 140) was used to know the morphology of the sample. The functional groups of the sample were analyzed by Fourier Transform Infrared Spectroscopy (Thermo Scientific Nicolet iS 10 spectrometer).


Result and Discussion

The reactions in the electrolysis process at the constant voltage of 60V for 30 minutes were shown by equation 1 and 2.^{17,18}


Cathode



Anode



In the solution, the Ni(OH)₂ was formed as shown by Equation 3.



XRD Analysis

The XRD pattern of the Nickel oxide was shown in figure 2.

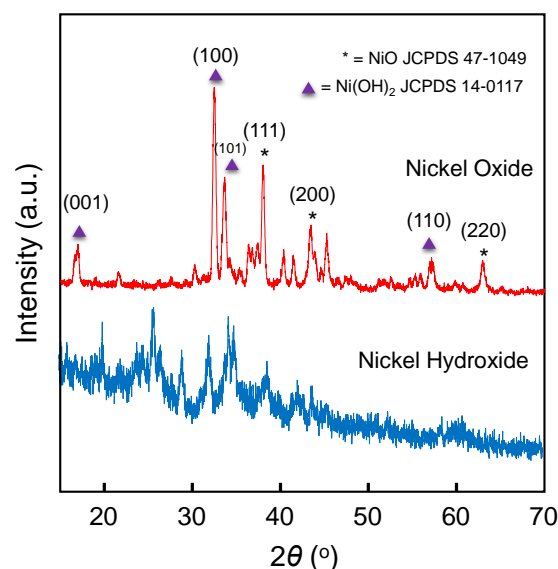


Figure 2. The X-Ray Diffraction pattern of Nickel Oxide (NiO)

There corresponding some peaks to the nickel oxide nanoparticle diffraction pattern (JCPDS 47-1049) indicate that the nickel oxide has been formed.¹¹ The appearing peaks

at $2\theta=37.94^\circ$, 43.51° , and $62,87^\circ$ can be indexed as (111), (200), and (220). Meanwhile, the impurity from nickel hydroxide peaks still appeared in the nickel oxide XRD pattern (JCPDS 14-0117), indicating the nickel oxide has not been perfectly formed.¹⁹

FTIR Analysis

Figure 3 shows the functional group of NiO and Ni(OH)₂. The NiO material had a transmittance peak at wavenumber 3397 cm^{-1} and 1640 cm^{-1} which represent the functional group of O-H vibrations and H-O-H bending vibration mode.²⁰ The appearance of O-H vibration and H-O-H bending vibration mode indicated that the sample absorbed moisture. On the other hand, the peaks at 1422 cm^{-1} and 999 cm^{-1} likely showed some precursor remnant materials in the synthesized NiO process.²¹ Meanwhile, the existence peak of Ni-O and Ni-O-H wavenumber 534 cm^{-1} and 693 cm^{-1} respectively indicate that the nickel oxide was present in the sample.^{22,23}

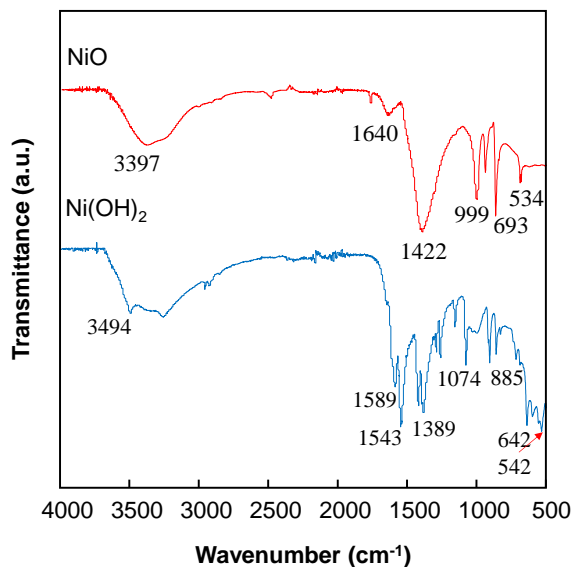


Figure 3. FTIR spectra of NiO and Ni(OH)₂.

SEM and TEM Analysis

The morphology of the NiO sample is shown in Figure 4.

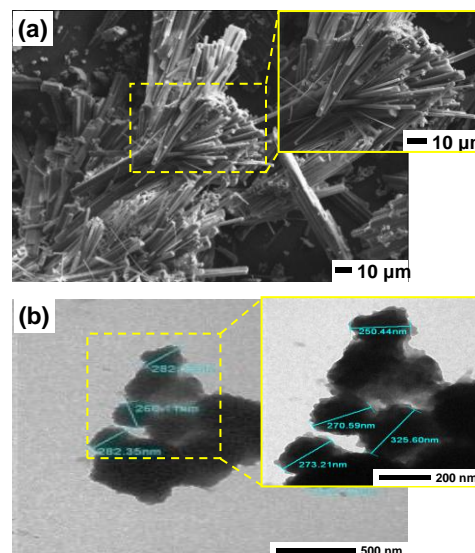


Figure 4. Characterization result of (a) SEM and (b) TEM from NiO nanotubes.

The synthesis of the NiO sample shows a tube shape in the SEM image (figure 4(a)), indicating the formation of NiO nanotubes.^{24,25} In the higher magnification, the sample has confirmed the agglomeration of one-dimensional nanotubes, and the rough surface may be caused by the set of NiO nanoparticles.²⁶ However, the sample has inhomogeneous shapes nanotubes. The inhomogeneous shapes were suspected by the existence of Nickel hydroxide and other remnant materials in the sample corresponding to the XRD and FTIR characterization. On the other hand, to know the NiO stabilized with CTAB size, the TEM characterization was conducted (figure 4(b)). TEM image showed the spherical structure of NiO with a particle size of 250.44 to 325.60 nm, indicating the sample was the nanoparticle's materials.

Thermogravimetric Analysis

The effect of heating treatment to mass changing of Ni(OH)₂ to NiO was investigated using thermogravimetric analysis. Figure 5 shows the Thermogravimetric curve of NiO at a temperature range of 100-900 °C. The first and declining points can be seen at a temperature of 170 °C with a reduced mass of about 4.0403 mg. This step is indicating the elimination of water content from the sample.²⁷ In the temperature of 320°C, the

1.180 mg of mass reduced due to the decomposition of sodium citrate.^{17,18}


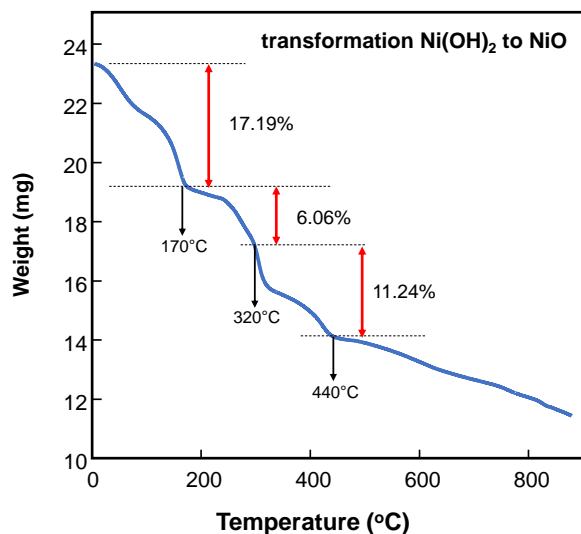


Figure 5. The thermogravimetric curve of NiO at the temperature range of 100-900 °C

Meanwhile, the last declining point can be seen at the temperature of 440°C with the 2.0536 mg mass loss. The reduced mass was possible due to the crystallization of the sample.²⁸ The conversion of Ni(OH)₂ to NiO was approximately formed at the temperature of 200-400°C (Eq. 4).²⁹



After the temperature reaches 600°C, the thermogravimetric curve became flattered. It indicates that there was not a mass loss in this temperature range of 600-900°C.

Conclusion

A simple synthesis of spherical nickel oxide (NiO) nanotubes has been successfully produced by electrolysis at high voltage techniques. The XRD result showed conformity with the Nickel oxide diffraction pattern. From FTIR characterization indicates the band of Ni-O stretching vibration. The morphology characterization of nickel oxide using Scanning Electron Microscopy (SEM) showed the nanotube structure, while Transmission Electron Microscopy showed the nanoparticle size from 250.44 to 325.60 nm in length. On the other hand, Thermogravimetric analysis (TGA) showed the transformation of Ni(OH)₂ to NiO.

References

1. Iskandar F, Setiawan B, Mayangsari TR, Maharsi R, Purwanto A, Aimon AH. Electrochemical impedance analysis of polyvinylpyrrolidone-coated sulfur/reduced graphene oxide (S/rGO) electrode. *Mater Res Express* [Internet]. 2018;6(2):25514. Available from: <http://dx.doi.org/10.1088/2053-1591/aace41>
2. Wang R, Han Y, Wang Z, Jiang J, Tong Y, Lu X. Nickel@ Nickel Oxide Core-Shell Electrode with Significantly Boosted Reactivity for Ultrahigh-Energy and Stable Aqueous Ni-Zn Battery. *Adv Funct Mater*. 2018;28(29):1802157.
3. Huang Y, Yang H, Xiong T, Adekoya D, Qiu W, Wang Z, et al. Adsorption energy engineering of nickel oxide hybrid nanosheets for high areal capacity flexible lithium-ion batteries. *Energy Storage Mater*. 2020;25:41-51.
4. Lee W, Kim I, Choi H, Kim K. Synthesis of Ni/NiO core-shell nanoparticles for wet-coated hole transport layer of the organic solar cell. *Surf Coatings Technol*. 2013;231:93-7.
5. Nie W, Tsai H, Blancon J, Liu F, Stoumpos CC, Traore B, et al. Critical role of interface and crystallinity on the performance and photostability of perovskite solar cell on nickel oxide. *Adv Mater*. 2018;30(5):1703879.
6. Wang H, Guo W, Jiang Z, Yang R, Jiang Z, Pan Y, et al. New insight into the enhanced activity of ordered mesoporous nickel oxide in formaldehyde catalytic oxidation reactions. *J Catal*. 2018;361:370-83.
7. Kang Y, Wang W, Pu Y, Li J, Chai D, Lei Z. An effective Pd-NiOx-P composite catalyst for glycerol electrooxidation: Co-existed phosphorus and nickel oxide to enhance performance of Pd. *Chem Eng J*. 2017;308:419-27.
8. Tonezzer M, Le DTT, Iannotta S, Van Hieu N. Selective discrimination of hazardous gases using one single metal oxide resistive sensor. *Sensors Actuators*

- B Chem. 2018;277:121–8.
9. Hoa ND, Hung CM, Van Duy N, Van Hieu N. Nanoporous and crystal evolution in nickel oxide nanosheets for enhanced gas-sensing performance. *Sensors Actuators B Chem.* 2018;273:784–93.
 10. Gamarnik MY. 25.P.31 Size-related change of lattice parameters in NiO nanoparticles. *J Aerosol Sci [Internet]*. 1994;25(SUPPL. 1):411–2. Available from: <https://www.scopus.com/inward/record.uri?eid=2-s2.0-0028424196&doi=10.1016%2F0021-8502%2894%2990435-9&partnerID=40&md5=4dab8473625721d99c0197b7cce95a93>
 11. El-Kemary M, Nagy N, El-Mehasseb I. Nickel oxide nanoparticles: Synthesis and spectral studies of interactions with glucose. *Mater Sci Semicond Process [Internet]*. 2013;16(6):1747–52. Available from: <http://www.sciencedirect.com/science/article/pii/S136980011300156X>
 12. Xu C, Hong K, Liu S, Wang G, Zhao X. A Novel Wet Chemical Route to NiO Nanowires. *J Cryst Growth.* 2003;255:308–12.
 13. Li C, Liu S. Preparation and Characterization of Ni(OH)₂ and NiO Mesoporous Nanosheets. *J Nanomater.* 2012;2012.
 14. Shajudheen VM, Sivakumar M, Kumar S. Synthesis and Characterization of NiO Nanoparticles by Thermal Oxidation of Nickel Sulfide Nanoparticles. *Mater Today Proc.* 2016;3(2450–2456).
 15. Barakat A, Al-Noaimi M, Suleiman M, Aldwayyan AS, Hammouti B, Hadda TB, et al. One Step Synthesis of NiO Nanoparticles via Solid-State Thermal Decomposition at Low-Temperature of Novel Aqua (2,9-dimethyl-1,10-phenanthroline) NiCl₂ Complex. *Int J Mol Sci.* 2013;14:23941–54.
 16. Kiani M, Tehrani MA, Sayahi H. Reusable and robust high sensitive non-enzymatic glucose sensor based on Ni(OH)₂ nanoparticles. *Anal Chim Acta.* 2014;839:26–33.
 17. Budipramana Y, Nurcahyanie YD, Jumali MA, Ratnawati R, Sugito S. Electrolysis Synthesis and Characterization Properties of Nickel Oxide Nanoparticle. *J Telecommun Electron Comput Eng.* 2018;10(2–3):113–6.
 18. Pramana YB, Ersam T, Kurniawan F. Synthesis nickel hydroxide by electrolysis at high voltage. *J Eng Appl Sci.* 2014;
 19. Mondal AK, Su D, Chen S, Zhang J, Ung A, Wang G. Microwave-assisted synthesis of spherical β-Ni(OH)₂ superstructures for electrochemical capacitors with excellent cycling stability. *Chem Phys Lett [Internet]*. 2014;610–611:115–20. Available from: <http://www.sciencedirect.com/science/article/pii/S0009261414006034>
 20. Abd A, Ali R, Hussein A. Fabrication And Characterization Of Nickel Oxide Nanoparticles/Silicon Heterojunction. *J Multidiscip Eng Sci Stud.* 2016 Apr 30;2:434–40.
 21. López-Ortiz A, Collins-Martínez VH, Hernández-Escobar CA, Flores-Gallardo SG, Zaragoza-Contreras EA. Protection of NiO nanoparticles against leaching in acid medium by grafting of polyacrylic acid. *Mater Chem Phys [Internet]*. 2008;109(2):306–10. Available from: <http://www.sciencedirect.com/science/article/pii/S0254058407007055>
 22. Qiao H, Wei Z, Yang H, Zhu L, Yan X. Preparation and characterization of NiO nanoparticles by anodic arc plasma method. *J Nanomater.* 2009;2009.
 23. Rahdar A, Aliahmad M, Azizi Y. NiO nanoparticles: synthesis and characterization. 2015;
 24. Ji R-Y, Chan D-S, Jow J-J, Wu M-S. Formation of open-ended nickel hydroxide nanotubes on three-dimensional nickel framework for enhanced urea electrolysis. *Electrochem Commun [Internet]*. 2013;29:21–4. Available from:

- <http://www.sciencedirect.com/science/article/pii/S1388248113000209>
25. Wu M-S, Huang K-C. Fabrication of nickel hydroxide electrodes with open-ended hexagonal nanotube arrays for high capacitance supercapacitors. *Chem Commun.* 2011;47(44):12122–4.
 26. Pang H, Lu Q, Li Y, Gao F. Facile synthesis of nickel oxide nanotubes and their antibacterial, electrochemical and magnetic properties. *Chem Commun [Internet]*. 2009;(48):7542–4. Available from:
<http://dx.doi.org/10.1039/B914898A>
 27. Patel KN, Deshpande MP, Gujarati VP, Pandya S, Sathe V, Chaki SH. Structural and optical analysis of Fe doped NiO nanoparticles synthesized by chemical precipitation route. *Mater Res Bull [Internet]*. 2018;106:187–96. Available from:
<http://www.sciencedirect.com/science/article/pii/S0025540817328295>
 28. Farooq O, Anis-ur-Rehman M, ul Haq A. Temperature dependent thermal and impedance response of NiO/Fe₂O₃ composite and compound nanoparticles. *J Alloys Compd [Internet]*. 2019;786:314–20. Available from:
<http://www.sciencedirect.com/science/article/pii/S0925838819303731>
 29. Lin C, Al-Muhtaseb S, Ritter J. Thermal Treatment of Sol-Gel Derived Nickel Oxide Xerogels. *J Sol-gel Sci Technol - J SOL-GEL SCI TECHNOL.* 2003 Aug 1;28:133–41.

Vol. 7, No. 1, Desember 2018

ISSN 1819-4018

JURNAL NEUTRINO

Jurnal Fisika dan Aplikasinya

Volume	7	No.	1	Desember	2018
--------	---	-----	---	----------	------

Journal Profile

Jurnal Neutrino

eISSN : 24605999 | pISSN : 24605999

Science

Universitas Islam Negeri Maulana Malik Ibrahim



S3

Sinta Score



Indexed by GARUDA

13

H-Index

12

H5-Index

601

Citations

485

5 Year Citations



Jurnal Neutrino

Scope of Publication

Jurnal Neutrino is physics journal and its applications (**P-ISSN:1979-6374,E-ISSN:2460-5999**) dedicated to publishing the good quality research across all aspects of experimental and theoretical applications of physics specialized in physics instrumentation, physics computation, biophysics, medical physics, environmental physics, nuclear physics, geophysics, electronics, optics and renewable energy.

Jurnal Neutrino publishes twice a year (April and October)

History Of Jurnal Neutrino

Jurnal Neutrino was first published in October 2008 in print version ISSN 1979-6374. The publication of Jurnal Neutrino aims to be the forum for academics and practitioners to write and publish their latest work. It is also to be a communications media amongs physicist in the world.

As Jurnal Neutrino had limited reader, Starting from 2012, Jurnal Neutrino published online version under Open Journal System (OJS). In 2015, Jurnal Neutrino formally received e-ISSN 2460-5999.

Jurnal Neutrino is now indexed by Crossref, Mendeley, Sinta and many more.



Editorial Team

Editor In Chief

Erika Rani M.Si, Department of Physics, Universitas Islam Negeri Maulana Malik Ibrahim Malang, Indonesia

Editor

Dr. Sungkono, (Scopus Author ID: 56136992400) Departmen Of Physics, Faculty of Mathematics and Natural Science, Institut Teknologi Sepuluh November Surabaya, Indonesia

Dr. Eny Latifah, M.Si, (Scopus Author ID: 56242585900) Department of Physics, State University of Malang, Indonesia

Dr. H. Agus Mulyono, Department of Physics, Universitas Islam Negeri Maulana Malik Ibrahim Malang, Indonesia

Utiya Hikmah, M.Si, (Scopus Author ID: 57197754656) Department of Physics, Universitas Islam Negeri Maulana Malik Ibrahim Malang, Indonesia

Farid Samsu Hananto, MT, Department of Physics, Universitas Islam Negeri Maulana Malik Ibrahim Malang, Indonesia

Muthmainnah M.Si, Department of Physics, Universitas Islam Negeri Maulana Malik Ibrahim Malang, Indonesia

Naqiibatin Nadliriyah, Department of Physics, Universitas Islam Negeri Maulana Malik Ibrahim Malang, Indonesia, Indonesia

Ahmad Luthfin, Department of Physics, Universitas Islam Negeri Maulana Malik Ibrahim Malang, Indonesia, Indonesia

International Editorial Board

Prof. Muhammad Yahaya, PhD, (Scopus Id=7003350598, h-index: 11) School of Applied Physics, Universiti Kebangsaan Malaysia, Bangi, Malaysia

Prof. Dr. rer. nat. Muhammad Nurhuda, (Scopus Author ID: 6602582826; H-INDEX: 11) Department of Physics, Brawijaya University of Malang, Indonesia

Prof. Dr. Arif Hidayat, M. Si, (Scopus Author ID = 7006069131; h-Index: 4) Department of Physics, State University of Malang, Indonesia

Web & Layout Editors

Rahmad Verdianto A.Md, Department of Physics, Maulana Malik Ibrahim State Islamic University of Malang, Indonesia

Kusairi S.Si, Department of Physics, Universitas Islam Negeri Maulana Malik Ibrahim Malang, Indonesia

Editorial Address:

Department of Physics, Faculty of Sains and Technology, Universitas Islam Negeri Maulana Malik Ibrahim Malang, Indonesia

B.J. Habibie 2nd Floor

Gajayana st. No.50 Malang 65144

Telp. 082-337-308-100

Email: neutrino@uin-malang.ac.id



Vol 13, No 1 (2020)

OCTOBER

Table Of Contents

Articles

IDENTIFICATION OF FAULT CONTINUITY AND HOT WATER RESERVOIR USE SCHLUMBERGER CONFIGURATION RESISTIVITY METHOD IN CANGAR Dhony Widyasandy, Aulia K Nugraha, Husni Cahyadi Kurniawan, Ahmad Luthfin DOI: 10.18860/neu.v13i1.8282 Views: 106 Downloads: 90	PDF 1-7
ELECTRONIC NOSE (E-NOSE) DESIGN FOR ARDUINO NANO-BASED HALAL HARAM IDENTIFICATION Muammar Kadafi, Rachmad Almi Putra DOI: 10.18860/neu.v13i1.8903 Views: 176 Downloads: 200	PDF 8-12
A SIMPLE SYNTHESIS OF NICKEL OXIDE NANOTUBE USING HIGH VOLTAGE ELECTROLYSIS Yanatra Budi Pramana, Bramianto Setiawan, Prihono Prihono, Yitno Utomo, Marianus Subandowo, Krisyanti Budipramana DOI: 10.18860/neu.v13i1.10224 Views: 135 Downloads: 83	PDF 13-18
TRANSESTERIFICATION OF PALM OIL USING THE TiO ₂ /nano-MONMORILLORITE (nano-MMT) COMPOSITE CATALYST FROM ACEH TAMIANG BENTONITE IN THE PRODUCTION OF BIODIESEL Teuku Andi Fadly, Ida Ratna Nila, Nirmala Sari DOI: 10.18860/neu.v13i1.10515 Views: 110 Downloads: 78	PDF 19-24
CROSS SECTION OF ELECTRON ANTINEUTRINO INTERACTION WITH 40AR AND 84KR AND ITS RELEVANCE TO GEONEUTRINO DETECTION Akmal Ferdiyan, Urip Nurwijayanto Prabowo DOI: 10.18860/neu.v13i1.10602 Views: 95 Downloads: 74	PDF 25-30