



B P International

B P International

F. No. SDI/BP/2314C/8089

Dated 21st Nov 21

Subject: Final decision for Manuscript No: (2021/BP/2314C), entitled: Scale-up of Green synthesis and characterization of silver nanoparticles using ethanol extract of Plantago major L. leaf and its antibacterial potential: A recent study

Dear Colleague,

We are pleased to inform that review and screening process have been completed for the following manuscript

Manuscript no: 2021/BP/2314C

Title: Scale-up of Green synthesis and characterization of silver nanoparticles using ethanol extract of Plantago major L. leaf and its antibacterial potential: A recent study

Author(s): Johan Sukweenadhia, Kezia Irianti Setiawanb, Christina Avantib, Kartini Kartinib, Esrat Jahan Rupac, Deok-Chun Yang

We are delighted to inform you that your manuscript is accepted for publication in

Book Name: Challenges and Advances in Chemical Science

Once your manuscript is moved to next process, our managing editors will keep you informed of your article's progress. You will also receive a galley proof of your manuscript for final review. We're excited to move forward with your submission. Please feel free to email me with any questions.

Thank you for submitting your paper.

Thanking you.

Dr. M. Basu

Chief Managing Editor

B P International

Reg. Offices:

India: Guest House Road, Street no - 1/6, Hooghly, West Bengal, India, Tele: +91 7439016438 | +91 9748770553 | WhatsApp: +91 7439016438

UK: Third Floor, 207 Regent Street, London, W1B 3HH, UK, Fax: +44 20-3058-1429

Website: www.bookpi.org



Letter validation link: <http://www.bookpi.org/acceptance-letter/>

Reg. Offices:

India: B P International, Guest House Road, Street no - 1/6, Hooghly, West Bengal, India, Corp. Firm Registration Number: L77527, Tele: +91 7439016438 | +91 9748770553 | WhatsApp: +91 7439016438

UK: B P International, 27 Old Gloucester Street London WC1N 3AX, UK, Fax: +44 20-3031-1429

Scale-Up of Green Synthesis and Characterization of Silver Nanoparticles Using Ethanol Extract of *Plantago major* L. Leaf and Its Antibacterial Potential: A Recent Study


Johan Sukweenadhi ^{a*}, Kezia Irianti Setiawan ^b, Christina Avanti ^b,
Kartini Kartini ^b, Esrat Jahan Rupa ^c and Deok-Chun Yang ^c

DOI: 10.9734/bpi/cacs/v8/2314C

ABSTRACT

Green synthesis of silver nanoparticles (Ag NPs) utilizing plant extracts has been widely optimized these days because of its eco-friendly, simple, and cost-effective manner. This present study was performed to evaluate the scale-up trial on synthesis parameter and centrifugation duration of *Plantago major* L. leaf ethanolic extract in the green synthesis of Ag NPs. Leaf extract concentration of 0.25%, 70°C of temperature, 60 min of synthesis time, and 30 min of centrifugation time were concluded as the optimized scale-up condition of green synthesis. The scale-up trial resulted in spherical silver nanoparticles with an average size of 12.2±5.11 nm, proven from various spectroscopic (UV-Vis, EDS, FTIR), microscopic observations (SEM, FE-TEM), and other observations (SAED, DLS, XRD). The synthesized Ag NPs exhibit good antibacterial activity against several tested bacteria at 20 µg mL⁻¹ of dosage. This study offers a nine times higher yield of the synthesized Ag NPs (107.2±6.82 mg) at about the same time as a smaller scale of green synthesis. Sufficient nanoparticles will provide flexibility to carry out its characterization efficiently and further bioactivity test and formulation experiments, such as in cosmetics, medical ointments, and other pharmaceutical products.

GRAPHICAL ABSTRACT

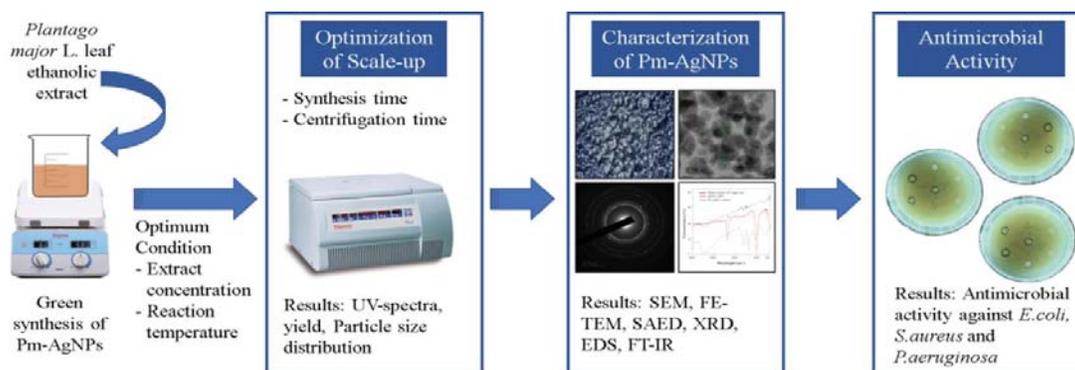

Keywords: Eco-friendly; higher yield; optimized scale-up; synthesized Ag NPs.

^a Department of Plant Biotechnology, Faculty of Biotechnology, University of Surabaya, Jalan Raya Kalirungkut, Kalirungkut, Surabaya 60293, East Java, Indonesia.

^b Department of Pharmaceutics, Faculty of Pharmacy, University of Surabaya, Jalan Raya Kalirungkut, Kalirungkut, Surabaya 60293, East Java, Indonesia.

^c Department of Oriental Medicinal Biotechnology, College of Life Sciences, Kyung Hee University, Giheung-gu, Yongin-si, Gyeonggi-do, Yongin, 446-701, Republic of Korea.

*Corresponding author: E-mail: sukwee@staff.ubaya.ac.id;

HIGHLIGHTS

- Scale-up optimization was done for green synthesis of Ag NPs from *Plantago major* L.
- Optimization process yielded almost nine times higher Ag NPs.
- Well-dispersed spherical and Ag NPs with sizes ranging from 10-20 nm were obtained.
- Synthesized Ag NPs show promising antibacterial activities.

ABBREVIATIONS

DLS	: Dynamic Light Scattering;
EDS	: Energy-dispersive X-ray spectroscopy;
FE-TEM	: Field Emission Transmission Electron Microscope;
FTIR	: Fourier Transform Infra-Red spectroscopy;
Pm-Ag NPs	: green synthesized silver nanoparticles using <i>Plantago major</i> L. leaf extract;
SAED	: selected area diffraction pattern;
SEM	: Scanning Electron Microscope;
UAE	: Ultrasonic-Assisted Extraction;
XRD	: X-ray diffraction.

1. INTRODUCTION

The benefits of *Plantago major* L. (after this called *P. major*) as folk medicines have been acknowledged globally for years. This plant has several bioactive compounds, including alkaloids, fatty acids, flavonoids, terpenoids, phenolic acid derivatives, vitamins, etc., which contribute to its specific therapeutic effects [1,2,3]. Leaf of *P. major* (called as "Daun Sendok" in Indonesia) has been widely known for its efficacy on wound healing empirically [4,5,6] among many other efficacies [1,7]. The plants, which are usually considered weeds on a daily basis, also have antibacterial [8] and antioxidant activities [9]. Based on the phytochemical analysis, it was found that plantamajoside and polyphenol content were high in its ethanol extract [7,10]. Polyphenol content is thought to be a responsible component in the wound healing process [3], whereas plantamajoside, a caffeic acid derivative, is known to have biological activities as an anti-inflammatory, antioxidant and antibacterial agent [5,10].

Nanoparticles are commonly used to increase several characteristics such as target specificity, permeability, drug activity, and bioavailability, solubility, stability, and pharmacological effects [11]. The current trend is metal nanoparticles, of which the most common are silver nanoparticles. Silver nanoparticles (Ag NPs) are widely used for antibacterial, anticancer, anti-inflammatory, and wound treatment [12]. The synthesis of nanoparticles can be done by physical, chemical, and biological methods. Physical and chemical methods were avoided due to environmental issues, while the biological method or so-called green synthesis is preferred because it is eco-friendly.

Moreover, the nanoparticle produced by the biological method is more valuable than the chemical method due to the non-existence of toxic organic residuals, minimum wastages, high volume of production, and repeatability [13]. The biological method can be conducted via plants, bacteria, yeasts, and viruses. It is known that proteins, amino acids, organic acids, vitamins, and plant secondary metabolites such as flavonoids, alkaloids, terpenoid, heterocyclic components, and polysaccharides have an important role in the synthesis of metal nanoparticles, acting as reducing and capping agents [14]. The use of plants for the synthesis of green nanoparticles is more beneficial for the resources of microorganisms [15,16].

Several previous results reported the green synthesis of nanoparticles from *P. major* with various extraction methods, solvent, plant parts, metal nanoparticles, and optimization conditions. Poor et al. [17] synthesized around 432 nm of Ag NPs utilizing water extract of *Plantago* seeds and tested on its cytotoxic activity. Lohrasbi et al. [18] made predominantly spherical Ag NPs with sizes ranging 4.6–30.6 nm from *Plantago* leaf extract and checked its decolorization activity. They used the boiling method and reflux on their way to prepare the extract, respectively. Küünal et al. [19] investigated two different conditions during the extraction of *Plantago* aerial parts. They concluded aqueous extraction

with the thermal condition and ethanol extraction with UV radiation, resulting in Ag NPs with a 50-100 nm range of size with antibacterial activities. Nikaeen et al. [20] confirmed the central composite design (CCD) prediction to optimize the Ag NPs synthesis from aqueous extract of *Plantago* seeds and yielded nanoparticles on 11 to 32.3 nm range of size.

One of the challenges that arise with green synthesis is controlling the shape and size of nanoparticles [21]. Those factors strongly affect the physical, optical, and catalytic properties of Ag NPs hence determining the application [22]. All the previous work reported various but limited *in vitro* applications of the Ag NPs from *Plantago*. Increasing the production scale needs to be done to fulfill the need to carry out further activity tests and toxicity tests. However, the scale-up trial of green synthesis is not reported yet. Ag NPs have been synthesized without any toxic reducing agent using ethanol extract of *P. major* leaf extract in this study. Up-scaling was carried out by increasing the synthesis volume and the centrifugation volume. The initial stage of the research was to optimize several synthesis parameters. The goal was to obtain the minimum time to produce an optimal amount of silver nanoparticles yield on upscale process. The final products (Pm-Ag NPs) were characterized by several spectroscopic and microscopic methods, and its antibacterial activity against Gram-positive and Gram-negative bacteria was studied by well diffusion technique. Recent study of similar green synthesis silver nanoparticles from *Plantago lanceolata* extract showed outstanding antioxidant and antibacterial activities [23]. According to the best of our knowledge, this is the first work reported the optimized scale-up green synthesis of silver nanoparticles from *Plantago* ethanolic leaf extracts. Sufficient amounts of nanoparticle will give more resource to do further experiments, such as bioactivity test add/or formulation experiments.

2. MATERIALS AND METHODS

2.1 Plant Materials and Plant Extract Preparation

The dried leaves of *P. major* were obtained from the Center for Research and Development of Medicinal and Traditional Medicinal Plants ("*Balai Besar Penelitian dan Pengembangan tanaman Obat dan Obat Tradisional*," Tawangmangu, Central Java, Indonesia) with Certificate of Plant Identification (certificate number 1258/D.T/IX/2017). The dried leaves were powdered and sorted using a mixer and 20-mesh sorting net to obtain a uniform size of powder particles. The fine leaf powder was extracted through 50% ethanol (10% w/v) using Ultrasonic-Assisted Extraction (UAE) with a frequency of 37 kHz for 20 min. The Whatman filter filters the extract and is stored at the refrigerator (4°C) for further synthesis [24].

2.2 Green Synthesis of Silver Nanoparticles and its Scale-Up Optimization

Silver nitrate (AgNO_3 ; Sigma-Aldrich, St. Louis, US) and various concentrations (w/v) of *P. major* leaf extract were used for the bio-reduction process. Each *P. major* leaf extract with concentrations of 0.25%, 0.50%, and 1.00% was mixed with AgNO_3 stock solution until reaching the final concentration of 1 mM. To find the optimal process of particle reduction, the synthesis process took place at various temperatures (60°C, 70°C, and 80°C) for 60 min. The heating and stirring process used a *hot plate magnetic stirrer* (Thermo Scientific Cimarec, Barnstead Thermolyne, NH, USA). The pH of the solution was adjusted to 10 by gently adding the NaOH 0.2 M. Several green synthesis parameters were modified from the previously reported condition (Nikaeen et al., 2020). Three independent replicates did all measurements.

Observations were done by looking at the color change into reddish-brown that marked the formation of silver nanoparticles. Plasmon resonance of silver nanoparticles was detected using a double beam ultraviolet-visible spectrophotometer (Thermo Fisher Scientific, Waltham, MA, USA). As modified from previous work, the maximum absorbance was recorded at a wavelength range between 300-500 nm [25]. Then, the purification and collection process of synthesized silver nanoparticles from *P. major* extract (Pm-Ag NPs) were done by using centrifugation at 2,000 rpm for 10 min (Hettich® Zentrifugen D-78532, Andreas Hettich GmbH & Co.KG, Tuttlingen, Germany) followed by centrifugation at 11,000 rpm for 15 min (Sorvall™ Legend™ Micro 17R Microcentrifuge, Thermo Fisher Scientific, Waltham, MA, USA). Upscaling trial was done by increasing the synthesis volume from 100 mL to 1000 mL (10x

up-scale) with the optimized condition from a small scale. First, Pm-Ag NPs were collected by centrifugation at 2000 rpm for 10 min to remove impurities. The supernatant was read for absorbance at a wavelength of 300-500 nm with a spectrophotometer. For silver nanoparticle collection, the last centrifugation step was carried out with 8 tubes. Each tube was filled with 35 ml (35x up-scale) of the purified supernatant at 11,000 rpm (Sorvall™ Biofuge Stratos centrifuge, Thermo Scientific Nalgene, Rochester, NY, USA). The duration of centrifugation was optimized by doing centrifugation at various duration, namely 5, 15, 30, and 45 min. The Pm-Ag NPs obtained after 11,000 rpm centrifugation were washed using de-ionized water to remove undesired components. Pellets were dried at room temperature till reaching their constant weight and used for further characterization and antibacterial activity tests.

2.3 Characterization of Green Synthesized Silver Nanoparticles

Estimation of particle size and its distribution were performed through the Dynamic Light Scattering technique (DLS; Delsa™ Nano C Particle Analyzer, Beckman-Coulter, USA). Data were analyzed based on three replicated tests. X-ray diffraction (XRD) was done to determine the phase distribution, crystallinity, and purity of the synthesized silver nanoparticles. XRD analysis was performed by using an X-Ray spectrometer (D8-Advance, Bruker, Germany) operated at 40 kV, 40 mA, with Cu(K α) radiation ($\lambda = 1.54 \text{ \AA}$), observation speed: 4°/min, step size 0.02, in range of the diffraction angle (2θ) from 10° to 90° [18]. The shape, morphology, and elemental distribution of the Pm-Ag NPs were analyzed by using Scanning Electron Microscope (SEM; JSM-6510, JEOL Co. Ltd., Japan) with the coating (Coater JFC-1600, JEOL Co. Ltd., Japan) and Field Emission Transmission Electron Microscope (FE-TEM) with a JEM-2100F (JEOL Co. Ltd., Japan) to check its elemental mapping. The instrument operated at 200 kV [19]. Further, the elemental mapping, selected area diffraction pattern (SAED), and energy-dispersive X-ray spectroscopy (EDX) of nanoparticles have been performed using FE-TEM (JEOL, Tokyo, Japan). Tests using Fourier Transform Infra-Red spectroscopy (FTIR; Jasco FT / IR 4200, Germany) were performed to determine the functional groups of plants present in Pm-Ag NPs.

2.4 Antibacterial Test of Synthesized Silver Nanoparticles

The antibacterial activity test was performed using the Disk Diffusion method on Muller Hinton Agar (MHA) medium. This test was performed against *Staphylococcus aureus* ATCC 25923, *Pseudomonas aeruginosa* ATCC 9027, and *Escherichia coli* ATCC 25922. Chloramphenicol ($250 \mu\text{g mL}^{-1}$) and Gentamicin ($100 \mu\text{g mL}^{-1}$) were used as a positive control against Gram-Positive and Gram-Negative bacteria, respectively. All tested bacteria were refreshed by sub-culturing it on Nutrient Broth (NB) and incubated at 37°C overnight. 100 μl bacteria suspension culture was spread over the surface of the MHA medium before the disk paper was given in a certain location at the top of MHA. 20 μl of several samples were dropped at the top of each disk. The culture was incubated for 48 hours, and then the diameter of the clear area was documented. Each treatment was done as three individual replications.

2.5 Statistical Analysis

Statistical analysis All values were presented as mean \pm SEM or mean \pm SD, n = 3. For multiple variables comparison, data were analyzed by ANOVA followed by Tukey test using GraphPad Prism statistical software (GraphPad Software Inc. Windows Version 5.01). Differences were significant at P < 0.05.

3. RESULTS AND DISCUSSION

3.1 Optimization of Green Synthesis and its Scale-Up Condition

The silver nanoparticle (Pm-Ag NPs) synthesis was done using ethanol extract of *Plantago major* L. leaf. The formation of silver nanoparticles usually could be suspected to happen by naked eye observation, that is, by changing the color of the solution into reddish-brown. Although it needs confirmation through other tests, the color change to reddish-brown is an early sign of the presence of

silver nanoparticles, as shown in previous work [26]. Surface plasmon resonance (SPR) is a characteristic of a metal that can be observed using a UV-Vis Spectrophotometer. Pm-Ag NPs from 0.25% *P. major* extract provide a high-intensity reddish-brown aqueous solution, followed by 0.5% and 1% extract concentration. On the other hand, Pm-Ag NPs from 2% and 3% *P. major* extract gave the color of the black solution. The black color usually indicates that many agglomerations have happened, and fewer nanoparticles were formed. This phenomenon was also reported in a previous study which stated that green synthesis in aqueous media under thermal heating produces larger nanoparticles that tend to agglomerate [19]. Therefore, the 2% and 3% concentrations of *P. major* extracts were not used in this research. At 60°C temperature, Pm-Ag NPs solution was showed the maximum absorbance wavelengths at 436.6 nm, 382.3 nm, and 383.3 nm, for 0.25%; 0.5%; and 1.0% *P. major* extract, respectively (Fig. 1a). At 70°C temperature, Pm-Ag NPs solution was showed the maximum absorbance wavelengths at 420.4 nm, 381.2 nm and 382.4 nm for 0.25%; 0.5%; and 1.0% *P. major* extract, respectively (Fig. 1b). Meanwhile, at 80°C temperature, Pm-Ag NPs solution was showed the maximum absorbance wavelengths at 426.4 nm, 383.8 nm and 390.4 nm for 0.25%; 0.5%; and 1.0% *P. major* extract, respectively (Fig. 1c). The characteristic of silver nanoparticles is to provide an SPR absorbance peak at wavelength 400-450 nm [27,28,29]. Other reports suggest that the peak at ~420 nm corresponds to the surface plasmon resonance of silver nanoparticles [12]. SPR shifting can be caused by increased particle size and plant extract [15,16], as shown on silver nanoparticles from *Passiflora caerulea* extract, which has been shown in silver nanoparticles a peak close to 379 nm [30].

Variations in the concentration of plant extracts can cause certain nanoparticles to differ from one another, as indicated by the various color changes of the reaction. This is due to the excitation of surface plasmon echoes in the silver nanoparticles. Due to the free conduction electrons induced by the electromagnetic field, the SPR for silver nanoparticles will receive a dark brown to reddish-brown color from colloidal silver. The conducting particles oscillate at a certain wavelength due to the SPR [31]. The increasing *P. major* extract concentration influences the amount of yield, as shown in Table 1. This may be happened by a rapid and continuous agglomeration process. Without agglomeration, particles will be dispersed very slowly and cannot form nanoparticles [32]. However, if the aggregation happened excessively, nanoparticles yield could also decrease because of eliminating the larger agglomeration at the first centrifuge step, as shown on Pm-Ag NPs yield of green synthesis using 0.50% 1.00% *P. major* leaf extract (Table 1). The decrease in absorption intensity at the optimum SPR wavelength may also be due to some silver nanoparticle aggregation [29]. 0.25% *P. major* extract at 70°C gave the strongest reddish-brown appearance, proper maximum wavelength, and highest absorbance and yield results; thus, it was selected as the synthesis parameter for an up-scale trial. The temperature and duration of the syntheses were slightly adjusted from the procedures described in previous studies [33].

For the up-scaling trial, 10x synthesis volume (1L) was applied using 0.25% *P. major* extract at 70°C with the same AgNO₃ concentration and pH condition of a smaller scale. Then, the absorbance of this solution was observed every 15 min using a spectrophotometer at a wavelength of 300-500 nm to observe the formation of silver nanoparticles (t_0 , t_{15} , t_{30} , t_{45} , and t_{60}). A color change indicates the formation of silver nanoparticles, which is a change in color from light yellow to reddish-brown (Supplementary Fig. S1a). The change in its absorption peak indicates the stability of the colloidal silver nanoparticle solution. The shift of the peak to a larger wavelength indicates less stability of the nanoparticles and tends to agglomerate. Like small-scale results, t_{60} showed the largest absorbance peak, in coherence with its solution color appearance (Supplementary Fig. S1b). The maximum absorbance was 421.8 nm, 423.3 nm, 424.2 nm, and 425.9 nm for t_{15} , t_{30} , t_{45} , and t_{60} , respectively (Supplementary Table S1).

Meanwhile, no maximum absorbance was observed for the initial extract (0.25% *P. major* extract, namely "E") and t_0 , at a range of 400-450 nm. During the scale-up trial, the stirring speed was adjusted from 120 rpm (small-scale) to 190 rpm (large-scale) by using the same device. The solution volume for the last step centrifugation was increased to 35 mL (35x up-scale) for the silver nanoparticles purification step. While using the same speed, various centrifugation duration (5, 15, 30, and 45 min) were applied. The UV-spectroscopy of its supernatant was observed as shown in Supplementary Fig. S1c. The absorbance and maximum wavelength of the supernatant resulting from

centrifugation were measured to obtain the minimum time to obtain optimal silver nanoparticles (Supplementary Table S2). Selection of the best centrifugation time determined by lowest absorbance value of the supernatant (Pm-Ag NPs solution). Within the same maximum wavelength range (420-430 nm), absorbance decreased as the duration of centrifugation increased. Still, by the 30 and 45 min, there was no longer a decrease in absorbance value. Thus, it can be concluded that the optimum centrifugation time to obtain optimal silver nanoparticles is 30 min. The yield from the up-scale trial was 107.2 ± 6.82 mg (4.29 ± 0.27 %). The result indicated that the larger scale green synthesis was done efficiently to yield a larger yield.

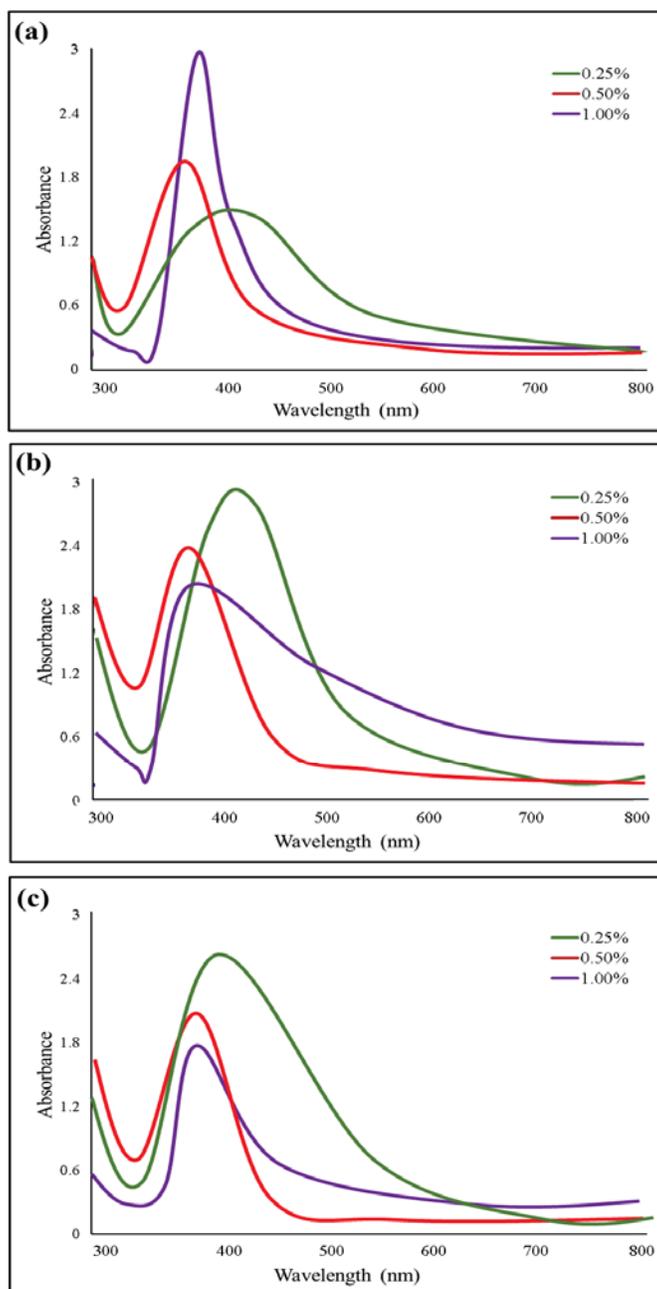


Fig. 1. UV-Vis spectra of Pm-Ag NPs solutions obtained from green-synthesis using various ethanol extract (w/v) at a different temperature: (a) 60°C, (b) 70°C, and (c) 80°C, respectively

Table 1. The yield of Pm-Ag NPs on small scale synthesis

The concentration of <i>P. major</i> Leaf Extract	Green synthesis Temperature		
	60°C	70°C	80°C
0.25%	11.2±0.87 mg ^a	11.9±0.57 mg ^a	10.8±0.93 mg ^{a,b}
	4.48±0.35 % ^a	4.75±0.23 % ^a	4.33±0.37 % ^a
0.50%	8.5±0.82 mg ^b	8.9±0.85 mg ^b	8.1±0.98 mg ^b
	3.40±0.33 % ^b	3.56±0.34 % ^b	3.25±0.39 % ^b
1.00%	5.9±0.91 mg ^c	6.1±0.97 mg ^c	5.6±0.91 mg ^c
	2.37±0.36 % ^c	2.43±0.39 % ^c	2.33±0.36 % ^c

Values are means ± SD of three determinations. Means within each column with different letters differ significantly ($P < 0.05$)

3.2 Particle Size and Distribution Study

Particle Size Analysis was used to determine the particle size and its distribution. The particle size distribution can be seen from the Polydispersity Index (PDI) value. Table 2 shows the particle size of Pm-Ag NPs and their polydispersity index. The *P. major* extract at a concentration of 0.25% yielded Ag NPs with the overall smallest particle size, whereas 0.50% and 1.00% produced overall larger sizes. Furthermore, the dispersity of Pm-Ag NPs was also measured as a PDI value. The polydispersity index (PDI) is a parameter that describes the spread or uniformity of the particle size distribution. PDI value can range between 0 to 1. The values of $PDI \leq 0.1$, $0.1-0.7$, and >0.7 are related to the highly monodispersed, moderately, and highly polydisperse distributions, respectively [34]. The other report stated that PDI less than 0.1 implies monodisperse distributions while the values more than 0.1 may imply polydisperse distributions. Polydisperse particles have poor particle size uniformities [35]. Meanwhile, the optimized scale-up synthesis condition of Pm-Ag NPs resulted in the average particle size at 12.2 ± 5.11 nm ($PDI = 0.18$). It is similar to the average particle size from the previous smaller scale of green synthesis, which resulted in 10.3 ± 3.98 nm ($PDI = 0.15$). The synthesized silver nanoparticles are nearly monodisperse due to the effective binding ability of secondary metabolites compounds with silver nanoparticles. It acts as a phyto-reductant and capping agent, resulting in uniformity on metallic nanoparticle size and minimalizing its aggregation [36,37]. The plant extract concentration needs to be optimized initially, not too little or too much to achieve that point. This result is coherent with the previous report on green synthesis of cooper [38], gold [39], and silver nanoparticles [39,40,41]. Furthermore, the optimization process of scaling up needs to be done because increasing the synthesis scale can change the rate of heat per mass transfer, which may cause differences in nanoparticle growth and the nucleation process. Therefore, it affects the yield of the green synthesis [36,42].

3.3 Shape, Morphology, and Elemental Distribution Study

The SEM results (20,000x) indicate that the nanoparticle has a spherical shape (Supplementary Fig. S2a). The Pm-Ag NPs produced through the bottom-up method will generally have a spherical shape [43,32]. Another report also supports this result, saying that Surface Plasmon Resonance (SPR) at 400-450 nm indicates that the particles have a spherical shape [26,44]. As shown in Supplementary Fig. S2b, the results of FE-TEM analysis revealed that the biosynthesized Pm-Ag NPs were spherical, with sizes ranging from ~10 nm to ~20 nm. It shows well-dispersed synthesized nanoparticles similar to previous work [15,39]. Furthermore, the FE-TEM results are coherent with the PSA results, as it shows similar spherical Pm-Ag NPs at ~10 nm to ~20 nm range of a size (Supplementary Fig. S2c). FE-TEM is the preferred method to directly observe the nanoparticles' morphology, size, and distribution [45].

SAED was used to identify the crystallite structure of the nanosized particles. There were four diffraction rings referred to [111], [200], [220], and [311] lattice plane of Bragg's reflections (Fig. 2a), which corresponds to the elemental silver, thus confirming the crystalline nature of Ag NPs. The obtained SAED patterns of Pm-Ag NPs also agreed with previous literature [45,13,32]. However, another report showed that its silver nanoparticles have five diffraction rings, referred to as the lattice pattern of [111], [200], [220], [311] and [222] [46]. The EDS spectra confirmed the silver nanoparticles

are in metallic form (Ag), with no presence of Ag_2O , which indicates the yields are free from any other impurities (Fig. 2b). The XRD pattern shows four intense peaks (as SAED results) in the whole spectrum of 2θ values ranging from 30° to 80° confirmed the presence of silver compounds in the synthesized nanoparticles (Fig. 2c). The Pm-Ag NPs analyzed by elemental mapping were visible in the electron image and were observed to be the major component in the nanoparticles (Fig. 2d).

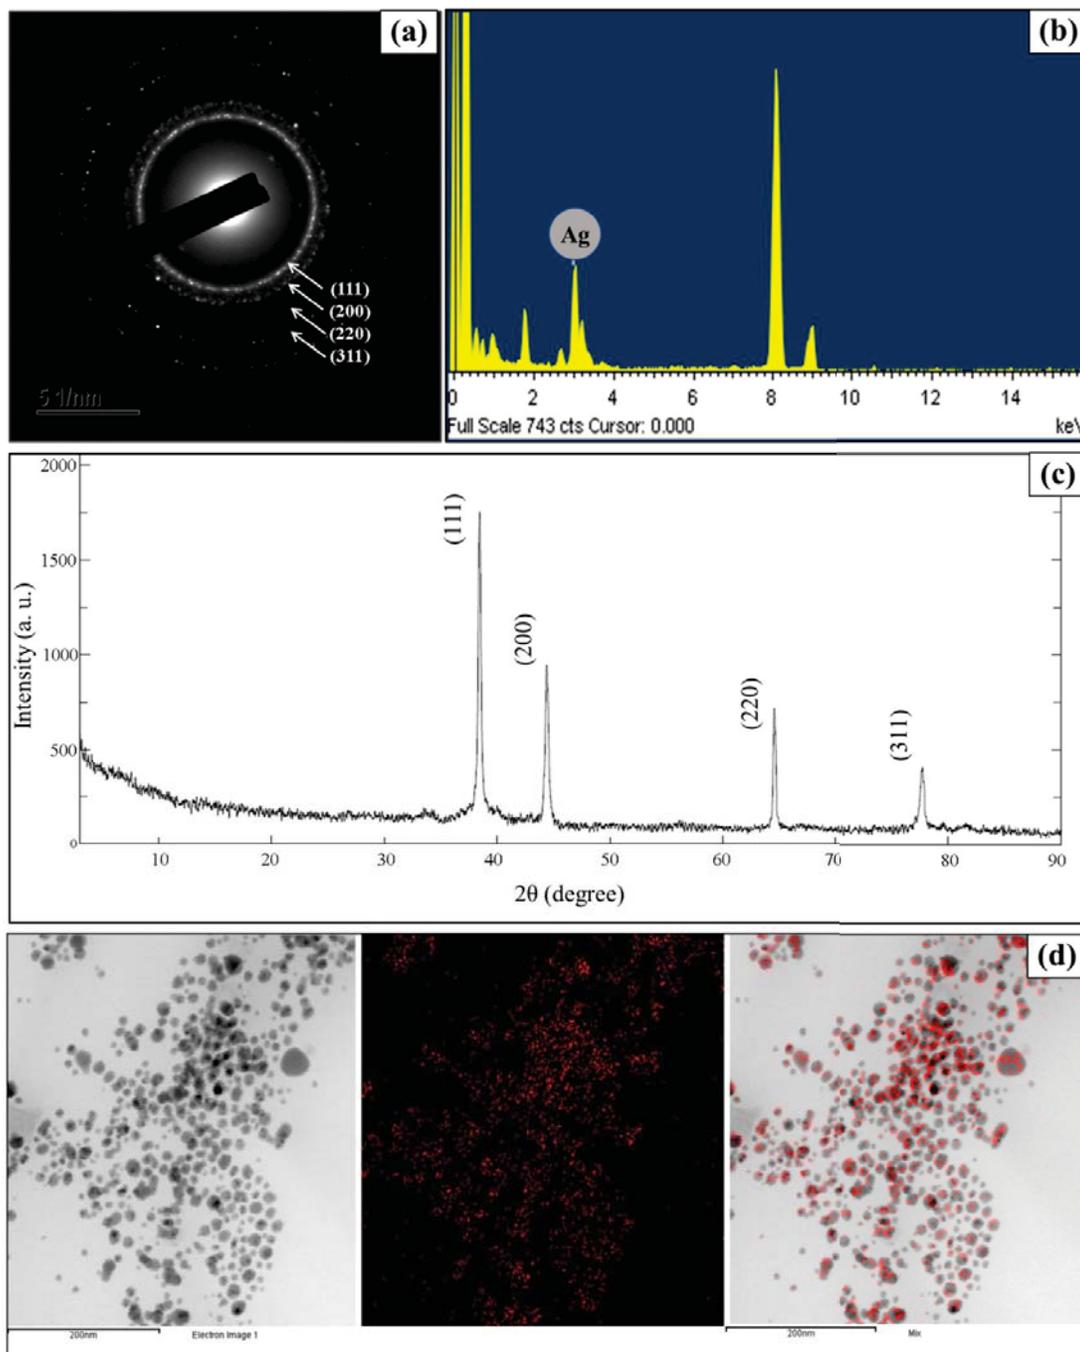


Fig. 2. (a) SAED pattern, (b) EDS spectrum, (c) XRD patterns of Pm-Ag NPs, and (d) elemental distribution mapping of Pm-Ag NPs

3.4 FTIR Analysis

FTIR analysis was used to determine the presence of functional groups in the *P. major* leaf extract and the yield of silver nanoparticles (Fig. 3). Vibration band at 3468.35 cm⁻¹ is happened due to O–H bonds, 1786.72 cm⁻¹ for bonds C=O, which is commonly found in the proteins [47], 1630.52 cm⁻¹ and 1612.2 cm⁻¹ for C–N bonds, which can be a sign of aromatic and aliphatic amines, 1408.75 cm⁻¹ for C–C or N–H bonds. The broadest peak designated to the hydroxyl group implies that this group plays a major role in the reduction of Ag⁺ and has a strong ability to bind with Ag NPs. The existence of the O–H bond, presumably derived from phenolic compounds in the *P. major*. These results also suggest a possibility of alcohol, phenol and proteins involved in the green synthesis of Ag NPs [36,17]. It is concurrent with the previous report on the observation of Pm-Ag NPs peak during FTIR analysis, and its predicted compound is shown in Supplementary Table S3. These plant metabolites act as capping and stabilizing agents for synthesized silver nanoparticles [48,12].

Table 2. Particle size average and polydispersity index of pm-ag nps on small scale synthesis

The concentration of <i>P. major</i> Leaf Extract	Green synthesis Temperature		
	60°C	70°C	80°C
0.25%	8.9±3.56 nm ^d PDI = 0.16	10.3±3.98 nm ^{c,d} PDI = 0.15	22.1±9.34 nm ^c PDI = 0.18
0.50%	49.3±21.56 nm ^{b,c} PDI = 0.19	62.7±28.3 nm ^b PDI = 0.20	76.8±33.2 nm ^{a,b} PDI = 0.19
1.00%	74.1±34.2 nm ^{a,b} PDI = 0.21	82.2±44.1 nm ^a PDI = 0.29	91.8±49.8 nm ^a PDI = 0.29

Values are means ± SD of three determinations. Means within each column with different letters differ significantly ($P < 0.05$)

Table 3. Antibacterial properties of Pm-Ag NPs

Code	Sample	Clear Zone Diameter (mm) against		
		<i>S. aureus</i>	<i>P. aeruginosa</i>	<i>E. coli</i>
1	Blank	0 ^f	0 ^f	0 ^f
2	Aquadest	0 ^f	0 ^f	0 ^f
3	0.25% <i>P. major</i> Extract	0 ^f	0 ^f	0 ^f
4	AgNO ₃ 1mM	5.73±0.164 ^e	6.85±0.393 ^d	9.56±0.351 ^{ab}
5	Pm-Ag NPs 10 µg mL ⁻¹	5.76±0.127 ^e	7.42±0.252 ^{bc}	9.12±0.152 ^b
6	Pm-Ag NPs 20 µg mL ⁻¹	7.31±0.532 ^{bc}	8.59±0.582 ^b	9.91±0.222 ^{ab}
7	Positive control	7.14±0.310 ^c	8.13±0.267 ^{bc}	10.54±1.084 ^a

Values are means ± SD of three determinations. Means within each column with different letters differ significantly ($P < 0.05$)

3.5 Antibacterial Activity Test

The mechanism of antibacterial activity of Ag NPs remains unclear to date. Meanwhile, the mechanism of action of silver itself is by disrupting the cell membrane, causing ROS, penetration of cell membrane, and will bind to DNA and protein. However, based on existing literature, the principle of the antibacterial mechanism of Ag NPs is divided into oxidative stress, metal ion release, and non-oxidative mechanism. Oxidative stress is a very important antibacterial mechanism. Ag NPs can produce superoxide radicals or reactive oxygen species (ROS) and hydroxyl ions, which can cause acute microbial death. The action that occurs is by disrupting the cell membrane, causing ROS, penetration of cell membrane, and binding to DNA and protein. The mechanism activity of Ag NPs as antibacterial is probably due to the surface charge of Ag NPs that bind to the negatively charged bacteria [49]. In our research, Gram (-) bacteria look more susceptible to Pm-Ag NPs than Gram (+) bacteria. This is due to the differences in the structure of cell membrane and cell wall between Gram (+) and Gram (-) bacteria [50]. The diameter of the clear zone region confirmed Pm-Ag NPs from either at 10 µg mL⁻¹ or 20 µg mL⁻¹ had a significantly different antibacterial activity with AgNO₃ and differed not significantly with tested antibiotics as a positive control (Fig. 4). It means that the efficacy

of synthesized silver nanoparticles was superior to that shown by AgNO_3 solution but equal compared with the chloramphenicol and Gentamicin.

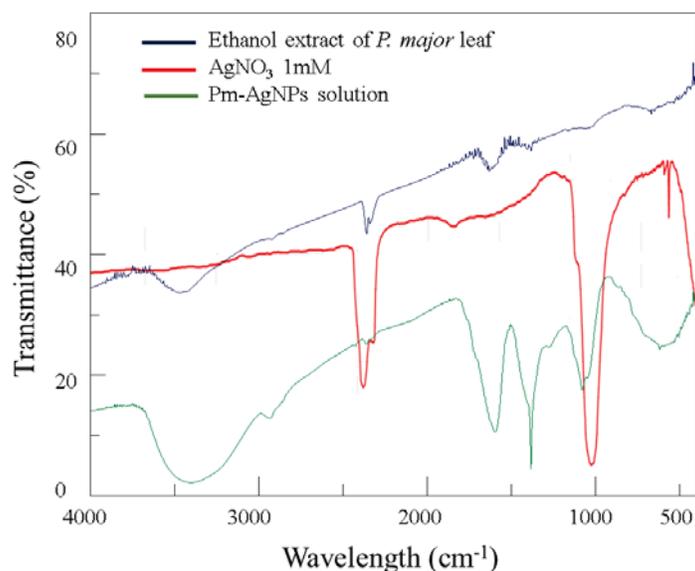


Fig. 3. FT-IR spectra of Pm-Ag NPs solutions compared with AgNO_3 and ethanol extract of *Plantago major* leaf

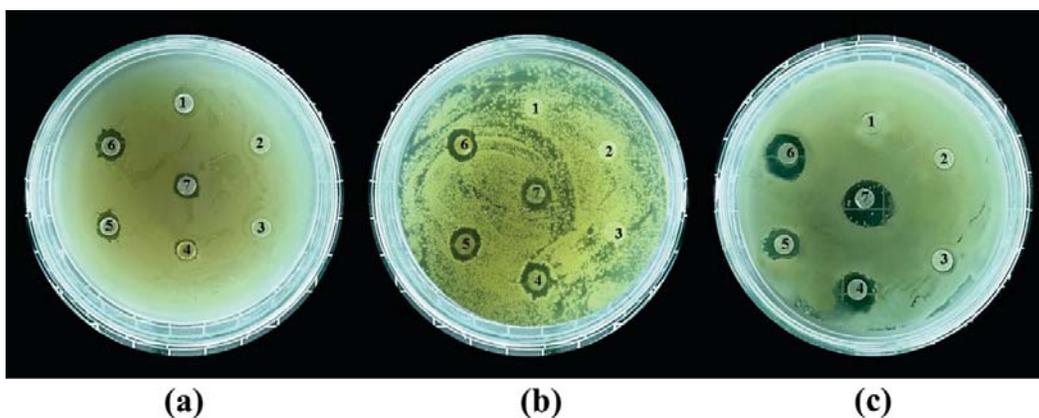


Fig. 4. Representative results of antibiotic activity test of Pm-Ag NPs against (a) *S.aureus*, (b) *E. coli* and (c) *P. aeruginosa*. Labeling Information as follows: 1 = Blank (no sample); 2 = Aquadest; 3 = 0.25% *P. major* Extract; 4 = AgNO_3 1mM; 5 = Pm-Ag NPs $10 \mu\text{g mL}^{-1}$; 6 = Pm-Ag NPs $20 \mu\text{g mL}^{-1}$; 7 = Positive control (Chloramphenicol $250 \mu\text{g mL}^{-1}$ or Gentamicin $100 \mu\text{g mL}^{-1}$)

4. CONCLUSION

An efficient scale-up and eco-friendly synthesis method of silver nanoparticles from *Plantago major* L. leaf extract have been conducted. The scale-up trial with 10x synthesis volume and 35x purification volume showed resemblant Ag NPs characteristics with the smaller scale. The spherical nanoparticles with a size ranging from 10-20 nm were obtained. All the UV-spectra and elemental analyses confirmed the presence of silver nanoparticles. The Pm-Ag NPs also exhibit potential antibacterial activity against *Staphylococcus aureus*, *Escherichia coli*, and *Pseudomonas aeruginosa* at a concentration of $20 \mu\text{g mL}^{-1}$. This study suggests that ethanolic leaf extract of *P. major* at a concentration of 0.25%, 70°C of temperature, and 60 min of synthesis can be done on a larger scale,

which efficiently offers nine times bigger yields. Therefore, there will be enough Pm-Ag NPs to be used on further bioactivity and formulation works.

FUNDING

This research was supported by the grant from the Ministry of Research and Technology/ National Research and Innovation Agency of the Republic of Indonesia (contract number 023/SP-Lit/LPPM-01/RistekBRIN/Mono/FF/III/2021) and the Korea Institute of Planning & Evaluation for Technology in Food, Agriculture, Forestry & Fisheries, Republic of Korea.

SUPPLEMENTARY MATERIALS

Supplementary material is available in the following link: https://www.bookpi.org/wp-content/uploads/2021/12/Supplementary_2021_BP_2314C.pdf

COMPETING INTERESTS

Authors have declared that no competing interests exist.

REFERENCES

1. Adom MB, Taher M, Mutalabisin MF, Amri MS, Abdul Kudus MB, Wan Sulaiman MWA, et al. Chemical constituents and medical benefits of *Plantago major*. *Biomed. Pharmacother.* 2017;96:348–360. Available:<https://doi.org/10.1016/j.biopha.2017.09.152>
2. Yernazarova KB, Abdrassulova ZT, Tuleuhanov ST, Tussupbekova GA, Salybekova NN, Isayev G, Basim H. Biological features of the medicinal plant *Plantago major* L. *Int. J. Biol. Chem.* 2019;12(1):86–93. Available:<https://doi.org/10.26577/ijbch-2019-1-i11>
3. Zubair M, Widén C, Renvert S, Rumpunen K. Water and ethanol extracts of *Plantago major* leaves show anti-inflammatory activity on oral epithelial cells. *J. Tradit. Complement. Med.* 2019;9(3):169–171. Available:<https://doi.org/10.1016/j.jtcme.2017.09.002>
4. Amini M, Kherad M, Mehrabani D, Azarpira N, Panjehshahin MR, Tanideh N. Effect of *Plantago major* on burn wound healing in rat. *J. Appl. Anim. Res.* 2010;37(1):53–56. Available:<https://doi.org/10.1080/09712119.2010.9707093>
5. Gonçalves S, Romano A. The medicinal potential of plants from the genus *Plantago* (Plantaginaceae). *Ind. Crops Prod.* 2016;83:213–226. Available:<https://doi.org/10.1016/j.indcrop.2015.12.038>
6. Kartini Islamie R, Handojo CS. Wound healing activity of aucubin on hyperglycemic rat. *J. Young Pharm.* 2018;10(2):s136–s139. Available:<https://doi.org/10.5530/jyp.2018.2s.28>
7. Nazarizadeh A, Mikaili P, Moloudizargari M, Aghajanshakeri S. Therapeutic Uses and Pharmacological Properties of *Plantago major* L. and its Active Constituents Antisecretory Effect of Hydrogen Sulfide on Gastric Acid Secretion and the Involvement of Nitric Oxide View project. *J. Basic Appl. Sci. Res.* 2013;3(9):212–221. Available:<https://www.researchgate.net/publication/256494446>
8. Dewi AF, Prajitno A, Yuniarti A. Phytochemicals and The Ability of *Plantago major* Linn. Extract to Inhibit The growth of *Aeromonas hydrophila*. *J. Exp. Life Sci.* 2019;9(2):70–75. Available:<https://doi.org/10.21776/ub.jels.2019.009.02.02>
9. Kartini K, Avanti C, Phechkrajang C, Vallisuta O. Antioxidant activity, HPTLC fingerprint, and discriminant analysis of *Plantago major* leaves from diverse origins in Indonesia. *Pharmacogn. J.* 2019;11(6):1483–1489. Available:<https://doi.org/10.5530/PJ.2019.11.229>
10. Zubair M, Nybom H, Lindholm C, Brandner JM, Rumpunen K. Promotion of wound healing by *Plantago major* L. leaf extracts - Ex-vivo experiments confirm experiences from traditional medicine. *Nat. Prod. Res.* 2016;30(5):622–624.

- Available:<https://doi.org/10.1080/14786419.2015.1034714>
11. Blanco-Fernandez B, Castaño O, Mateos-Timoneda MÁ, Engel E, Pérez-Amodio S. Nanotechnology Approaches in Chronic Wound Healing. *Adv. Wound Care.* 2020;1–67.
Available:<https://doi.org/10.1089/wound.2019.1094>
 12. Singh P, Kim YJ, Singh H, Mathiyalagan R, Wang C, Yang DC. Biosynthesis of anisotropic silver nanoparticles by *Bhargavaea indica* and their synergistic effect with antibiotics against pathogenic microorganisms. *J. Nanomater.* 2015;1–10.
Available:<https://doi.org/10.1155/2015/234741>
 13. Soshnikova V, Kim YJ, Singh P, Huo Y, Markus J, Ahn S, et al. Cardamom fruits as a green resource for facile synthesis of gold and silver nanoparticles and their biological applications. *Artif. Cells Nanomed. Biotechnol.* 2018;46(1):108–117.
Available:<https://doi.org/10.1080/21691401.2017.1296849>
 14. Duan H, Wang D, Li Y. Green chemistry for nanoparticle synthesis. *Chem. Soc. Rev.* 2015;44(16):5778–5792.
Available:<https://doi.org/10.1039/c4cs00363b>
 15. Gomathi M, Prakasam A, Rajkumar PV, Rajeshkumar S, Chandrasekaran R, Anbarasan PM. Green synthesis of silver nanoparticles using *Gymnema sylvestre* leaf extract and evaluation of its antibacterial activity. *S. Afr. J. Chem. Eng.* 2020;32:1–4.
Available:<https://doi.org/10.1016/j.sajce.2019.11.005>
 16. Ramesh AV, Devi DR, Battu GR, Basavaiah K. A Facile plant mediated synthesis of silver nanoparticles using an aqueous leaf extract of *Ficus hispida* Linn. f. for catalytic, antioxidant and antibacterial applications. *S. Afr. J. Chem. Eng.* 2018;26:25–34.
Available:<https://doi.org/10.1016/j.sajce.2018.07.001>
 17. Poor MHS, Khatami M, Azizi H, Abazari Y. Cytotoxic activity of biosynthesized Ag Nanoparticles by *Plantago major* towards a human breast cancer cell line. *Rend. Lincei Sci. Fis. Nat.* 2017;28(4):693–699.
Available:<https://doi.org/10.1007/s12210-017-0641-z>
 18. Lohrasbi S, Kouhbanani MAJ, Beheshtkhoo N, Ghasemi Y, Amani AM, Taghizadeh S. Green Synthesis of Iron Nanoparticles Using *Plantago major* Leaf Extract and Their Application as a Catalyst for the Decolorization of Azo Dye. *Bio Nano Science.* 2019;9(2):317–322.
Available:<https://doi.org/10.1007/s12668-019-0596-x>
 19. Kūūnal S, Visnapuu M, Volubujeva O, Soares Rosario M, Rauwel P, Rauwel E. Optimisation of plant mediated synthesis of silver nanoparticles by common weed *Plantago major* and their antimicrobial properties. *IOP Conference Series: Materials Science and Engineering.* 2019;613(1).
Available:<https://doi.org/10.1088/1757-899X/613/1/012003>
 20. Nikaeen G, Yousefinejad S, Rahmdel S, Samari F, Mahdavinia S. Central Composite Design for Optimizing the Biosynthesis of Silver Nanoparticles using *Plantago major* Extract and Investigating Antibacterial, Antifungal and Antioxidant Activity. *Sci. Rep.* 2020;10(1):1–16.
Available:<https://doi.org/10.1038/s41598-020-66357-3>
 21. Crisan CM, Mocan T, Manolea M, Lasca LI, Tăbăran FA, Mocan L. Review on silver nanoparticles as a novel class of antibacterial solutions. *Appl. Sci.* 2021;11(3):1–18.
Available:<https://doi.org/10.3390/app11031120>
 22. Lee SH, Jun BH. Silver nanoparticles: Synthesis and application for nanomedicine. *Int. J. Mol. Sci.* 2019;20(4).
Available:<https://doi.org/10.3390/ijms20040865>
 23. Shah MZ, Guan ZH, Din AU, Ali A, Rehman AU, Jan K, et al. Synthesis of silver nanoparticles using *Plantago lanceolata* extract and assessing their antibacterial and antioxidant activities. *Scientific Reports.* 2021;11(1):1–14.
Available:<https://doi.org/10.1038/s41598-021-00296-5>
 24. Wen C, Zhang J, Zhang H, Dzah CS, Zandile M, Duan Y, Ma H, Luo X. Advances in ultrasound assisted extraction of bioactive compounds from cash crops – A review. *Ultrason. Sonochem.* 2018;48:538–549.
Available:<https://doi.org/10.1016/j.ultsonch.2018.07.018>
 25. Fatimah I, Hidayat H, Nugroho BH, Husein S. Ultrasound-assisted biosynthesis of silver and gold nanoparticles using *Clitoria ternatea* flower. *S. Afr. J. Chem. Eng.* 2020;34:97–106.
Available:<https://doi.org/10.1016/j.sajce.2020.06.007>

26. Kartini K, Alviani A, Anjarwati D, Finna Fanany A, Sukweenadhi J, Avanti C. Process optimization for green synthesis of silver nanoparticles using Indonesian medicinal plant extracts. *Processes*. 2020;8(8). Available:<https://doi.org/10.3390/PR8080998>
27. Jalilian F, Chahardoli A, Sadrjavadi K, Fattahi A, Shokoohinia Y. Green synthesized silver nanoparticle from *Allium ampeloprasum* aqueous extract: Characterization, antioxidant activities, antibacterial and cytotoxicity effects. *Adv. Powder Technol.* 2020;31(3):1323–1332. Available:<https://doi.org/10.1016/j.appt.2020.01.011>
28. Kumar V, Singh S, Srivastava B, Bhadouria R, Singh R. Green synthesis of silver nanoparticles using leaf extract of *Holoptelea integrifolia* and preliminary investigation of its antioxidant, anti-inflammatory, antidiabetic and antibacterial activities. *J. Environ. Chem. Eng.* 2019;7(3):103094. Available:<https://doi.org/10.1016/j.jece.2019.103094>
29. Nahar K, Yang DC, Rupa EJ, Khatun K, Al-Reza SM. Eco-friendly synthesis of silver nanoparticles from *Clerodendrum viscosum* leaf extract and its antibacterial potential. *Nanomed. Res. J.* 2020;5(3):276–287. Available:<https://doi.org/10.22034/NMRJ.2020.03.008>
30. Santhoshkumar J, Sowmya B, Venkat Kumar S, Rajeshkumar S. Toxicology evaluation and antidermatophytic activity of silver nanoparticles synthesized using leaf extract of *Passiflora caerulea*. *S. Afr. J. Chem. Eng.* 2019;29:17–23. Available:<https://doi.org/10.1016/j.sajce.2019.04.001>
31. Santhoshkumar J, Kumar SV, Rajeshkumar S. Synthesis of zinc oxide nanoparticles using plant leaf extract against urinary tract infection pathogen. *Resource-Efficient Technologies.* 2017;3(4):459–465. Available:<https://doi.org/10.1016/j.reffit.2017.05.001>
32. Yap YH, Azmi AA, Mohd NK, Yong FSJ, Kan SY, Thirmizir MZA, Chia PW. Green Synthesis of Silver Nanoparticle Using Water Extract of Onion Peel and Application in the Acetylation Reaction. *Arab. J. Sci. Eng.* 2020;45(6):4797–4807. Available:<https://doi.org/10.1007/s13369-020-04595-3>
33. Tri Aksari Dewi K, Sukweenadhi J, Avanti C. Karakter Fisik dan Aktivitas Antibakteri Nanopartikel Perak Hasil Green Synthesis Menggunakan Ekstrak Air Daun Sendok (*Plantago major* L.) [Physical Characteristics and Antibacterial Activity of Silver Nanoparticle from Green Synthesis Process using Aqueous Extract of *Plantago major* L.] *Pharmaceutical Sciences and Research*, 201916(2):69–81. [in Bahasa Indonesia]
34. Honary S, Barabadi H, Gharaei-Fathabad E, Naghibi F. Green synthesis of copper oxide nanoparticles using *Penicillium aurantiogriseum*, *Penicillium citrinum* and *Penicillium waksmanii*. *Digest J. Nanomater. Bios.* 2012;7(3):999–1005.
35. Raval N, Maheshwari R, Kalyane D, Youngren-Ortiz SR, Chougule MB, Tekade RK. Importance of physicochemical characterization of nanoparticles in pharmaceutical product development. In *Basic Fundamentals of Drug Delivery*. Elsevier Inc; 2018. Available:<https://doi.org/10.1016/B978-0-12-817909-3.00010-8>
36. Marslin G, Siram K, Maqbool Q, Selvakesavan RK, Kruszka D, Kachlicki P, Franklin G. Secondary metabolites in the green synthesis of metallic nanoparticles. *Materials.* 2018;11(6):1–25. Available:<https://doi.org/10.3390/ma11060940>
37. Rajeshkumar S, Bharath LV. Mechanism of plant-mediated synthesis of silver nanoparticles – A review on biomolecules involved, characterization and antibacterial activity. *Chem. Biol. Interacts.* 2017;273:219–227. Available:<https://doi.org/10.1016/j.cbi.2017.06.019>
38. Manoj D, Saravanan R, Santhanalakshmi J, Agarwal S, Gupta VK, Boukherroub R. Towards green synthesis of monodisperse Cu nanoparticles: An efficient and high sensitive electrochemical nitrite sensor. *Sens. Actuators B Chem.* 2018;266:873–882. Available:<https://doi.org/10.1016/j.snb.2018.03.141>
39. Mariychuk R, Porubská J, Ostafin M, Čaplovičová M, Eliašová A. Green synthesis of stable nanocolloids of monodisperse silver and gold nanoparticles using natural polyphenols from fruits of *Sambucus nigra* L. *Appl. Nanosci.* 2020;10(12):4545–4558. Available:<https://doi.org/10.1007/s13204-020-01324-y>

40. Singh J, Mehta A, Rawat M, Basu S. Green synthesis of silver nanoparticles using sun dried tulsi leaves and its catalytic application for 4-Nitrophenol reduction. *J. Environ. Chem. Eng.* 2018;6(1):1468–1474.
Available:<https://doi.org/10.1016/j.jece.2018.01.054>
41. Singh P, Ahn S, Kang JP, Veronika S, Huo Y, Singh H, et al. *In vitro* anti-inflammatory activity of spherical silver nanoparticles and monodisperse hexagonal gold nanoparticles by fruit extract of *Prunus serrulata*: A green synthetic approach. *Artif. Cells. Nanomed. Biotechnol.* 2018;46(8):2022–2032.
Available:<https://doi.org/10.1080/21691401.2017.1408117>
42. Tighe CJ, Cabrera RQ, Gruar RI, Darr JA. Scale up production of nanoparticles: Continuous supercritical water synthesis of Ce-Zn oxides. *Ind. Eng. Chem.* 2013;52(16):5522–5528.
Available:<https://doi.org/10.1021/ie3025642>
43. Nasirboroumand M, Montazer M, Barani H. Preparation and characterization of biocompatible silver nanoparticles using pomegranate peel extract. *J. Photochem. Photobiol. B.* 2018;179:98–104.
Available:<https://doi.org/10.1016/j.jphotobiol.2018.01.006>
44. Rafique M, Sadaf I, Tahir MB, Rafique MS, Nabi G, Iqbal T, Sughra K. Novel and facile synthesis of silver nanoparticles using *Albizia procera* leaf extract for dye degradation and antibacterial applications. *Mater. Sci. Eng. C.* 2019;99:1313–1324.
Available:<https://doi.org/10.1016/j.msec.2019.02.059>
45. Chen L, Huo Y, Han YX, Li JF, Ali H, Batjikh I, et al. Biosynthesis of gold and silver nanoparticles from *Scutellaria baicalensis* roots and *in vitro* applications. *Appl. Phys. A.* 2020;126(6).
Available:<https://doi.org/10.1007/s00339-020-03603-5>
46. Kanniah P, Radhamani J, Chelliah P, Muthusamy N, Joshua Jebasingh Sathiya Balasingh E, Reeta Thangapandi J, et al. Green Synthesis of multifaceted silver nanoparticles using the flower extract of *aerva lanata* and evaluation of its biological and environmental applications. *ChemistrySelect.* 2020;5(7):2322–2331.
Available:<https://doi.org/10.1002/slct.201903228>
47. Hemmati S, Rashtiani A, Zangeneh MM, Mohammadi P, Zangeneh A, Veisi H. Green synthesis and characterization of silver nanoparticles using *Fritillaria* flower extract and their antibacterial activity against some human pathogens. *Polyhedron.* 2019;158:8–14.
Available:<https://doi.org/10.1016/j.poly.2018.10.049>
48. Das RK, Bhuyan D. Microwave-mediated green synthesis of gold and silver nanoparticles from fruit peel aqueous extract of *Solanum melongena* L. and study of antimicrobial property of silver nanoparticles. *Nanotechnol. Environ. Eng.* 2019;4(1):1–6.
Available:<https://doi.org/10.1007/s41204-018-0052-0>
49. Wang L, Hu C. The antimicrobial activity of nanoparticles : present situation and prospects for the future. 2017;1227–1249.
50. Dakal TC, Kumar A, Majumdar RS, Yadav V. Mechanistic basis of antimicrobial actions of silver nanoparticles. *Front. Microbiol.* 2016;7:1–17.
Available:<https://doi.org/10.3389/fmicb.2016.01831>

Biography of author(s)



Johan Sukweenadhi

Department of Plant Biotechnology, Faculty of Biotechnology, University of Surabaya, Jalan Raya Kalirungkut, Kalirungkut, Surabaya 60293, East Java, Indonesia

Research and Academic Experience: 2021 - present

- Optimization and Validation of Pilot Scale Extraction and Formulation Process of Korean Panax ginseng Extract Powder Through Cultured Roots Mountain Ginseng Technology
- Research on the Development of Molecular Markers for Early Detection of Resistant Tobacco against Ralstonia and Phytophthora

2020 - present

- Research on the Optimization of Nicotine Extraction Methods from Tobacco Agrowaste
- Prediction of flowering and fruiting of tomatoes in vitro using linear regression method based on information systems
- Formulation of Plant-Growth-Enhancing-Bacteria in Increasing Yield and / or Resistance of Commodity Crops: A Comprehensive Study on Screening of Potential Plant-Growth-Enhancing-Bacteria from Rhizosphere Isolates

2019 - present

- Development of Silver Nanoparticle-Based Diabetic Ulcer Topical Preparations: Selection of Potential Indonesian Plant Extracts for Wound Healing
- *In vitro* culture initiation and standardization of gingerol levels from the Red Ginger culture

2017-2018

- Standardization of dry weight yield and ginsenoside content from Culture Root Mountain Ginseng
- Exploration of Plant-Enhancing Bacteria-Growth-Plants from Red Rice (*Oryza sativa* L.) cv. Barak Cenana

2013 - 2016

- Development of food security by Rural Collaboration – Improving the commodity crop tolerance level against stresses
- Transcriptomic Study of Panax ginseng Meyer under Abiotic and Biotic Stresses
- Study of Physiological Response of Panax ginseng Meyer under Abiotic and Biotic Stresses
- Histological, Genomic, Transcriptomic and Metabolomic Study of Panax ginseng Meyer
- Isolation, Screening, and Characterization of Novel Bacteria from Ginseng and Ginseng soils
- Molecular Characterization of Korean Ginseng (Panax ginseng Meyer)

Bachelor Degree (2007-2011)

University of Surabaya

Faculty of Biotechnology

S.Si. (Bachelor of Science)

Master and Doctoral Degree (2012-2017)

Kyung Hee University

Graduate School of Biotechnology

Ph.D. (Doctor of Philosophy)

Research Area: Plant biotechnology, Plant Secondary Metabolites Engineering, Plant tissue culture, Plant-Microbe Interaction

Number of Published Papers: He has 36 Research articles.

Special Award: Top 10 National Outstanding Lecturer 2019 – Ministry of Research, Technology and Higher Education, Republic Indonesia.

Any Other Remarkable Point: He is a Research Consultant at Kalbe Ubaya Hanbang-Bio Laboratory Global Young Scientist Summit 2019 Attendee.

© Copyright (2022): Author(s). The licensee is the publisher (B P International).


DISCLAIMER

This chapter is an extended version of the article published by the same author(s) in the following journal. South African Journal of Chemical Engineering, 38: 1–8, 2021.

**Challenges and Advances in
Chemical Science
Vol. 8**



B.P. International

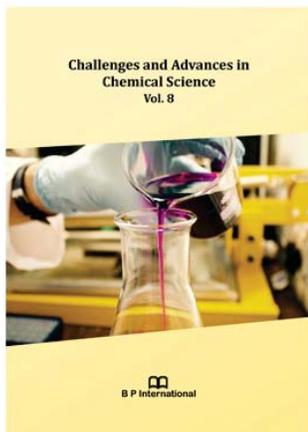

(<https://bookstore.bookpi.org/wp-content/uploads/2022/02/CACS-V8.jpg>)

Challenges and Advances in Chemical Science Vol. 8

Dr. Pradip K. Bhowmik, (Editor)

Professor, Department of Chemistry and Biochemistry, University of Nevada Las Vegas, Nevada, USA.

BOOK DETAILS ([HTTPS://STM.BOOKPI.ORG/CACS-V8/ISSUE/VIEW/540](https://stm.bookpi.org/CACS-V8/ISSUE/VIEW/540))

BUY NOW ([HTTPS://BOOKSTORE.BOOKPI.ORG/ORDER-FORM/PRODUCT=CHALLENGES+AND+ADVANCES+IN+CHEMICAL+SCIENC+8](https://bookstore.bookpi.org/order-form/product=challenges+and+advances+in+chemical+science+8))

SKU: CACS-V8

Category: Chemical Science ([Https://Bookstore.Bookpi.Org/Product-Category/Chemical-Science/](https://Bookstore.Bookpi.Org/Product-Category/Chemical-Science/))

Book Details

Editor	<i>Dr. Pradip K. Bhowmik</i>
Pages	149
Publisher	<i>B P International</i>
Language	<i>English</i>
ISBN-13 (15)	978-93-5547-065-2 (Print) 978-93-5547-353-0 (eBook)
Published	<i>February 07, 2022</i>

About The Author / Editor




Dr. Pradip K. Bhowmik

Professor, Department of Chemistry and Biochemistry,
University of Nevada Las Vegas, Nevada, USA.

Description

This book covers key areas of Chemical Science. The contributions by the authors include CO₂ conversion, polyethylene membrane, enzyme immobilization, synergistic effect, composition hydrogel, air quality index, index values, air pollutants, Green synthesis, silver nanoparticles, pharmaceutical products, calorimetry, oxidizing agent, absorption spectra, dimeric product, Raman spectroscopy, moisture content, enthalpy change, heat capacity, FT-IR spectra, Kubelka-Munk expression, diffuse reflectance spectra, chemical reactions, antitumorogenic activity, MDCK cell line, cellulose photo-oxidation, copper monochloride, chemical nickel plating. This book contains various materials suitable for students, researchers and academicians in the field of Chemical Science.

Related products

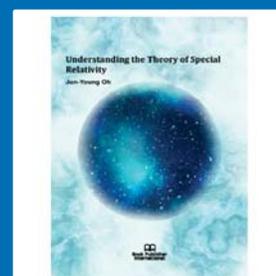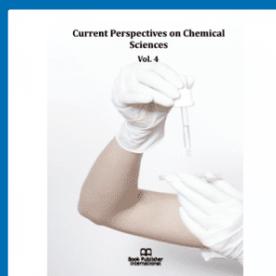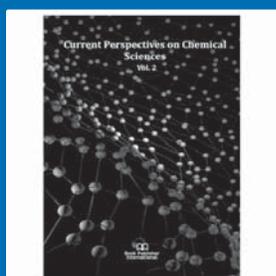

Challenges and Advances in Chemical Science Vol. 8

(<https://stm.bookpi.org/CACS-V8/index>)

(<https://stm.bookpi.org/CACS-V8/issue/current>)

New Releases

Challenges and Advances in Chemical Science Vol. 8

(<https://stm.bookpi.org/CACS-V8/issue/current>)

Our Books

(<http://www.bookpi.org/bookstore/>)



About

This book covers key areas of Chemical Science. The contributions by the authors include CO₂ conversion, polyethylene membrane, enzyme immobilization, synergistic effect, composition hydrogel, air quality index, index values, air pollutants, Green synthesis, silver nanoparticles, pharmaceutical products, calorimetry, oxidizing agent, absorption spectra, dimeric product, Raman spectroscopy, moisture content, enthalpy change, heat capacity, FT-IR spectra, Kubelka-Munk expression, diffuse reflectance spectra, chemical reactions, antitumorigenic activity, MDCK cell line, cellulose photo-oxidation, copper monochloride, chemical nickel plating. This book contains various materials suitable for students, researchers and academicians in the field of Chemical Science.

Information

Services:

1. Professional review, editing and plagiarism checking.
2. Professional cover-page design and typesetting.
3. Specialized English editing and proofreading
4. Digital Object Identifier (DOI) allotment.
5. ISBN number (online and print version)
6. Online publication of the book and printing in the press.
7. Normally Books will be closed access to increase the possibility of sale and authors will retain the copyright of the book chapter/ books. Special requests of open access books can also be considered in case of complete book publication.

Latest Articles

Activation of the Surface of Cotton Fabrics for Chemical Metallization (<https://stm.bookpi.org/CACS-V8/article/view/5637>)

Low and High Molecular Weight Chitosan Analogues of Imidazole-2-Thiosemicarbazones and Their Copper(II) Complexes: Synthesis, Characterization, and Antitumorigenic Activity in vitro (<https://stm.bookpi.org/CACS-V8/article/view/5636>)

Experimental Investigation on the Effect of Agitation and Flow Rate in Three-stage Continuous Stirrer Tank Reactors Connected in Series for Ethyl Acetate Saponification Reaction (<https://stm.bookpi.org/CACS-V8/article/view/5635>)

Determination of Three Detergent Products and Identification of Surface Active Agents by Infrared Absorption Spectra and a Reflectance Graph (<https://stm.bookpi.org/CACS-V8/article/view/5634>)

Most Viewed

Activation of the Surface of Cotton Fabrics for Chemical Metallization (<https://stm.bookpi.org/CACS-V8/article/view/5637>)

Low and High Molecular Weight Chitosan Analogues of Imidazole-2-Thiosemicarbazones and Their Copper(II) Complexes: Synthesis, Characterization, and Antitumorigenic Activity in vitro (<https://stm.bookpi.org/CACS-V8/article/view/5636>)

Experimental Investigation on the Effect of Agitation and Flow Rate in Three-stage Continuous Stirrer Tank Reactors Connected in Series for Ethyl Acetate Saponification Reaction (<https://stm.bookpi.org/CACS-V8/article/view/5635>)

Determination of Three Detergent Products and Identification of Surface Active Agents by Infrared Absorption Spectra and a Reflectance Graph (<https://stm.bookpi.org/CACS-V8/article/view/5634>)

Most Read

Activation of the Surface of Cotton Fabrics for Chemical Metallization (<https://stm.bookpi.org/CACS-V8/article/view/5637>)

Low and High Molecular Weight Chitosan Analogues of Imidazole-2-Thiosemicarbazones and Their Copper(II) Complexes: Synthesis, Characterization, and Antitumorigenic Activity in vitro (<https://stm.bookpi.org/CACS-V8/article/view/5636>)

Experimental Investigation on the Effect of Agitation and Flow Rate in Three-stage Continuous Stirrer Tank Reactors Connected in Series for Ethyl Acetate Saponification Reaction (<https://stm.bookpi.org/CACS-V8/article/view/5635>)

Determination of Three Detergent Products and Identification of Surface Active Agents by Infrared Absorption Spectra and a Reflectance Graph (<https://stm.bookpi.org/CACS-V8/article/view/5634>)

Board of Editors

Home
(<https://Bookpi.Org>) » Board Of Editors

Dr. Nadia Sabry El-Sayed El-Gohary
Mansoura University, Egypt

Prof. Matheus Ramalho de Lima
Federal Rural University of Semi-Arid, Brazil

Prof. Telat Yanik
Atatürk University, Turkey

Dr. Natt Makul
Phranakhon Rajabhat University, Thailand

Prof. Thomas F. George
University of Missouri-St. Louis One University Boulevard St. Louis, USA

Dr. Ashish Anand
University of Mississippi Med Ctr, USA and William Carey school of Osteopathic Medicine, USA

Prof. Giuseppe Murdaca
University of Genoa, Italy

Dr. Sevgul Donmez
Gaziantep University, Turkey

Prof. Ahmed Medhat Mohamed Al-Naggar
Cairo University, Egypt

Prof. Rasmia Sayed Sayed Darwesh
Agriculture Research Center, Egypt

Dr. T. Selvamuthukumar
Annamalai University, India

Prof. Mohamed M. El Nady
Egyptian Petroleum Research Institute, Egypt

Prof. Huan Yu
Chengdu University of Technology, China

Dr. Mohd Rafatullah
Universiti Sains Malaysia, Malaysia

Prof. Mohamed Fawzy Ramadan Hassanien
Umm Al-Qura University, Saudi Arabia and Zagazig University, Egypt

Prof. Lanzhuang Chen
Minami Kyushu University, Japan

Prof. Chun-Chien Kuo
National Taipei University of Business, Taiwan

Dr. George P. Laliotis
Agricultural University of Athens, Greece

Dr. Sung Cheal Moon
Korea Institute of Materials Science (KIMS), Republic of Korea

Prof. Marcello Iriti
Milan State University, Italy

Dr. Imran Aslan
Bingol University, Turkey

Dr. Him Lal Shrestha
Kathmandu Forestry College, Nepal

Prof. Luigi Giacomo Rodino
University of Turin, Italy

Prof. Cengiz Yucedag
Mehmet AkifErsoy University, Turkey

Prof. Khadiga Ahmed Ismail Eltris

Ain Shams University, Egypt

Prof. Gul Ozcan

University of Istanbul, Turkey

Prof. Vlasta Hus

University of Maribor, Slovenia

Dr. Sachin Kumar Jain

IPS Academy College of Pharmacy, India

Dr. Stephen Mugisha Akandwanaho

University of KwaZulu-Natal, South Africa

Dr. Wan Mazlina Md Saad

Universiti Teknologi MARA, Malaysia

Dr. Jean Beguinot

University of Burgundy, France

Dr. Fang Xiang

University of International and Business Economics, China

Prof. Tuneera Bhaduria

Feroze Gandhi P.G.College, India

Prof. Vijaya Khader

Acharya N.G. Ranga Agricultural University, India

Prof. Darko Nozic

General hospital Acibadem Belmedic Belgrade, Serbia

Dr. Vodnar, Dan – Cristian

University of Agricultural Sciences and Veterinary Medicine, Romania

Dr. Shigenori Ito

Sankuro Hospital, Japan

Dr. Pasquale Russo

University of Foggia, Italy

Dr. Oluyomi A. Sowemimo

Obafemi Awolowo University, Nigeria

Prof. Nicolas Padilla- Raygoza

University of Guanajuato, Mexico

Prof. Vijai Krishna Das(Retd.)

Kamla Nehru Institute of Physical and Social Sciences, India

Prof. Abdel Aziz Mousa Thabet

Al Quds University, Palestine

Prof. Francisco Cruz Sosa

Universidad Autónoma Metropolitana-Iztapalapa (UAM-Iztapalapa), Mexico

Dr. Dharmesh Chandra Sharma

J. A. Groups of Hospital and G. R. Medical College, India

Prof. Ademir de Oliveira Ferreira

Federal Rural University of Pernambuco, Brazil

Dr. Leye Samuel Ayeni

Adeyemi College of Education, Nigeria

Prof. Ashraf Talaat Youssef

Fayoum University, Egypt

Prof. Hon H. Ho

State University of New York, USA

Prof. Charbell Miguel Haddad Kury

Universidade Federal do Rio de Janeiro, Brazil

Prof. Rusu Teodor

University of Agricultural Sciences and Veterinary Medicine Cluj-Napoca, Romania

Dr. Rajeev Kumar

Navsari Agricultural University, India

Dr. Afroz Alam

Banasthali University, India

Dr. Fahmida Khan

National Institute of Technology Raipur, India

Prof. Jong-Wuu Wu

National Chiayi University, Taiwan

Dr. Tsygankova Victoria Anatolyivna

Dr. Alina Georgeta Mag
"Lucian Blaga" University of Sibiu, Romania

Prof. Mustafa Turkmen
Giresun University, Turkey

Prof. Sebahattin Tuzemen
Atatürk University, Turkey

Prof. Jorge Paredes Vieyra
Universidad Autonoma De Baja California, Mexico

Dr. Win Myint Oo
SEGi University, Malaysia

Prof. Hung-Jen Liu
National Chung Hsing University, Taiwan

Dr. M.V.N.L.Chaitanya
Chitkara University, India

Prof. Moacir Marocolo
Federal University of Juiz de Fora, Brazil

Dr. Xingting Wang
Louisiana State University, USA

Dr. Amal Hegazi Ahmed Elrefaei
Atomic Energy Authority, Egypt

Dr. Manikant Tripathi
Dr. Rammanohar Lohia Avadh University, India

Prof. Kwong Fai Andrew Lo
Chinese Culture University, Taiwan

Prof. Hari Mohan Srivastava
University of Victoria, Canada

Dr. Ramesh Gurunathan
Sunway Medical Center, & CENGILD GI Medical Centre, Malaysia

Prof. Wagih Mommtaz Ghannam
Mansoura University, Egypt

Associate Prof. (Dr.) Bakare Kazeem Kayode
Albukhary International University, Malaysia

Dr. Mehmood Ali Noor
Chinese Academy of Agricultural Sciences, China

Prof. Kuldip Singh
Government Medical College, India

Dr. P. Elangovan
B.S. Abdur Rahman Crescent Institute of Science & Technology, India

Prof. Jaffu Othniel Chilongola
Tumaini University, Tanzania

Dr. Georgios Tsoulfas
Aristoteleion University of Thessaloniki, Greece

Prof. Oscar Jaime Restrepo Baena
Universidad Nacional de Colombia, Colombia

Prof. Suprakash Chaudhury
Dr. D.Y. Patil Medical College Hospital & Research Center, India

Dr. Barkat Ali Khan
Gomal University, Pakistan

Dr. Vineet Kaswan
Sardarkrushinagar Dantiwada Agricultural University, India

Prof. Manuel Alberto M. Ferreira
Lisbon University, Portugal

Prof. Anuj Kumar Goel
Chandigarh University, India

Dr. Pietro Scicchitano
Hospital "F. Perinei" Altamura (BA), Italy

Prof. (Dr.) Erich Cosmi
University of Padua, Italy

Prof. Syed A. A. Rizvi

Larkin University, USA

IF International

[HOME](#) [ABOUT](#) [BOOKS](#) [TESTIMONIALS](#) [EDITORS](#) [PRICES](#) [SUBMISSION](#) [INDEXING](#) [CONTACT](#)

Prof. Ikem, Innocent Chiedu

Obafemi Awolowo University, Nigeria

Prof. Arun Singh

Rohilkhand Medical College & Hospital,
Bareilly International University, India

Dr. Mirnaluci Paulino Ribeiro Gama

Hospital Universitario Evangelico de Curitiba, Brazil

Prof. Magdy El-Sharkawy

Ain-Shams University, Egypt

Dr. Triki Mohamed Amine

Sahloul University Hospital, Tunisia

Dr. Salisu Muhammad Lawan

Kano University of Science and Technology (KUST), Nigeria

Dr. Aneta T. Popova

University of food technologies, Bulgaria

Prof. Gnana Sheela K

Toc H Institute of Science & Technology, India

Prof. Yong X. Gan

California State Polytechnic University, Pomona, USA

Dr. Suraya Hani Bt Adnan

Universiti Tun Hussein Onn Malaysia, Malaysia

Prof. Maria Serrano Mula

Universidad Miguel Hernandez, Spain

Prof. Pradip K. Bhowmik

University of Nevada Las Vegas, USA

Dr. Janvier Gasana

Kuwait University Health Sciences Center Faculty of Public Health, Kuwait

Dr. Georgios Androutsopoulos

University of Patras, Greece

Dr. Mohammad Reza Naroui Rad

Agriculture and Natural Resources Research and Education Center of Sistan, Iran

Dr. Naseem A. Qureshi

Al-Falah University, India

Dr. Ravi Kumar Chittoria

Jawaharlal Institute of Postgraduate Medical Education and Research, India

Prof. Olusegun Felix Ayadi

Texas Southern University, USA

Dr. Karthikeyan Venkatachalam

Prince of Songkla University, Thailand

Prof. Gabriel Olaniran Adegoke

University of Ibadan, Nigeria

Dr. Essam A. Makky

Universiti Malaysia Pahang (UMP), Malaysia

Dr. Charles Oluwaseun Adetunji

Edo University, Nigeria

Dr. Kristina Mastanjević

University of Osijek, Croatia

Prof (Dr.) Abd Elmoneim Osman Elkhalfa

University of Hail, Kingdom of Saudi Arabia

Dr. Uttara Singh

Panjab University, India

Dr. Manvesh Kumar Sihag

Mansinhbhai Institute of Dairy & Food Technology, India

Dr. Olorunjuwon Omolaja Bello

University of Medical Sciences (UNIMEDs), Nigeria

Dr. E. Seda Koc

Namik Kemal University, Turkey

Dr. Harekrushna Sutar

Indira Gandhi Institute of Technology, India

Dr. Guang Yih Sheu

Chang Jung Christian University, Taiwan

HOME ABOUT ▾ BOOKS TESTIMONIALS EDITORS PRICES SUBMISSION INDEXING CONTACT

Prof. Shi-Hai Dong

National Polytechnic Institute, Unit Professional Adolfo Lopez Mateos, Mexico

Dr. Atila Yildirim

Necmettin Erbakan University, Turkey

Dr. Ritu Singh

G.B. Pant University of Agriculture and Technology, India

Prof. Jelena Purenovic

Kragujevac University, Serbia

Prof. John Yahya I. Elshimali

UCLA School of Medicine & Charles R. Drew University of Medicine and Science, USA

Prof. Rafik Karaman

Al-Quds University, Palestine

Prof. Aurora Martínez Romero

Juarez University, Mexico

Prof. (Dr.) Turgut Türsoy

Near East University, Turkey

Dr. Maria Ciurea

University of Petroşani, Romania

Dr. Rajkumar Venkatesh Raikar

KLE Dr. M. S. Sheshgiri College of Engineering and Technology, India

Dr. Omveer Singh

Gautam Buddha University, India

Prof. Figen Balo

Firat University, Turkey

Prof. Giovanni Bucci

University of L'Aquila, Italy

Dr. FAGBADEBO Omololu Michael

Durban University of Technology, South Africa

Dr. Ho Soon Min

INTI International University, Malaysia

Dr. Madogni Vianou Irene

Universite d'Abomey-Calavi (UAC), Benin

Dr. Takashi Ikeno

National Cancer Center Hospital East, Japan

Dr. Ana Cláudia Correia Coelho

University of Trás-os-Montes and Alto Douro, Portugal

Dr. Osama A. Saeed

University of Anbar, Iraq

Prof. Oscar Jaime Restrepo Baena

Universidad Nacional de Colombia, Colombia

Prof. Rachid Masrour

Sidi Mohamed Ben Abdellah University, Morocco

Prof. Khalil Kassmi

Mohamed Premier University, Morocco

Dr. Emmanouil Magiorkinis

General Hospital for Chest Diseases "Sotiria", Greece

Dr. Asma Hanif

University of Karachi, Pakistan

Dr. Richard W. Sawadogo

Institute for Health Sciences Research, Ouagadougou, Burkina Faso

Dr. Belisario Dominguez-Mancera

University Veracruz, Mexico

Dr. Vasilii Erokhin

Harbin Engineering University, China

Dr. Neha Munjal

Lovely Professional University, India

Prof. Sandra A. Marinho

State University of Paraiba, Brazil

Dr. Farzaneh Mohamadpour

Dr. Ridzwan Che Rus
Sultan Idris Education University, Malaysia

Dr. Rajiv Dutta
Shobhit Institute of Engineering & Technology, India

Prof. Abbas Mohammed
ExAudio AB, Sweden

Prof. Chen Chin Chang
Tainan University of Technology, Taiwan

Prof. Ahmed Fawzy Yousef
Desert Research Center, Egypt

Prof. Hamdy M Afefy
Pharos University, Egypt

Prof. Raad Yahya Qassim
The Federal University of Rio de Janeiro, Brazil

Prof. (Dr.) Ana Pedro
University of Aveiro, Portugal

Dr. Veronica Mindrescu
Transylvania University of Brasov, Romania

Dr. Madogni Vianou Irene
Universite d'Abomey-Calavi (UAC), Benin

Dr. Muhammad Shehzad
University of Poonch Rawalakot, Pakistan

Prof. Qing-Wen Wang
Shanghai University, China

Prof. Randa Salah Goma Mahmoud
University of Zagazig, Egypt

Prof. Begum Rokeya
Bangladesh University of Health Sciences, Bangladesh

Prof. Gustavo Henrique Silva de Souza
Federal Institute of The North of Minas Gerais, Brazil

Prof. Koji Nagata
Korea Advanced Institute of Science and Technology, Korea

Dr. Dariusz Jacek Jakóbczak
Koszalin University of Technology, Poland

Prof. Katarina Monkova
Technical University in Kosice, Slovakia
and
Tomas Bata University in Zlin, Czech Republic

Prof. Mervat Mahdy Ramadan Mahdy
Benha University, Egypt

Prof. El-Sayed Mohamed Abo-Dahab Khedary
South Valley University, Egypt

Prof. (Dr.) Serpil Ünver Saraydın
Cumhuriyet University, Turkey

Dr. Fatima Mubarak
Aga Khan University, Pakistan

Prof. Maged Refaat
Ain Shams University, Egypt

Prof. Akmal S. Gaballa
Zagazig University, Egypt

Dr. Leo Willyanto Santoso
Petra Christian University, Indonesia

Prof. Vinoth Prabhu Veeramani
University of Tabuk, Kingdom of Saudi Arabia

Dr. Osunsanmi Foluso Oluwagbemiga
University of Zululand, South Africa

Prof. Levent SON
Mersin University, Turkey

Prof. Armando García Chiang

Universidad Autónoma Metropolitana-Iztapalapa, México

Dr. Giou-Teng, Yiang

Tzu Chi University, Taiwan, R.O.C.

Dr. LUO, Ching-Ruey (Edward)

National Chi Nan University, Taiwan

Prof. Tian-Xiao He

Illinois Wesleyan University, USA

Prof. Arthur V.M. Kwena

Moi University, Kenya

Dr. Pınar Oğuzhan Yıldız

University of Atatürk, Turkey

Prof. Ahmed Kamal Dyab

Assiut University, Egypt

Prof. Mohamed Abdel-Raheem

National Research Centre, Egypt

Dr. Iqtidar Hussain

Gomal University, Pakistan

Dr. Hayder Ali Mohammed

University of Kerbala, Iraq

Dr. Jamal Hussaini

University of Technology, Malaysia

Prof. (Dr.) Aysun Turkmen

Giresun University, Turkey

Dr. Seyed Alireza Mousavi Shirazi

Islamic AZAD University, Iran

Dr. Gonzalo Emiliano Aranda Abreu

Veracruzana University, Mexico

Prof. Kevin Fernandez

AIMST University, Malaysia

Dr. Meryem ALTUN EKİZ

Hatay Mustafa Kemal University, Turkey

Prof. (Dr.) Hasan Köten

Istanbul Medeniyet University, Türkiye

Prof. Dennis Gamad Caballes

De La Salle-College Of Saint Benilde, Philippines

Dr. Hiroko Kanoh

Yamagata University, Japan

Dr. Mariusz Cycoń

M. University of Silesia, Poland

Dr. Khalid Mjasam Batoo

King Saud University, Saudi Arabia

Dr. Katayoun Haryalchi

Guilan University of Medical Science, Iran

Prof. Ehab Abdel Aziz Ahmed EL-Shaarawy

Cairo University, Egypt

Prof. Gerald Aranoff

Ariel University, Israel

Dr. Firas Tayseer Ayasrah

Al Ain University, United Arab Emirates (UAE)

Dr. Abolfazl Azadi

AREEO, Iran

Prof. Gamal M.A. Lashin

Zagazig University, Egypt

Dr. Kamo P. Chilingaryan

Peoples' Friendship University, Russia

Dr. Mohamad Fadhili bin Yahaya

Universiti Teknologi Mara, Malaysia

Dr. Khalfa Ali

University of Ain Temouchent, Algeria

Dr. Demissu Hundie Senbeta

ABOUT US

BP International is an international publishing organization that publishes textbooks, atlases, monographs, e-books, reference books in scientific, technical, and medical areas. As an innovative publisher, BP International is helping to move science forward.

USEFUL LINKS

[Editorial Policies](#)
[Peer Review Policy](#)
[Privacy Policy](#)
[Authorship Dispute Policy](#)
[Prices](#)
[Author Guidelines](#)
[Refund Policy](#)

OUR CONTACTS

ASIA PACIFIC OFFICE

Reg. Address
Guest House Road, Street no – 1/6, Hooghly,
West Bengal, India.

Corporate Address
Diamond Heritage Building, 16, Strand Road,
Kolkata, 700001 West Bengal, India

Tel: +91 7439016438 | +91 9748770553
WhatsApp: +91 7439016438
Email: director@bookpi.org
Email: editor@bookpi.org

UK OFFICE

27 Old Gloucester Street London WC1N 3AX,
UK
Fax: +44 20-3031-1429
Email: director@bookpi.org
Email: editor@bookpi.org

FOLLOW US

Facebook (<https://www.facebook.com/bookpiofficial>)
Twitter (https://twitter.com/intent/follow?source=followbutton&variant=1.0&screen_name=bookpiofficial)
YouTube (https://www.youtube.com/channel/UCrw4-3q3kFZNdw51cKjr2XQ?sub_confirmation=1)
Blogger (<https://bookpi.blogspot.com/>)
Tumblr (<https://bookpiofficial.tumblr.com/>)
Word Press (<https://bookpublisherint.wordpress.com/>)