



# Improved oily wastewater rejection and flux of hydrophobic PVDF membrane after polydopamine-polyethyleneimine co-deposition and modification

Putu Doddy Sutrisna<sup>\*</sup>, Pra Cipta Buana W. Mustika, Ronaldo Pangestu Hadi, Caren, Yosia Elenio Gani

Department of Chemical Engineering, Universitas Surabaya (UBAYA), East Java, Indonesia

## ARTICLE INFO

### Keywords:

Polydopamine  
Polyethyleneimine  
Hydrophilicity  
O/W separation

## ABSTRACT

The surface structure and properties of a membrane largely determine its in-service performance during a filtration process. Polyvinylidene fluoride (PVDF) hydrophobic membrane is widely used in the separation of oily wastewater because of its mechanical strength, but is susceptible to oil fouling, whereas hydrophilic membranes are easily damaged in water due to their wettability but are resistant to oil. The advantages of the two membranes are then combined by modifying the hydrophobic membrane to be hydrophilic to maintain stability, mechanical strength, and antifouling performance. PVDF ultrafiltration membranes were modified with a mixture of different concentrations of polydopamine (PDA) and polyethyleneimine (PEI) using different deposition times (6, 12, and 24 h) and characterized using SEM, FTIR, and contact angle. Membrane performance was tested using a dead-end module for 60 min. The PDA-modified membrane showed a decrease in hydrophilicity from 88.1° to 77.7° after being coated with 0.5 g/L PDA for 6 h, while with the addition of 2 g/L PEI, the hydrophilicity reached 64.6°. SEM characterization showed the presence of aggregates formed during the PDA polymerization process and decreased with the addition of PEI. This is in line with the results obtained from the performance test with the dead-end module where the smaller the aggregate, the greater the flux produced. FTIR characterization showed a strong bond between PDA and PDA-PEI with the membrane as the concentration and coating time increased.

## 1. Introduction

Rapid industrial growth such as in the oil and gas, petrochemical, pharmacy, and food industries has led to an increase in oily wastewater (OWW) (Tawalbeh et al., 2018; Yue et al., 2018; Zulfiqar et al., 2019). Disposal of OWW results in various lines of environmental pollution including surface water, underground water, and soil. In addition, there is also a possibility of air pollution due to OWW that evaporates (Ahmad et al., 2020). This OWW pollution has a negative impact on surface water, where the presence of OWW blocks the entry of sunlight and oxygen into the water. Facing these challenges, various technologies have been developed for OWW separation. Meanwhile, the developed technology must have high efficiency, low energy consumption, low cost, and compact size (Fan et al., 2021). The most conventional technology is skimming, which is generally used for the separation of heterogeneous OWWs. Alternative technologies such as adsorption,

absorption, chemical and biological processes were also developed to overcome these problems, but resulted in the low effectiveness of the process, especially for water-oil emulsions which are difficult to process using these conventional techniques (Sun et al., 2020; Yang et al., 2021; Yue et al., 2019). Recently, the exploration of membrane technology as a promising solution to overcome the problems related to water management including the removal of OWW from surface water has attracted many researchers (Bolto et al., 2020). Of concern, OWW itself can be classified as free oil (>150µm), dispersed oil (20–150µm), and emulsified oil (<20µm) (Tanudjaja et al., 2019). It is generally found that OWW in surface water easily interacts with various other impurities, surfactants and forms emulsified oil. Therefore, it is appropriate to use membranes as a separation technology, because of their small droplet (<10µm) separation capability.

The selection of the right membrane for the emulsified oil filtration process is important to consider as the smaller pore size than the droplet

<sup>\*</sup> Corresponding author.

E-mail address: [pudod@staff.ubaya.ac.id](mailto:pudod@staff.ubaya.ac.id) (P.D. Sutrisna).

<https://doi.org/10.1016/j.sajce.2023.01.006>

Received 26 September 2022; Received in revised form 14 December 2022; Accepted 19 January 2023

Available online 22 January 2023

1026-9185/© 2023 The Author(s). Published by Elsevier B.V. on behalf of Institution of Chemical Engineers. This is an open access article under the CC BY-NC-ND license (<http://creativecommons.org/licenses/by-nc-nd/4.0/>).

is one of the main keys to the effectiveness of the separation. In addition to the pore size, chemical and thermal stability and mechanical strength also need to be considered (Hai et al., 2019; Hu et al., 2021; Li et al., 2018; Sun and Feng, 2017; Sun et al., 2020; Zhang et al., 2016). The membrane materials that are commonly synthesized are polysulfone (PS), polyethersulfone (PES), polyvinylidene fluoride (PVDF), polyacrylonitrile (PAN), and cellulose acetate (CA) (Padaki et al., 2015; Subasi and Cicek, 2017). In this research, PVDF-based membranes were selected for research and development. This is based on the resistance to chemical compounds and its stability in various operating pressures. Although PVDF membrane has many advantages, it has very hydrophobic properties (Liu et al., 2014). Therefore, PVDF membranes tend to have a higher risk of fouling (Zhao et al., 2013). Moreover, the formation of fouling on the membrane has a fatal effect on decreasing the separation efficiency, so the related issue is always a trend to be discussed (Li et al., 2019). Surface modification is one alternative to reduce membrane hydrophobicity (Tang et al., 2017). The formation of a hydration layer on the surface inhibits the formation of fouling due to the bonding of water with the hydrophilic surface.

Many efforts have been made to improve the properties of PVDF membranes, especially hydrophilicity and resistance to fouling. Almaie et al. have succeeded in reducing the hydrophilicity of PVDF membranes through modification of the active surface of the membrane (Almaie et al., 2022). Several selected studies related to OOW separation using PVDF membranes can be seen in Table 1.

Surface modification using polydopamine (PDA) has attracted much attention because of its strong adhesive properties with abundant functional moieties and excellent biocompatibility. This ability refers to self-polymerization which ensures the formation of bonds (Li et al., 2019). In addition, the nature of PDA which tends to be hydrophilic can prevent the formation of fouling due to organic compounds (McCloskey et al., 2010). However, the deposition of PDA is a time-consuming process, and the resulting hydrophilicity is barely satisfactory (Li et al., 2018; Wardani et al., 2019). PDA oligomers usually form rough surfaces and large aggregate particles because of the non-covalent interaction. Therefore, it is possibly lead to membrane fouling and reduce water permeability.

Polyethyleneimine or PEI could react with amine and catechol causing covalent bonds that lead to strong networks to improve coating stability. Apart from that, PEI is also known as an amine-rich cationic polymer (Zhao et al., 2015). Thus, PEI can combine with PDA through a

Michael-addition and Schiff-base reaction mechanism. Therefore, the aggregate formed in solution will contain PDA and PEI, and both will be deposited together into the substrate simultaneously (Lv et al., 2018). The mechanism by which PEI occurs is believed to be able to react with oxidized dopamine and inhibit the interaction of hydrogen bonds and  $\pi$ - $\pi$  bonds. The same thing was also reported by Lv et al., who tested the kinetics of PEI/PDA coating on the surface of silicon wafers (Lv et al., 2018). Illustrations of the reaction and coating mechanisms can be seen in Figs. 1d and 1e. The addition of PEI significantly accelerated the deposition reaction process between PDA and PEI (Qiu et al., 2018). On the other hand, the addition of PEI also reduced particle size and hinder non-covalent interactions forming a homogenous and loose layer on a substrate during the polymerization process (Ding et al., 2020). PEI also increases the membrane surface wettability causing a more hydrophilic membrane.

In this research, it is hoped that a breakthrough will be obtained related to improving the properties of PVDF membranes through modifications using PDA-PEI. The scope of successful modification includes: hydrophobicity-hydrophilicity, permeability, rejection. The hope is to obtain hydrophilic PVDF membranes with high rejection and flux capabilities.

## 2. Materials and methods

### 2.1. Materials


Polyvinylidene fluoride (PVDF) membrane was obtained from Microdyn-Nadir with a nominal pore size of 0.03 $\mu$ m. Dopamine-HCl, Polyethylenimine, and 20mM tris buffer saline were supplied from Sigma Aldrich. NaOH 0.1N was supplied from Emsure, the other chemicals were tween 20, oil, and acetone were used without any further modifications. Commercial palm oil has the following specifications: Density at 40°C=0.916 $\pm$ 0.005 g/cm<sup>3</sup>, Kinematic viscosity at 40°C=35.7 mm<sup>2</sup>/s, pH at 25°C=5.4. All solutions were prepared by aquadest.

### 2.2. Coating PVDF membrane

PVDF membrane coating was carried out by immersing the membrane in various modifying solutions. First of all, before the modification process, membrane needs to be washed by soaking in acetone for 30

**Table 1**  
Selected studies related to oily wastewater separation using PVDF membranes.

Materials	Synthesis and/or Modified Method	Results Permeation Flux (L.m <sup>-2</sup> .h <sup>-1</sup> )	Separation Efficiencies (%)	Detail Properties Improvement	Ref
PZGS-PVDF (0, 0.5, 1.0, and 1.5%PZGS)	Phase Immersion (PI)	5.7 – $\pm$ 71	77.2 – 99.3	The addition of PZGS in the synthesis of PVDF is proven to be able to increase hydrophilicity, which is indicated by a decrease in the contact angle from 84.1° to 58.1° The stability of the membrane separation performance in the acid – neutral – base range was also obtained by the addition of the PZGS.	(Mansha et al., 2022)
PVDF-b-PVI Membrane	Atom transfer radical polymerization (ATRP)	181 $\pm$ 1.82 – 420.25 $\pm$ 0.96	81.2 $\pm$ 2.1 – 98.08 $\pm$ 0.5	The modification using [CuBr]:[DMDP] increased the hydrophilicity, which was marked by a decrease in the contact angle from 89.5° to 30.98° In addition, the modification was also successful in the formation of anti-fouling on the membrane surface.	(Valizadeh et al., 2022)
PVDF-b-P (PEGMA-co-BVIm-Br) membrane	Nonsolvent-induced phase separation (NIPS)	176 – 400	81.2 – 96.1	The successful modification reduced the hydrophobicity of the membrane, indicated by a decrease in the contact angle, which was originally 89.5° $\pm$ 1.96 to 33.8° $\pm$ 1.55. In addition, the modification also succeeded in increasing the stability of the flux and resistance to fouling.	(Valizadeh et al., 2021)
CCB-Fe/PPnp-PVDF	Phase Immersion (PI)	$\pm$ 9 – $\pm$ 11	~ 99	The successful modification reduced the potential for fouling by reducing hydrophobicity (CA 81° $\pm$ 0.9 to 44° $\pm$ 1.7).	(Baig et al., 2022)
PVDF/PPAm-TA	Immersing	1184.3	99.47	Properties have improved, especially resistance to fouling, service life, hydrophobicity (135° – 158)	(Jiang et al., 2022)
PVDF/PDA-PEI	Immersing	This will be discussed later			This work

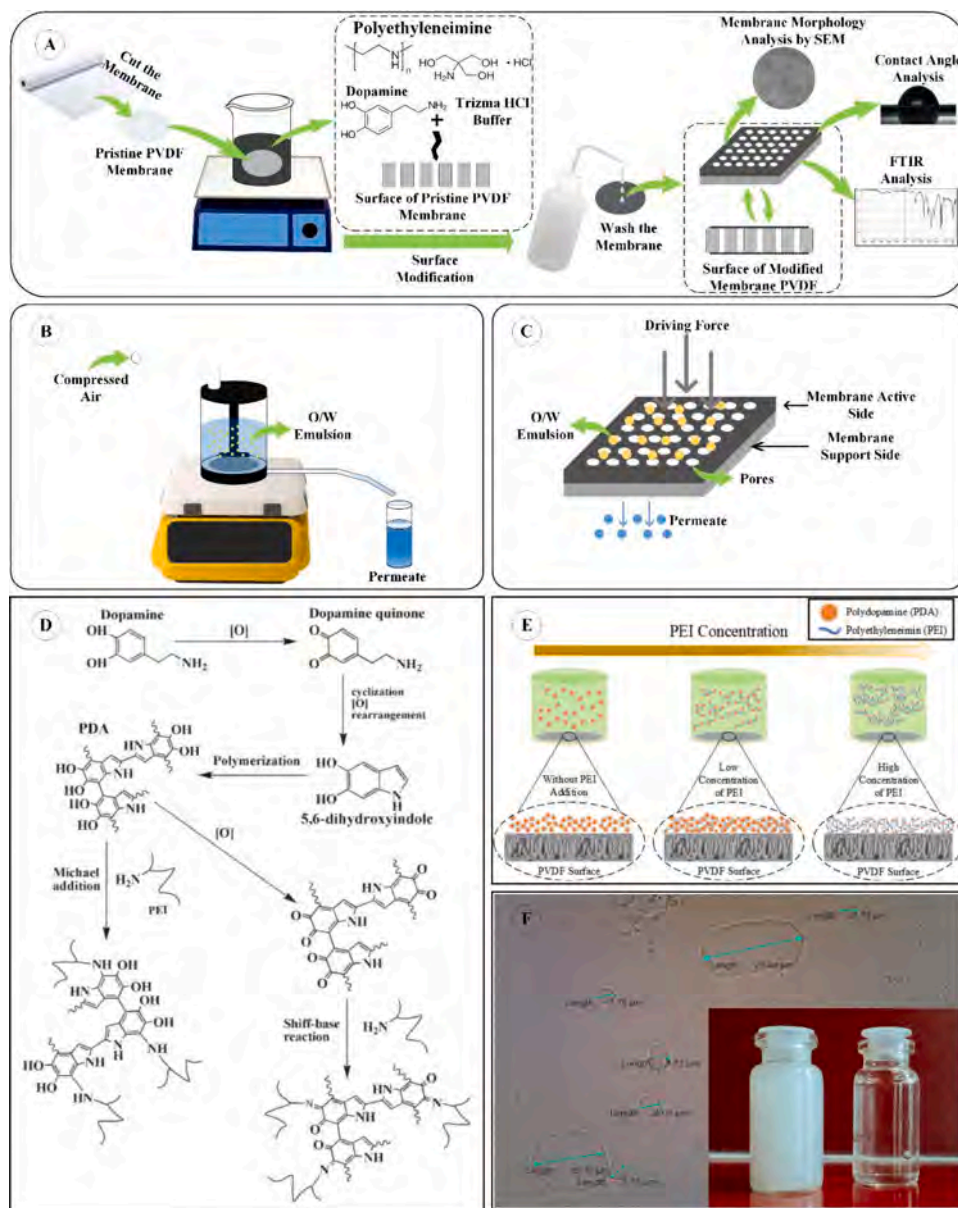

**Fig. 1.** Schematic illustration of (a) PVDF membrane modification, (b) Dead-end filtration, (c) Filtration process mechanism, (d) PDA-PEI copolymerization mechanism (Reproduced with permission from Zhao et al., (2015), (e) PEI concentration effect on copolymerization, (f) OWW droplet under a microscope.

min. At the same time, PDA solution was prepared by dissolving dopamine-HCL with Trizma-HCL pH 8.5 for concentrations of 0.5, 1, 2, and 3 g/L, respectively. Meanwhile, PDA-PEI solution was prepared by adding PDA solution with the addition PEI for each concentration. PEI concentrations were varied at 0.5, 1, 2, and 3 g/L at a PDA concentration of 3 g/L. For information, acidity control was carried out by adding 0.1N NaOH to the Trizma-HCL solution preparation with a pH of 8.5.

Next, the membrane was immersed in each variation of the PDA and PDA-PEI solutions for 6, 16, and 24 h. Immersion was carried out on a shaker at a speed of 60rpm to homogenize the PDA and PDA-PEI solutions. After the immersion was completed, the membrane was washed and rinsed using distilled water to remove the remaining PDA and PDA-PEI particles that were not tightly bounded. The membrane was then dried for 24 h. Drying is intended to remove residual water from the washing process. As a note, PVDF membrane modification was conducted by immersing the membrane inside PDA-PEI solution. Hence, the possibility of PDA-PEI coverage of both sides of PVDF membrane was clearly possible. In addition, the membranes were applied to treat oily wastewater where high degree of hydrophilicity of membrane is

required and the increase of hydrophilicity on both sides of the membranes actually help to improve the flux and rejection of the membranes.

Functional groups on the membrane were characterized using Fourier Transform Infrared (FTIR) [Shimadzu, IRTracer-100] at a wavelength range of 500–4500  $\text{cm}^{-1}$ . The morphological structure of the membrane surface was characterized using Scanning Electron Microscopy (SEM) [Zeiss, EVO MA10]. The hydrophilicity of the membrane was analyzed using contact angle [DataPhysics Instruments, OCA25]. The membrane modification procedure can be seen in Fig 1a.

### 2.3. Filtration performance using dead-end modules

The membrane filtration performance was tested using an oil-in-water emulsion (simulated oily wastewater) sample with a concentration of 5000ppm. Samples were prepared by dissolving 0.5g of palm oil in 100mL of water and adding 0.5% Tween 20 as an emulsifier. Homogenization (IKA, T25 digital ULTRA-TURRAX®) was carried out at room temperature  $\pm 20^\circ\text{C}$  for 5 min (15,000rpm). OWW droplets under a microscope (Olympus Microscope, CX21LED) can be observed in Fig

1f. The droplet images were taken 6 times, which can be seen in Fig S1. The average droplet diameter from various points of collection is around  $8.88 \pm 8.066 \mu\text{m}$ . In appearance, the OWW is cloudy white (left) and the permeate is clear (right) (see Fig 1f). The emulsion stability test was carried out for 60 min and it was found that the emulsion did not experience coalescence.

This dead-end configured filtration module has an active area of  $38.5 \text{ cm}^2$ . During the process, the thrust is supplied from the compressed gas pressure, which is controlled and measured every time. Before measuring the performance, each membrane was first tested using 100mL aquadest, and the water flux was measured. Data collection related to water flux was carried out for 30 min. After that, the performance test was carried out by adding 100mL of water-oil emulsion and calculating the flux every 10 min for 60 min.

Rejection measurements were carried out every 10 min by measuring the concentration of permeate. The measured concentration is compared with the initial concentration to obtain the percentage of rejection. As a marker, each performance measurement was carried out at room temperature ( $\pm 20^\circ\text{C}$ ).

Water flux was measured and calculated by the following equation:

$$J_w = \frac{V_w}{A \cdot t \cdot P}$$

where  $V_w$ ,  $t$ ,  $A$ ,  $P$  are volume permeate (L), time (h), active membrane area ( $\text{m}^2$ ), and pressure (bar), respectively. Meanwhile, the rejection measurement and calculation followed the following equation:

$$R = \left(1 - \frac{C_p}{C_f}\right) \times 100\%$$

where,  $C_p$  and  $C_f$  are the permeate concentration (ppm) and the initial feed concentration (ppm), respectively. The procedure for testing the performance of the membrane, and the mechanism for separating the OWW, are shown in Fig 1b and Fig. 1c, respectively.

### 3. Results and discussion

#### 3.1. Membrane characterization with fourier transform infrared (FTIR)

Characterization related to the chemical composition on the surface of the PVDF membrane was carried out using FTIR. In brief, several functional groups that mark the presence of PDA-PEI, including N—H, C—O, C—N, and O—H. These functional groups tend to be hydrophilic, in which case the H atoms form better hydrogen bonds with water. Thus, water passes through the membrane more easily than oil. Based on the literature, the success of membrane modification using PDA is most evident with -OH and -NH bonds. This bond indicates the attachment of the amine group specifically to the membrane substrate (Li et al., 2022).

The results of the characterization in Fig. 2 indicate a change in chemical composition after the PDA coating process. The formation of N—H/O—H bonds gives a stretching vibration response in the absorption wavelength range of  $3000$  to  $3600 \text{ cm}^{-1}$ . The presence of these bonds forms stretching vibrations on the C=C aromatic ring and gives a detectable response at  $1500$  to  $1650 \text{ cm}^{-1}$ . However, the existence of this bond is quite difficult to observe in this research. This occurs because the peak formed by the bending-shearing N—H vibration at  $1600 \text{ cm}^{-1}$  coincides with the peak caused by the C=C bond. Additional evidence for the success of the coating is indicated in the characterization results showing the presence of O—H, C—N and C—O groups found at  $1170$ ,  $1275$ , and  $1401 \text{ cm}^{-1}$ , respectively.

The addition of PEI in the PVDF membrane coating process using PDA is expected to provide changes in surface properties indicated in the FTIR characterization.

The FTIR response from the addition of PEI showed that the C=N bond that should have formed in the  $1560 \text{ cm}^{-1}$  range was not visible. However, another response from the addition of PEI was observed that the FTIR response to N—H and O—H bonds tended to be weak. This indicates that the formation of agglomerates on the membrane surface also decreased. In other words, the addition of PEI was successful in preventing the formation of agglomerates.

#### 3.2. Membrane surface morphology using scanning electron microscopy (SEM)

The surface morphology of the membrane using SEM indicated changes due to PDA and PDA-PEI coating. As observed in Fig. 3(a–h), the surface of the pure membrane is smooth and uniform. PDA and PDA-PEI coating showed changes in the characteristics of the membrane from being smooth to rough and not uniform. The membrane roughness increased with the increase in the amount of PDA agglomerate deposition. Observations on PDA-modified PVDF membranes showed that the coating time affected the roughness of the membrane, this was also observed on PDA-PEI hybrid membranes. The interaction of non-covalent bonds results in an increase in the number of aggregates during deposition, which is accompanied by a rougher surface morphology of the membrane. The amount of aggregate covering the pores on the membrane surface that is affected by the amount of PDA on the surface can be observed in the modified PVDF membrane morphology with  $0.5 \text{ g/L}$  compared to  $3 \text{ g/L}$ .

On the other hand, the addition of PEI made the membrane smoother due to the destruction of non-covalent bonds in the PDA aggregates. The impact of the addition of PEI was observed on the PDA-PEI hybrid membrane, both at  $0.5 \text{ g/L}$  and  $3 \text{ g/L}$  PDA. The addition of  $2 \text{ g/L}$  PEI stabilized the polymerization process, and the agglomerates on the membrane surface were minimized. PEI concentration also affects the

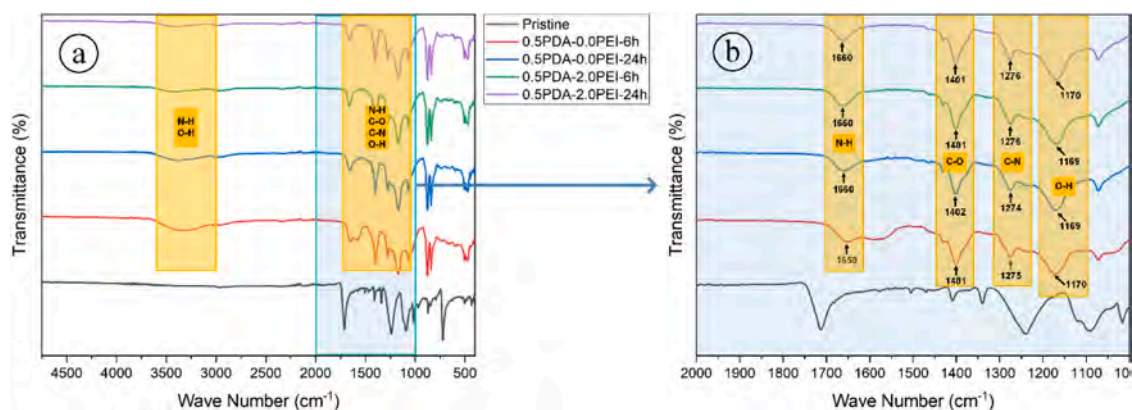


Fig. 2. FTIR spectra of PVDF membrane: Pristine and PDA – PEI hybrid modified. (a) Wave Number  $500 - 4500 \text{ cm}^{-1}$ , (b) Magnification for wave number  $1000 - 2000 \text{ cm}^{-1}$ .

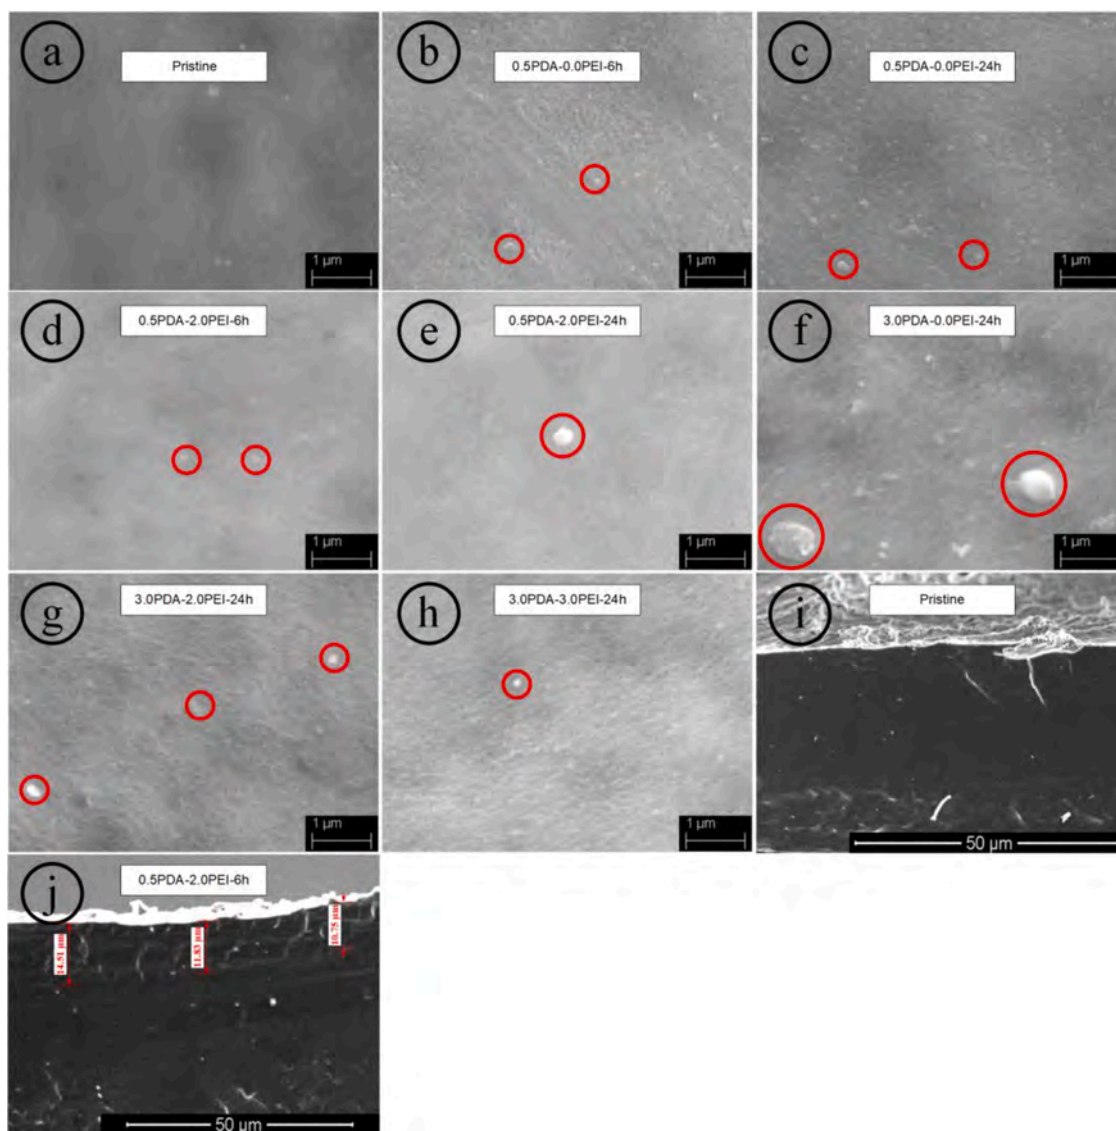


Fig. 3. Morphology of various membranes using SEM; a – h (20,000x magnification): surface, i – j (1,200x magnification): cross section.

polymerization process, this can be observed in PDA-PEI hybrid membranes with 2 g/l and 3 g/L PEI. It shows that with the addition of PEI the membrane is smoother. This proves that the greater the PEI concentration, the smoother the membrane surface because the destruction of non-covalent bonds in PDA aggregates is a lot. Research conducted by Wang et al. and Lv et al. both found that the addition of PEI played a role in stabilizing PDA polymerization. The indication appears on the surface of the membrane as a result of their SEM characterization (Lv et al., 2015; Wang et al., 2017). Apart from the membrane roughness, the coating thickness of the membrane was also measured by means of SEM. In Fig. 3(i–j) it is observed the comparison between the thickness of the membrane before and after modification with a change of around  $12.36 \pm 1.94 \mu\text{m}$ .

### 3.3. Contact angle test (CA)

The nature of the membrane surface related to the contact angle is one of the focuses and indicators of the successfulness of membrane modification. In line with this, coating using PDA-PEI resulted in a decrease in the contact angle, or in other words, the membrane tends to be more hydrophilic. The presence of PDA gives a hydrophilic shade because the functional groups are amine, imine, and catechol.

Interestingly, the presence of a PEI layer on the membrane surface contributed to the decrease in the contact angle due to the amino groups (Yang et al., 2014). The experimental data of membrane's contact angles in this study is presented in Fig 4.

Pristine PVDF membrane has a contact angle of  $88.1^\circ$ , which indicates its high hydrophobicity. The presence of functional groups obtained from PDA coating showed a decrease in contact angle, which has proved by the 0.5 g/L coatings that succeeded in reducing the contact angle to  $77.7^\circ$  with a coating time of 6 h. The decrease in contact angle with respect to coating time can also be observed when 24 h of processing has obtained a decrease to  $75.2^\circ$ . In addition, the amount of mass of the superimposed PDA also gives a finite contact angle reduction, which indicates the presence of functional groups that play an important role in changing the surface properties of the membrane. The results showed that coating using 3 g/L succeeded in reducing the contact angle up to  $64.9^\circ$  for 6 h of coating time, while for 24 h of coating it decreased to  $62.6^\circ$ . These results indicate the amount of PDA mass for coating is more dominant than the coating time.

The presence of PEI as a stabilizer of PDA polymerization has an effect due to the presence of functional groups, in addition to reducing the possibility of agglomeration formation. It appears that the addition of 2 g/L PEI to a fix of 0.5 g/L PDA resulted in a decrease in the contact

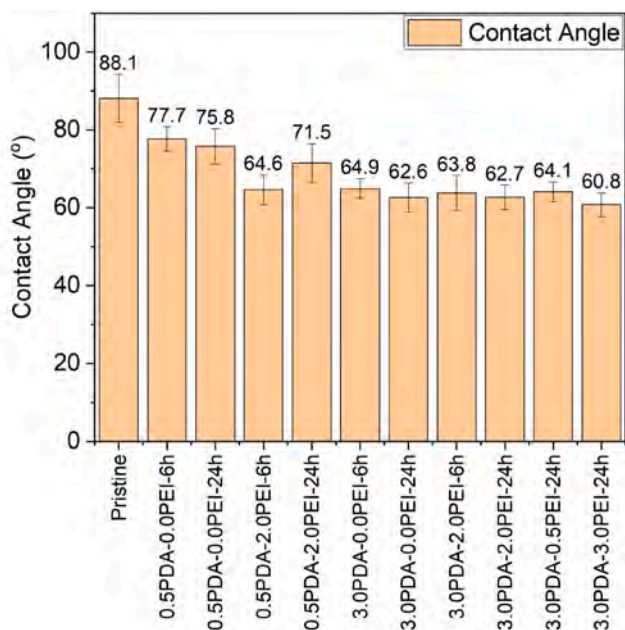


Fig. 4. Contact Angle on Modified PDA, PDA-PEI, and Pristine PVDF Membranes.

angle to 71.5°, which was originally 75.8° for a 24-hour immersion time. However, this trend of adding PEI as a stabilizer needs to be reviewed at different PDA concentrations, the addition of various PEIs to the 3g PDA fixation did not give similar results. At first, the immersion with 3 g/L of PDA without adding PEI was originally 62.6°, and the addition of 2 g/L of PEI actually increased to 62.7°. Also, the addition of 0.5 g/L PEI actually resulted in a small increase in membrane’s contact angle. As a reason, the rate of polymerization that occurs at a fairly high PDA concentration cannot be fully controlled by the addition of PEI. In particular, this phenomenon is supported by variations in PEI at a concentration of 3g/l PDA.

The best decrease in contact angle at the fixation concentration of PDA 3 g/L was observed in the combination of PEI 3 g/L with a contact angle of 60.8°. The exposure indicates that combined PDA-PEI concentrations should be considered to provide the intended results. This refers to the consideration of PEI’s ability as a stabilizer which is expected to control the polymerization rate and inhibit the emergence of agglomeration.

### 3.4. Dead-end system membrane performance test

Various criteria related to membrane performance are also indicators of the success of modified membranes. In this study, the membrane performance was evaluated through the value of flux and rejection. Often, these two things contradict each other and are inseparable due to various factors. As previously discussed, surface properties such as hydrophobicity and size play an important role in the resulting performance. Meanwhile, membrane modification is expected not to affect these properties but to prevent membrane fouling. Observations on various membrane coating times using 0.5 g/L PDA have been carried out. The results prove that the formation of a PDA layer on the surface of the membrane is able to prevent fouling, this can be observed in Fig 5a. In general, the longer coating time results in the formation of agglomerates. The presence of this aggregate actually results in the formation of blocking on the membrane which results in a lower flux initially, but on the other hand, the flux stability is more guaranteed. When related to the rejection value, the presence of PDA on the membrane surface increases the achievable rejection. The rejection is found in Fig 5b, a pristine membrane, which initially had 86% rejection, increased with an achievement range of 96–98%. This finding provides valuable information which states that the addition of 0.5 g/L PDA resulted in better membrane’s performance compared to membrane without PDA addition.

Apart from rejection, the permeate flux also indicates an increase in the stability of the OWW separation (see Fig. 5a). In the membrane without PDA modification, it was shown that the flux tended to decrease suddenly at sometime early in the filtration process and tended to be stable at some time afterward. Different things were shown due to the addition of PDA, in which the flux decreased gradually. This phenomenon indicates the presence of PDA helps membrane stability against fouling due to oily water. Meanwhile, the decrease in rejection and flux with increasing polymerization time is indicated by the ongoing polymerization and the tendency to form aggregates in the process.

Observations on the effect of PDA concentration need to be carried out to measure its effect on the initial coating. A coating time of 24 h was chosen, in which the most agglomerates were formed on the membrane surface compared to 6 and 16 h. As shown in Fig 6a, the flux tends to be stable at increasing PDA concentration. This indicates that the presence of PDA is beneficial for flux stability. However, this finding was not supported by the rejection trends which in fact decreased with the presence of more PDA at the beginning of the coating as shown in Fig 6b. Apart from that, the indication of excessive PDA concentration encourages polymerization that is too fast, and the growth of aggregates

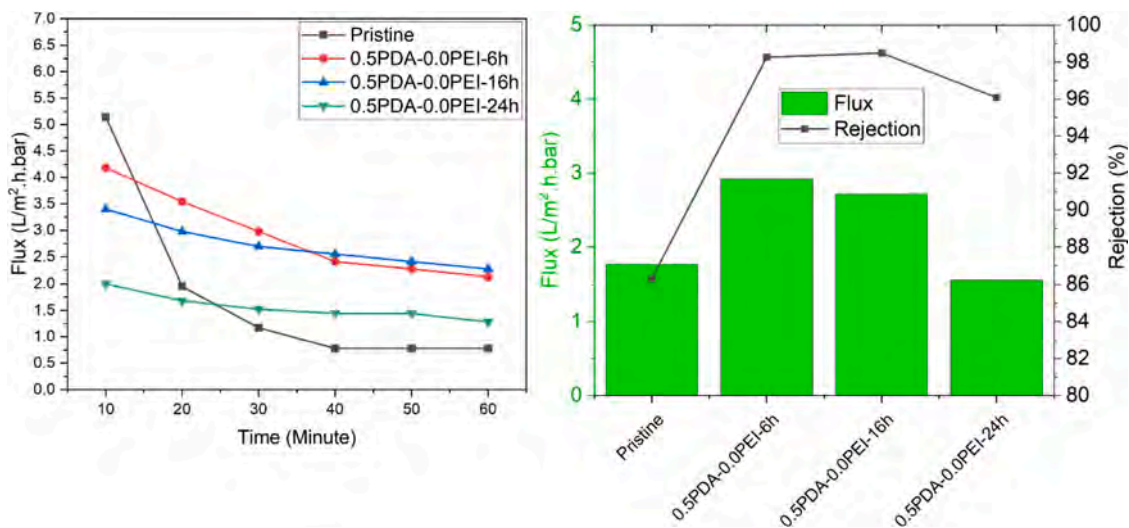


Fig. 5. PDA-modified PVDF membrane water flux (a) and rejection capability (b) at various coating times.

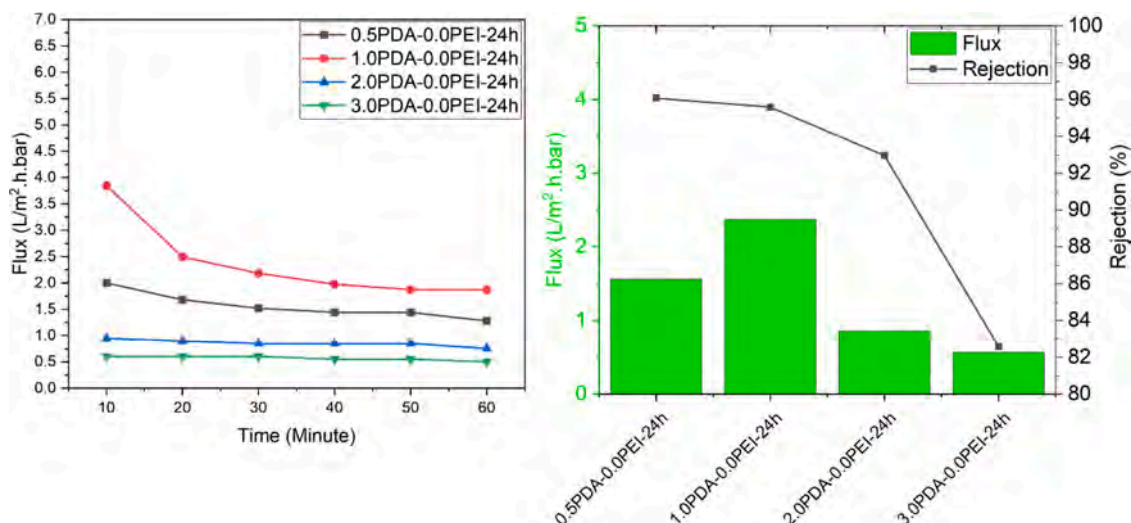


Fig. 6. PDA-modified PVDF membrane water flux (a) and rejection capability (b) at various PDA concentrations when coating time fixed at 24 h.

becomes unavoidable.

Consideration of adding polymerization stabilizer becomes an attractive option. In this research, PEI was added to prevent the formation of agglomerates in PDA polymerization. The SEM images on Fig. 3f-h with various PEI concentrations indicated the decrease in PDA aggregate formation. This decrease in aggregate formation should alter the membrane performance during separation. From Fig. 7a and b the addition of PEI could increase the initial flux and also oil rejection capacities of the membranes. The formation of PDA aggregates should be avoided because aggregates might plug the support's pores and also alter the rejection efficiency of the membrane (Lv et al., 2018). It was previously mentioned that a concentration of 1 g/L PDA gives the best condition in terms of flux and rejection. Thus, the effect of coating time on certain PDA-PEI concentrations was carried out first. In this observation using 2 g/L PEI, the attached flux shows that increasing coating time does not always result in a decrease in flux. This indicates that the existing PDA-PEI interaction has already experienced saturation at 16 and 24 h. Rejection as another review showed the same thing, the addition of time did not increase the rejection. The two performance parameters are presented in Fig 7a and 7b. In addition, the role of PEI as a stabilizer is also insignificant at a concentration of 1 g/L PDA. This is indicated by the more controlled polymerization of dopamine compared to high concentrations. Moreover, the excess PEI will form aggregates,

which are highly water soluble and free to move.

The results of the comparison related to the coating time of PDA-PEI show that the trend towards the stability of the fusion has been achieved. However, further investigation of the ability of PEI as a stabilizer for various concentrations of PDA still needs to be conducted. Reflecting on the previous values, the variation starts from 0.5 g/L PDA and ends with 3 g/L PDA. As shown in Fig 8a, 0.5 g/L PDA gave the best initial flux, but up to 60min, the filtration time trended downward. On the other hand, at 1 and 2 g/L PDA, the flux was initially lower, but at 60 min the filtration seemed to have stabilized. Nonetheless, 0.5 g/L PDA remains a leading candidate in this process. This is inseparable from the trend that allows achieving stability in the near future. Rejection was achieved up to 98% with the lowest value for 3 g/L PDA. It is possible that the PDA concentration is too high and it binds to PEI more dominantly before it sticks to the surface of the membrane which results in a less than optimal coating process.

#### 4. Conclusion

In summary, it is shown that the addition of PDA-PEI as a PVDF membrane modifying agent has a measurable physical effect. Among them, the surface properties in the form of hydrophilicity which has increased markedly by a decreased contact angle (88.1° to 64.6° for 0.5

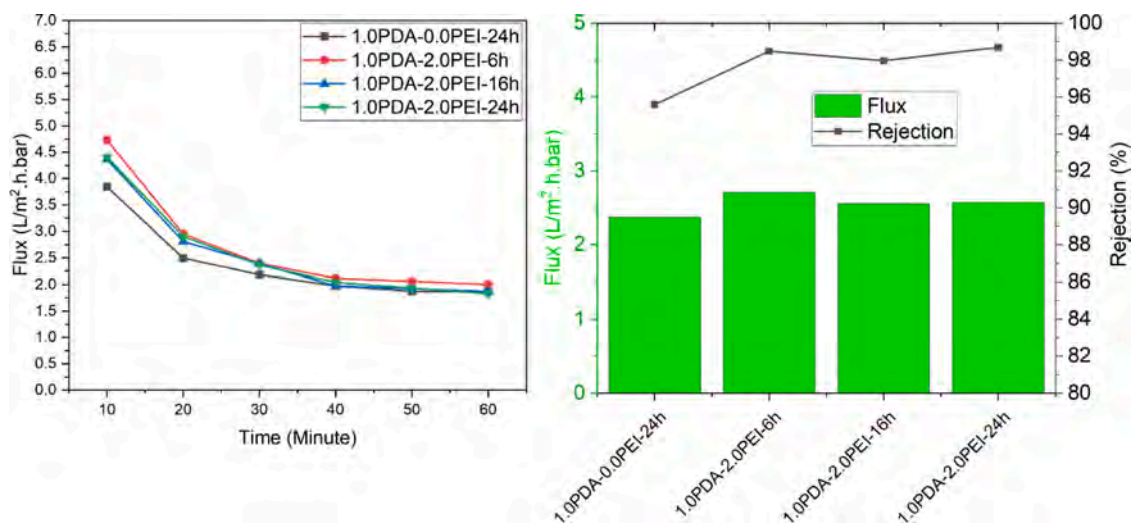


Fig. 7. PDA-PEI modified PVDF membrane water flux (a) and rejection capability (b) at various PEI concentrations when concentration PDA constant at 1 g/L.

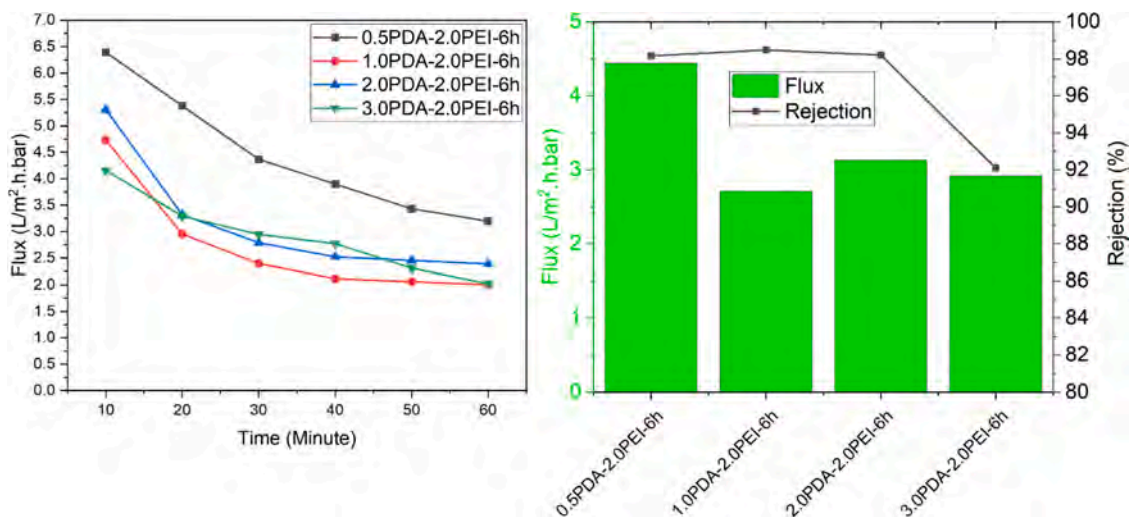


Fig. 8. PDA-PEI modified PVDF membrane water flux (a) and rejection capability (b) at various PDA concentration when concentration PEI constant at 2 mol.

g/L PDA - 2 g/L PEI for 6 h copolymerization), and membrane roughness which also increased was observed through SEM. FTIR supports the fact that PDA-PEI has successfully coated the surface of PVDF membranes. Meanwhile, the measured filtration performance in flux stability and rejection showed satisfactory results. In general, the modification of the membrane is capable of rejecting more than 90% of the OWW, with increased stability against fouling. Based on various reviews, it is concluded that 0.5 g/L PDA - 2 g/L PEI for 6 h is the best blend with an average flux around  $\pm 4.4 \text{ L} \cdot \text{m}^{-2} \cdot \text{h}^{-1} \cdot \text{bar}^{-1}$  and 98% rejection.

#### CRediT authorship contribution statement

**Putu Doddy Sutrisna:** Conceptualization, Methodology, Resources, Supervision, Writing – review & editing, Project administration, Funding acquisition. **Pra Cipta Buana W. Mustika:** Writing – original draft, Software, Formal analysis. **Ronaldo Pangestu Hadi:** Writing – review & editing, Formal analysis. **Investigation, Formal analysis, Writing – review & editing.** **Yosia Elenio Gani:** Investigation, Formal analysis, Writing – review & editing.

#### Declaration of Competing Interest

The authors declare that they have no known competing financial interests or personal relationships that could have appeared to influence the work reported in this paper.

#### Acknowledgements

The authors gratefully acknowledge the financial support from The Ministry of Education, Culture, Research, Technology and Higher Education of Indonesia under The University's Research Excellence Fundamental Research Grant under contract No. 069/SP-Lit/LPPM- 01/KemendikbudRistek/Multi/FT/III/2022.

#### Supplementary materials

Supplementary material associated with this article can be found, in the online version, at doi:10.1016/j.sajce.2023.01.006.


#### References

Ahmad, T., Guria, C., Mandal, A., 2020. A review of oily wastewater treatment using ultrafiltration membrane: a parametric study to enhance the membrane performance. *J. Water Process Eng.* 36, 101289 <https://doi.org/10.1016/j.jwpe.2020.101289>.

- Almaie, S., Vatanpour, V., Rasoulifard, M.H., Seyed Dorraji, M.S., 2022. Novel negatively-charged amphiphilic copolymers of PVDF-g-PAMPS and PVDF-g-PAA to improve permeability and fouling resistance of PVDF UF membrane. *React. Funct. Polym.* 179, 105386 <https://doi.org/10.1016/j.reactfunctpolym.2022.105386>.
- Baig, N., Alowaid, A.M., Abdulazeez, I., Salhi, B., Sajid, M., Kammakakam, I., 2022. Designing of nanotextured inorganic-organic hybrid PVDF membrane for efficient separation of the oil-in-water emulsions. *Chemosphere* 308, 136531. <https://doi.org/10.1016/j.chemosphere.2022.136531>.
- Bolto, B., Zhang, J., Wu, X., Xie, Z., 2020. A review on current development of membranes for oil removal from wastewaters. *Membranes (Basel)* 10, 1–18. <https://doi.org/10.3390/membranes10040065>.
- Ding, J., Wu, H., Wu, P., 2020. Preparation of highly permeable loose nanofiltration membranes using sulfonated polyethylenimine for effective dye/salt fractionation. *Chem. Eng. J.* 396, 125199 <https://doi.org/10.1016/j.cej.2020.125199>.
- Fan, T., Su, Y., Fan, Q., Li, Z., Cui, W., Yu, M., Ning, X., Ramakrishna, S., Long, Y., 2021. Robust Graphene@PPS fibrous membrane for harsh environmental oil/water separation and all-weather cleanup of crude oil spill by joule heat and photothermal effect. *ACS Appl. Mater. Interfaces* 13, 19377–19386. <https://doi.org/10.1021/acsmi.1c04066>.
- Hai, A., Durrani, A.A., Selvaraj, M., Banat, F., Haija, M.A., 2019. Oil-water emulsion separation using intrinsically superoleophilic and superhydrophobic PVDF membrane. *Sep. Purif. Technol.* 212, 388–395. <https://doi.org/10.1016/j.seppur.2018.10.001>.
- Hu, Y., Yue, M., Yuan, F., Yang, L., Chen, C., Sun, D., 2021. Bio-inspired fabrication of highly permeable and anti-fouling ultrafiltration membranes based on bacterial cellulose for efficient removal of soluble dyes and insoluble oils. *J. Memb. Sci.* 621, 118982 <https://doi.org/10.1016/j.memsci.2020.118982>.
- Jiang, Y., Xian, C., Xu, X., Zheng, W., Zhu, T., Cai, W., Huang, J., Lai, Y., 2022. Robust PAAm-TA hydrogel coated PVDF membranes with excellent crude-oil antifouling ability for sustainable emulsion separation. *J. Memb. Sci.* 667, 121166 <https://doi.org/10.1016/j.memsci.2022.121166>.
- Li, C., Yang, Q., Chen, D., Zhu, H., Chen, J., 2022. polydopamine coating with enhanced stability and. *RSC Adv.* 12, 35051–35063. <https://doi.org/10.1039/d2ra05130c>.
- Li, J.H., Ni, X.X., Zhang, D.Bin, Zheng, H., Wang, J.Bin, Zhang, Q.Q., 2018. Engineering a self-driven PVDF/PDA hybrid membranes based on membrane micro-reactor effect to achieve super-hydrophilicity, excellent antifouling properties and hemocompatibility. *Appl. Surf. Sci.* 444, 672–690. <https://doi.org/10.1016/j.apsusc.2018.03.034>.
- Li, M., Wu, L., Zhang, C., Chen, W., Liu, C., 2019. Hydrophilic and antifouling modification of PVDF membranes by one-step assembly of tannic acid and polyvinylpyrrolidone. *Appl. Surf. Sci.* 483, 967–978. <https://doi.org/10.1016/j.apsusc.2019.04.057>.
- Liu, L., Chen, H., Yang, F., 2014. Enhancing membrane performance by blending ATRP grafted PMMA-TiO<sub>2</sub> or PMMA-PSBMA-TiO<sub>2</sub> in PVDF. *Sep. Purif. Technol.* 133, 22–31. <https://doi.org/10.1016/j.seppur.2014.06.015>.
- Lv, Y., Yang, H.C., Liang, H.Q., Wan, L.S., Xu, Z.K., 2015. Nanofiltration membranes via co-deposition of polydopamine/polyethylenimine followed by cross-linking. *J. Memb. Sci.* 476, 50–58. <https://doi.org/10.1016/j.memsci.2014.11.024>.
- Lv, Y., Yang, S.J., Du, Y., Yang, H.C., Xu, Z.K., 2018. Co-deposition kinetics of polydopamine/polyethyleneimine coatings: effects of solution composition and substrate surface. *Langmuir* 34, 13123–13131. <https://doi.org/10.1021/acs.langmuir.8b02454>.
- Mansha, M., Salhi, B., Ali, S., Khan, S.A., Baig, N., 2022. Novel procaine-based gemini zwitterion incorporated PVDF membranes for efficient treatment of oily wastewater. *J. Environ. Chem. Eng.* 10, 107935 <https://doi.org/10.1016/j.jece.2022.107935>.
- McCloskey, B.D., Park, H.B., Ju, H., Rowe, B.W., Miller, D.J., Chun, B.J., Kin, K., Freeman, B.D., 2010. Influence of polydopamine deposition conditions on pure water flux and foulant adhesion resistance of reverse osmosis, ultrafiltration, and



- microfiltration membranes. *Polymer* (Guildf) 51, 3472–3485. <https://doi.org/10.1016/j.polymer.2010.05.008>.
- Padaki, M., Surya Murali, R., Abdullah, M.S., Misdan, N., Moslehyani, A., Kassim, M.A., Hilal, N., Ismail, A.F., 2015. Membrane technology enhancement in oil-water separation. A review. *Desalination* 357, 197–207. <https://doi.org/10.1016/j.desal.2014.11.023>.
- Qiu, W.Z., Yang, H.C., Xu, Z.K., 2018. Dopamine-assisted co-deposition: an emerging and promising strategy for surface modification. *Adv. Colloid Interface Sci.* 256, 111–125. <https://doi.org/10.1016/j.cis.2018.04.011>.
- Subasi, Y., Cicek, B., 2017. Recent advances in hydrophilic modification of PVDF ultrafiltration membranes – a review: part I. *Membr. Technol.* 2017, 7–12. [https://doi.org/10.1016/S0958-2118\(17\)30191-X](https://doi.org/10.1016/S0958-2118(17)30191-X).
- Sun, C., Feng, X., 2017. Enhancing the performance of PVDF membranes by hydrophilic surface modification via amine treatment. *Sep. Purif. Technol.* 185, 94–102. <https://doi.org/10.1016/j.seppur.2017.05.022>.
- Sun, Y., Zong, Y., Yang, N., Zhang, N., Jiang, B., Zhang, L., Xiao, X., 2020. Surface hydrophilic modification of PVDF membranes based on tannin and zwitterionic substance towards effective oil-in-water emulsion separation. *Sep. Purif. Technol.* 234, 116015 <https://doi.org/10.1016/j.seppur.2019.116015>.
- Tang, Y.P., Cai, T., Loh, D., O'Brien, G.S., Chung, T.S., 2017. Construction of antifouling lumen surface on a poly(vinylidene fluoride) hollow fiber membrane via a zwitterionic graft copolymerization strategy. *Sep. Purif. Technol.* 176, 294–305. <https://doi.org/10.1016/j.seppur.2016.12.012>.
- Tanudjaja, H.J., Hejase, C.A., Tarabara, V.V., Fane, A.G., Chew, J.W., 2019. Membrane-based separation for oily wastewater: a practical perspective. *Water Res.* 156, 347–365. <https://doi.org/10.1016/j.watres.2019.03.021>.
- Tawalbeh, M., Al Mojily, A., Al-Othman, A., Hilal, N., 2018. Membrane separation as a pre-treatment process for oily saline water. *Desalination* 447, 182–202. <https://doi.org/10.1016/j.desal.2018.07.029>.
- Valizadeh, K., Heydarinasab, A., Hosseini, S.S., Bazgir, S., 2022. Fabrication of modified PVDF membrane in the presence of PVI polymer and evaluation of its performance in the filtration process. *J. Ind. Eng. Chem.* 106, 411–428. <https://doi.org/10.1016/j.jiec.2021.11.016>.
- Valizadeh, K., Heydarinasab, A., Hosseini, S.S., Bazgir, S., 2021. Preparation of modified membrane of polyvinylidene fluoride (PVDF) and evaluation of anti-fouling features and high capability in water/oil emulsion separation. *J. Taiwan Inst. Chem. Eng.* 126, 36–49. <https://doi.org/10.1016/j.jtice.2021.07.018>.
- Wang, J., Zhu, J., Tsehay, M.T., Li, J., Dong, G., Yuan, S., Li, X., Zhang, Y., Liu, J., Van Der Bruggen, B., 2017. High flux electroneutral loose nanofiltration membranes based on rapid deposition of polydopamine/polyethyleneimine. *J. Mater. Chem. A* 5, 14847–14857. <https://doi.org/10.1039/c7ta02661g>.
- Wardani, A.K., Ariono, D., Subagjo, Wenten, I.G., 2019. Hydrophilic modification of polypropylene ultrafiltration membrane by air-assisted polydopamine coating. *Polym. Adv. Technol.* 30, 1148–1155. <https://doi.org/10.1002/pat.4549>.
- Yang, Y., Jiang, X., Goh, K., Wang, K., 2021. The separation of oily water using low-cost natural materials: review and development. *Chemosphere* 285, 131398. <https://doi.org/10.1016/j.chemosphere.2021.131398>.
- Yue, X., Li, Z., Zhang, T., Yang, D., Qiu, F., 2019. Design and fabrication of superwetting fiber-based membranes for oil/water separation applications. *Chem. Eng. J.* 364, 292–309. <https://doi.org/10.1016/j.cej.2019.01.149>.
- Yue, X., Zhang, T., Yang, D., Qiu, F., Li, Z., Zhu, Y., Yu, H., 2018. Oil removal from oily water by a low-cost and durable flexible membrane made of layered double hydroxide nanosheet on cellulose support. *J. Clean. Prod.* 180, 307–315. <https://doi.org/10.1016/j.jclepro.2018.01.160>.
- Zhang, S., Wu, L., Deng, F., Zhao, D., Zhang, Chao, Zhang, Chaocan, 2016. Hydrophilic modification of PVDF porous membrane: via a simple dip-coating method in plant tannin solution. *RSC Adv.* 6, 71287–71294. <https://doi.org/10.1039/c6ra13634f>.
- Zhao, C., Xu, X., Chen, J., Yang, F., 2013. Effect of graphene oxide concentration on the morphologies and antifouling properties of PVDF ultrafiltration membranes. *J. Environ. Chem. Eng.* 1, 349–354. <https://doi.org/10.1016/j.jece.2013.05.014>.
- Zhao, C., Zuo, F., Liao, Z., Qin, Z., Du, S., Zhao, Z., 2015. Mussel-inspired one-pot synthesis of a fluorescent and water-soluble polydopamine-polyethyleneimine copolymer. *Macromol. Rapid Commun.* 36, 909–915. <https://doi.org/10.1002/marc.201500021>.
- Zulfiqar, U., Thomas, A.G., Yearsley, K., Bolton, L.W., Matthews, A., Lewis, D.J., 2019. Renewable adsorbent for the separation of surfactant-stabilized oil in water emulsions based on nanostructured sawdust. *ACS Sustain. Chem. Eng.* 7, 18935–18942. <https://doi.org/10.1021/acssuschemeng.9b04294>.

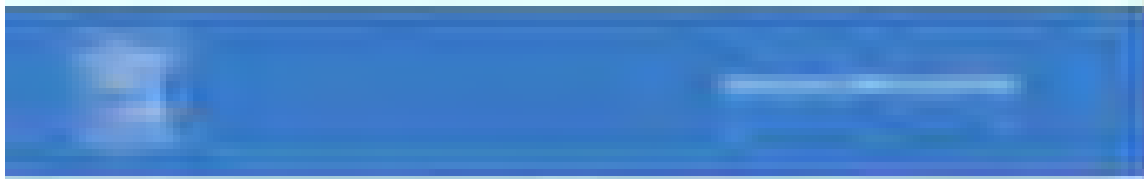

# South African Journal of Chemical Engineering

ISSN 1875-3752 (print) / ISSN 1875-3760 (online)



**SAChE**  
SOCIETY OF  
CHEMICAL ENGINEERS



ScienceDirect

## South African Journal of Chemical Engineering

Open access

6.8

CiteScore

Submit your article

Guide for authors

Menu

Search in this journal

- > Aims and scope
- > **Editorial board**
- > Abstracting & indexing

### Editorial board by country/region

22 editors and editorial board members in 8 countries/regions

1 South Africa (10)

2 India (3)

3 United Kingdom (3)

> [See more editors by country/region](#)

### Editorial board

#### Editor-in-Chief



Professor Milan Carsky, PhD

University of KwaZulu-Natal, Durban, South Africa

Fluidization, Combustion, Liquid-liquid extraction, Neural networks

Deputy Editor-in-Chief

FEEDBACK



Professor Thokozani Majazi, PrEng, PhD

University of the Witwatersrand Johannesburg School of Chemical and Metallurgical Engineering, Johannesburg, South Africa

Process Optimization, Water Minimization, Energy Optimization, Process Systems Engineering, Batch Processes

[View full biography](#)

## Editors



Professor Mohamed Abdel Salam, PhD

King Abdulaziz University, College of Science, Chemistry Department, Jeddah, Saudi Arabia

Chemistry, Nanomaterials, Environmental Chemistry, Electrochemistry, Catalysis

[View full biography](#)



Professor Kathleen Bernardo Aviso, PhD

De La Salle University, Department of Chemical Engineering, Manila, Philippines

Decision support tools for environmental processes, Mathematical modelling using fuzzy logic approach, Environmental Engineering and Management, Low-carbon energy technologies. Green technologies

[View full biography](#)



Professor Santanu Bandyopadhyay, PhD

Indian Institute of Technology Bombay, Department of Energy Science and Engineering, Mumbai, India

Pinch Analysis, Energy System Optimization, Renewable Energy Systems

[View full biography](#)



Dr. Valeria Di Sarli, PhD

National Research Council Institute of Science and Technology for Sustainable Energy and Mobility, Napoli, Italy

Combustion, Turbulence, Flame Propagation, Flammability, Explosions, Process Safety, Chemical Reactor Engineering, Catalytic Micro-Combustors, Catalytic Diesel and Gasoline Particulate Filters, Innovative Fuels, Hydrogen, Syngas, Oxy-combustion, Computational Fluid

FEEDBACK

Eddy Simulation



Dr. Ali Eftekhari, PhD

Belfast Royal Academy, Belfast, United Kingdom

Electrochemistry, Nanotechnology, Nanoscience, Spectroscopic Techniques for Nanotechnology



Professor Raymond Everson, PhD

North-West University, Potchefstroom, South Africa

Circulating fluidized bed modeling, Carbon dioxide capture and utilization, Hydrogen processing, Microchannel reactor applications, Coal technology, Fisher-Tropsch reaction



Professor Dominic Foo, PhD

University of Nottingham Malaysia, Semenyih, Malaysia

Process integration, Process design, Process optimisation, Waste minimisation, CO2 reduction, Batch process modelling and optimisation

[View full biography](#)



Dr. Adeniyi Jide Isafiade, PhD

University of Cape Town, Department of Chemical Engineering, Cape Town, South Africa

Energy and Resource Network Synthesis and Optimisation, Process Safety



Professor David Lokhat, PhD

University of KwaZulu-Natal School of Engineering, Durban, South Africa

Chemical Reaction Engineering, Process Intensification, Advanced Materials

[View full biography](#)



FEEDBACK

Professor Adam Luckos, PhD

University of the Witwatersrand Johannesburg School of Chemical and Metallurgical Engineering, Johannesburg, South Africa

Clean coal technologies, Power generation, Fluidization, Combustion and gasification of coal, Biomass and waste materials, Fluidized-bed processes in metallurgy and minerals processing



Professor Bhim Charan Meikap, PhD

Indian Institute of Technology Kharagpur, Department of Chemical Engineering, Kharagpur, India

Air and Water Pollution Control, Fluidization, CO2 Capturing, Hazardous Waste Management, Renewable and Alternative Energy



Professor Iqbal Mujtaba, FEng FICHEM CEng PhD DIC

University of Bradford, Bradford, United Kingdom

Rigorous and CFD based Modelling, Simulation and Optimisation, Desalination, Wastewater treatment, Application of Neural Network techniques

[View full biography](#)



Professor Paul Musonge, PhD

Durban University of Technology, Durban, South Africa

Physical adsorption for the removal of heavy metals in waste water, Production of Biofuels, Applications of DOE and ANN to predictions, Optimization and design, IoT applications in process industry

[View full biography](#)

Professor Edison Muzenda, PhD

Botswana International University of Science and Technology, Palapye, Botswana

Bioenergy Engineering, Sustainable and Social Engineering, Waste Utilization, Separation processes



Dr. Brian North, PhD

Council for Scientific and Industrial Research, Pretoria, South Africa

Fluidisation, Combustion, Waste-to-energy, Green Hydrogen, Power-to-X



FEEDBACK



Dr. Jhuma Sadhukhan, PhD

University of Surrey, Department of Chemical and Process Engineering, Guildford, United Kingdom

Bioprocess, Biorefineries, Renewable energy systems, Design, Dynamic simulation, Optimisation, Sustainability analysis

[View full biography](#)



Professor Eric W. J. van Steen, PhD

University of Cape Town, Department of Chemical Engineering, Cape Town, South Africa

Catalysis, Thermodynamics, Fisher-Tropsch reaction, Kinetics



Prof. Dr. Vasudevan Subramanyan, PhD

Central Electrochemical Research Institute CSIR - Library, Karaikkudi, India

Electrochemistry, Treatment of drinking water, Electrocoagulation, Advanced electrochemical oxidation, Production and reactions of the oxygenated radicals, Electrochemical synthesis, Electrochemical ozone generation, Development of catalysts/membrane for Proton Exchange Membrane (PEM)

[View full biography](#)



Dr. Kaniki Tumba, PhD

Mangosuthu University of Technology, Department of Chemical Engineering, Durban, South Africa

Thermodynamics, Phase equilibria



Professor Roswanira A Wahab, PhD

Universiti Teknologi Malaysia, Department of Chemistry, Skudai, Malaysia

Bio-based nanomaterials, Nanocomposite, Nanomaterials, Enzyme catalysis, Enzyme technology, Bioinformatics

[View full biography](#)

## Society Contact

Professor David Lokhat, PhD

University of KwaZulu-Natal School of Engineering, Durban, South Africa

FEEDBACK

Chemical Reaction Engineering, Process Intensification, Advanced Materials

All members of the Editorial Board have identified their affiliated institutions or organizations, along with the corresponding country or geographic region. Elsevier remains neutral with regard to any jurisdictional claims.



Copyright © 2023 Elsevier B.V. or its licensors or contributors.  
ScienceDirect® is a registered trademark of Elsevier B.V.







ScienceDirect

## South African Journal of Chemical Engineering

Open access

6.8  
CiteScore[Submit your article](#)[Guide for authors](#)

Menu



Search in this journal

## Volume 44

*In progress* (April 2023)

This issue is in progress but contains articles that are final and fully citable.

[Download full issue](#)[← Previous vol/issue](#)[Next vol/issue >](#)

Receive an update when the latest issues in this journal are published

[Sign in to set up alerts](#)

## Reviews

Review article *Open access*Recent trend of metal promoter role for CO<sub>2</sub> hydrogenation to C<sub>1</sub> and C<sub>2+</sub> products

Novia Amalia Sholeha, Holilah Holilah, Hasliza Bahruji, Athirah Ayub, ... Didik Prasetyoko

Pages 14-30

[Download PDF](#) [Article preview](#) Review article *Open access*

Comprehensive review of progress made in soil electrokinetic research during 1993–2020, Part I: Process design modifications with brief summaries of main output

Ahmed Abou-Shady, Mohamed E.A. Ali, Sahar Ismail, Osama Abd-Elmottaleb, ... Ahmed El-Harairy

Pages 156-256

[Download PDF](#) [Article preview](#) Review article *Open access*

A review on polyaniline (PANI) based nanocomposites for water purification

FEEDBACK

Md. Masum Talukder, Mohammad Mizanur Rahman Khan, Md. Khairul Amin  
Pages 276-282

[Download PDF](#) Article preview 

Review article Open access

Anti-fouling electrospun organic and inorganic nanofiber membranes for wastewater treatment

Nur Ain Atiqah Mohd Amin, Mohd Akmal Mokhter, Nurulhidayah Salamun, Mohd Fuad bin Mohamad, Wan M.Asyraf Wan Mahmood  
Pages 302-317

[Download PDF](#) Article preview 

### Full Length Articles

---

Research article Open access

Comparative adsorptive performance of adsorbents developed from kaolin clay and limestone for de-fluoridation of groundwater

Adane Adugna Ayalew  
Pages 1-13

[Download PDF](#) Article preview 

Research article Open access

Formulation, optimization of a poultry feed and analysis of spectrometry, biochemical composition and energy facts

Hamza Belkhanchi, Younes Ziat, Maryama Hammi, Ousama Ifguis  
Pages 31-41

[Download PDF](#) Article preview 

Research article Open access

Improved oily wastewater rejection and flux of hydrophobic PVDF membrane after polydopamine-polyethyleneimine co-deposition and modification

Putu Doddy Sutrisna, Pra Cipta Buana W. Mustika, Ronaldo Pangestu Hadi, Caren, Yosia Elenio Gani  
Pages 42-50

[Download PDF](#) Article preview 

Research article Open access

Quebracho tannin as corrosion inhibitor in neutral media and novel rust conversion agent for enhanced corrosion protection

Victoria Vorobyova, Oleksiy Sikorsky, Margarita Skiba, Georgii Vasyliev  
Pages 68-80

[Download PDF](#) Article preview 

Research article Open access

An experimental and numerical comparison study on a heat sink thermal performance with new fin configuration under mixed convective conditions

Ali J. Obaid, Vinous M. Hameed  
Pages 81-88

[Download PDF](#) Article preview 

FEEDBACK 

Research article [Open access](#)

### Statistical analyses of pore radii on the performance of PET-nanocomposite membranes in the removal of iron and anions from Ibeshe River

Oluranti Agboola, Ajibola Ademola Khalih, Olagoke Oladokun, Augustine Omoniyi Ayeni, ... Ojo Sunday Isaac Fayomi

Pages 89-102

[Download PDF](#) [Article preview](#) 

Research article [Open access](#)

### Biodiesel production from renewable biosources ternary oil blends and its kinetic-thermodynamic parameters using Eyring Polanyi and Gibb's-Duhem equations

Adepoju T.F., Ukanwa K.S., Eyibio U.P., Etim V., ... Balogun T.A.

Pages 103-112

[Download PDF](#) [Article preview](#) 

Research article [Open access](#)

### Characterization of activated carbon from waste tea (*Camellia sinensis*) using chemical activation for removal of methylene blue and cadmium ions

Mohd Affandy Aqilah Mariah, Kobun Rovina, Joseph Merilyn Vonnice, Kana Husna Erna

Pages 113-122

[Download PDF](#) [Article preview](#) 

Research article [Open access](#)

### Investigation of some new triazole derivatives for inhibiting the acid corrosion of C1018 carbon steel: Correlation of electrochemical studies with quantum chemical calculations

N. Phadke Swathi, Seranthimata Samshuddin, Talal A. Aljohani, Kedila Rasheeda, ... Aeshah Hassan Alamri

Pages 123-134

[Download PDF](#) [Article preview](#) 

Research article [Open access](#)

### Relative magnetic field and slipping effect on Casson dusty fluid of two phase fluctuating flow over inclined parallel plate

Dolat khan, Poom Kumam, Wiyada Kumam, Panawan Suttiarporn, Ali Rehman

Pages 135-146

[Download PDF](#) [Article preview](#) 

Research article [Open access](#)

### Mild steel corrosion control through locally sourced calcium oxide on zinc phosphating process

Ayoola Ayodeji, Ajinomisanghan Eworitsemogha, Durodola Bamidele, Fayomi Ojo

Pages 147-155

[Download PDF](#) [Article preview](#) 


Research article [Open access](#)

### A green functionalized method of Cu-BTC on poly(vinyl alcohol)/chitosan composite mat and its antibacterial potential

Kamonthip Singbumrung, Kanjana Motina, Worapat Inprasit, Penwisa Pisitsak, Thitirat Inprasit

Pages 257-264

FEEDBACK 

[Download PDF](#) Article preview 

Research article Open access

### Experimental studies of the inhibitory effect of thiamazole on copper corrosion in near neutral 3% sodium chloride solution

Maryama Hammi, Charaf Lazrak, Younes Ziat, Ousama Ifiguis, Hamza Belkhanchi

Pages 265-275


[Download PDF](#) Article preview 

Research article Open access

### Multi-application of fennel (*Foeniculum vulgare*) seed composites for the adsorption and photo-degradation of methylene blue in water

Ntandokazi Mabungela, Ntaote David Shooto, Fanyana Mtunzi, Eliazer Bobby Naidoo, ... Siyasanga Mpelane

Pages 283-296

[Download PDF](#) Article preview 

Research article Open access

### MXene/PPy nanocomposite as an electrode material for high-capacity Na-ion batteries investigated from first principle calculation

Anthony Chidi Ezika, Emmanuel Rotimi Sadiku, Suprakas Sinha Ray, Yskandar Hamam, Gbolahan Joseph Adekoya

Pages 297-301


[Download PDF](#) Article preview 

Research article Open access

### Optimization of the removal efficiency of o-Toluidine: Adsorption on sugarcane bagasse or biodegradation using *Phanerochaete chrysosporium* immobilized on bagasse?

Amene Azaritorbat, Bahram Nasernejad

Pages 318-328

[Download PDF](#) Article preview 

#### Articles from Special Issue 'Chemical Engineering for Sustainable Development'

---

Research article Open access

### A reduced order model for triethylene glycol natural gas dehydration system

Daniel Jia Sheng Chong, Dominic C.Y. Foo, Zulfan Adi Putra

Pages 51-67

[Download PDF](#) Article preview 

---

[< Previous vol/issue](#)

[Next vol/issue >](#)

ISSN: 1026-9185

Copyright © 2023 Institution of Chemical Engineers (IChemE). Published by Elsevier B.V.

FEEDBACK 



Copyright © 2023 Elsevier B.V. or its licensors or contributors.



ScienceDirect® is a registered trademark of Elsevier B.V.

FEEDBACK 



## South African Journal of Chemical Engineering

COUNTRY	SUBJECT AREA AND CATEGORY	PUBLISHER	H-INDEX
<a href="#">Netherlands</a>  Universities and research institutions in Netherlands  Media Ranking in Netherlands	<a href="#">Chemical Engineering</a> <a href="#">Catalysis</a> <a href="#">Filtration and Separation</a> <a href="#">Fluid Flow and Transfer Processes</a> <a href="#">Process Chemistry and Technology</a>  <a href="#">Energy</a> <a href="#">Energy (miscellaneous)</a>  <a href="#">Social Sciences</a> <a href="#">Education</a>	<a href="#">Elsevier BV</a>	<b>22</b>
PUBLICATION TYPE	ISSN	COVERAGE	INFORMATION
Journals	10269185	2016-2021	<a href="#">Homepage</a> <a href="#">How to publish in this journal</a>

### SCOPE

The journal has a particular interest in publishing papers on the unique issues facing chemical engineering taking place in countries that are rich in resources but face specific technical and societal challenges, which require detailed knowledge of local conditions to address. Core topic areas are: Environmental process engineering • treatment and handling of waste and pollutants • the abatement of pollution, environmental process control • cleaner technologies • waste minimization • environmental chemical engineering • water treatment Reaction Engineering • modelling and simulation of reactors • transport phenomena within reacting systems • fluidization technology • reactor design Separation technologies • classic separations • novel separations Process and materials synthesis • novel synthesis of materials or processes, including but not limited to nanotechnology, ceramics, etc. Metallurgical process engineering and coal technology • novel developments related to the minerals beneficiation industry • coal technology Chemical engineering education • guides to good practice • novel approaches to learning • education beyond university.

Join the conversation about this journal




Quartiles

### FIND SIMILAR JOURNALS

options

1 <b>Indian Journal of Chemical Technology</b> IND  <b>58%</b> similarity	2 <b>Chemical Engineering Communications</b> GBR  <b>55%</b> similarity	3 <b>Xiandai Huagong/Modern Chemical Industry</b> CHN  <b>54%</b> similarity	4 <b>International Journal of Chemical Engineering</b> USA  <b>54%</b> similarity	5 <b>Journal of the Taiwan Institute of Chemical</b> TWN  <b>52%</b> similarity
--	--	---	--	--

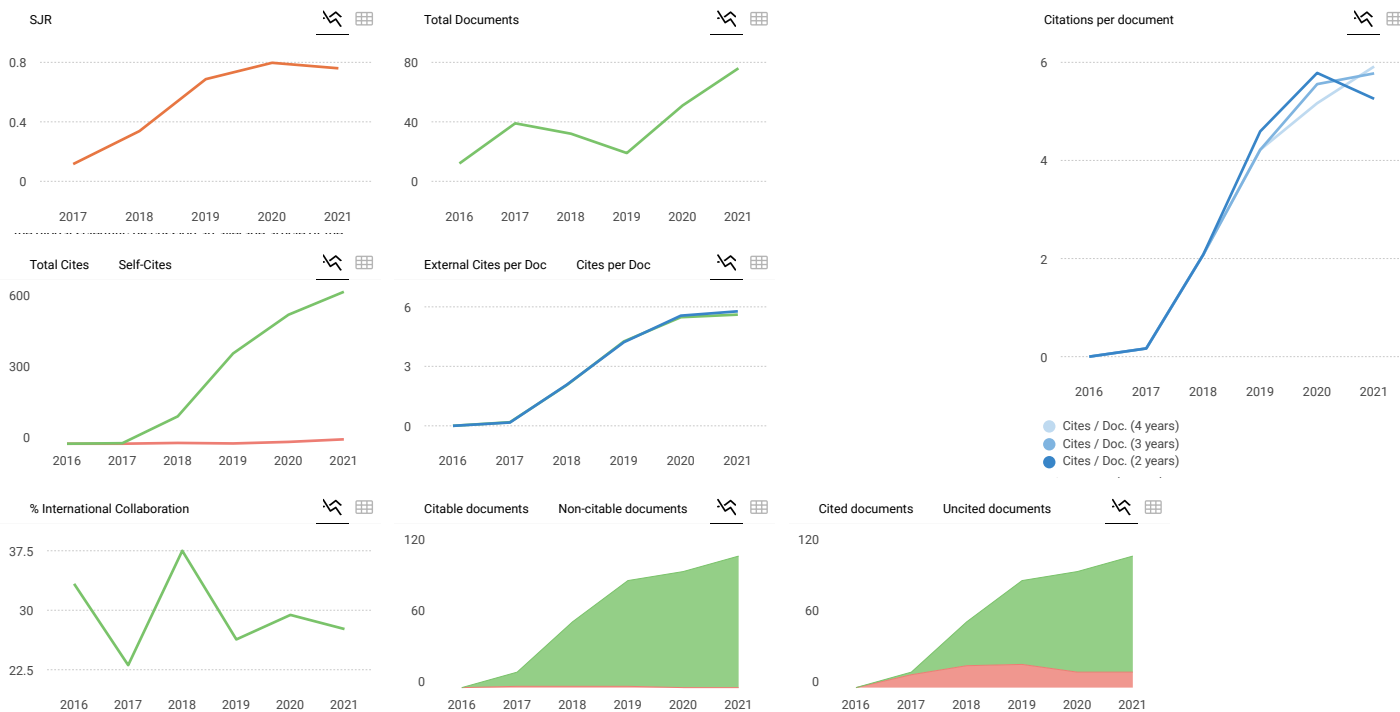

South African Journal of Chemical Engineering

Q1 Education

Best quartile

SJR 2021 0.76

powered by scimagojr.com

← Show this widget in your own website

Just copy the code below and paste within your html code:

```
<a href="https://www.scimagojr.com" style="display: inline-block; width: 100px; height: 15px; background-color: #f0f0f0; border: 1px solid #ccc;">
```

**SCImago Graphica**

Explore, visually communicate and make sense of data with our [new data visualization tool](#).

Metrics based on Scopus® data as of April 2022

**R** rana adnan 7 months ago

Dear sir  
i  
I want to submit my article in your journal, i am phd student in analytical chemistry and i worked very hard on my article to be at the journal level.  
with best regards

reply



**Melanie Ortiz** 7 months ago

SCImago Team

Dear Rana,  
Thank you for contacting us.  
We are sorry to tell you that SCImago Journal & Country Rank is not a journal. SJR is a portal with scientometric indicators of journals indexed in Elsevier/Scopus.  
We suggest you visit the journal's homepage (See submission/author guidelines) or contact the journal's editorial staff , so they could inform you more deeply.  
Best Regards, SCImago Team

Leave a comment

Name

Email

(will not be published)

[Submit](#)

The users of Scimago Journal & Country Rank have the possibility to dialogue through comments linked to a specific journal. The purpose is to have a forum in which general doubts about the processes of publication in the journal, experiences and other issues derived from the publication of papers are resolved. For topics on particular articles, maintain the dialogue through the usual channels with your editor.

Developed by:



Powered by:

Follow us on [@ScimagoJR](#)

Scimago Lab, Copyright 2007-2022. Data Source: Scopus®

The logo for 'EST MODUS IN REBUS' features the Latin phrase in a serif font, with the subtitle 'Hortatio (Salvo 1.1.106)' in a smaller font below it, all contained within a dark rectangular box.

[Cookie settings](#)[Cookie policy](#)





# Source details

## South African Journal of Chemical Engineering

Open Access ⓘ

Scopus coverage years: from 2016 to Present

Publisher: Elsevier

E-ISSN: 1026-9185

Subject area: Social Sciences: Education Chemical Engineering: Fluid Flow and Transfer Processes Energy: Energy (miscellaneous)

Chemical Engineering: Filtration and Separation [View all](#) ▾

Source type: Journal

CiteScore 2021

6.8 ⓘ

SJR 2021

0.760 ⓘ

SNIP 2021

1.583 ⓘ

[View all documents](#) >

[Set document alert](#)

[Save to source list](#) [Source Homepage](#)

[CiteScore](#) [CiteScore rank & trend](#) [Scopus content coverage](#)

CiteScore 2021 ▾

$$6.8 = \frac{1,228 \text{ Citations 2018 - 2021}}{181 \text{ Documents 2018 - 2021}}$$

Calculated on 05 May, 2022

CiteScoreTracker 2022 ⓘ

$$6.9 = \frac{1,657 \text{ Citations to date}}{241 \text{ Documents to date}}$$

Last updated on 05 April, 2023 • Updated monthly

### CiteScore rank 2021 ⓘ

Category	Rank	Percentile
Social Sciences		
Education	#61/1406	95th
Chemical Engineering		
Fluid Flow and Transfer Processes	#10/87	89th
Energy		
Energy (miscellaneous)	#7/34	80th

[View CiteScore methodology](#) > [CiteScore FAQ](#) > [Add CiteScore to your site](#) 🌐

---

## About Scopus

[What is Scopus](#)

[Content coverage](#)

[Scopus blog](#)

[Scopus API](#)

[Privacy matters](#)

## Language

[日本語版を表示する](#)

[查看简体中文版本](#)

[查看繁體中文版本](#)

[Просмотр версии на русском языке](#)

## Customer Service

[Help](#)

[Tutorials](#)

[Contact us](#)

---

## ELSEVIER

[Terms and conditions](#) ↗ [Privacy policy](#) ↗

Copyright © Elsevier B.V. ↗ . All rights reserved. Scopus® is a registered trademark of Elsevier B.V.

We use cookies to help provide and enhance our service and tailor content. By continuing, you agree to the use of cookies ↗.

